AD-A185 440 MECHANICAL PROPERTY EVALUATION OF A SERIES OF COOMERCIAL TUNGSTEN ALLOYS(U) ARMY BALLISTIC RESEARCH LAB ABERDEEN PROVING GROUND MD W J BRUCHEY ET AL. JUN 87 BRL-MR-3606

1/1

UNCLASSIFIED F/G 11/6.1 NL

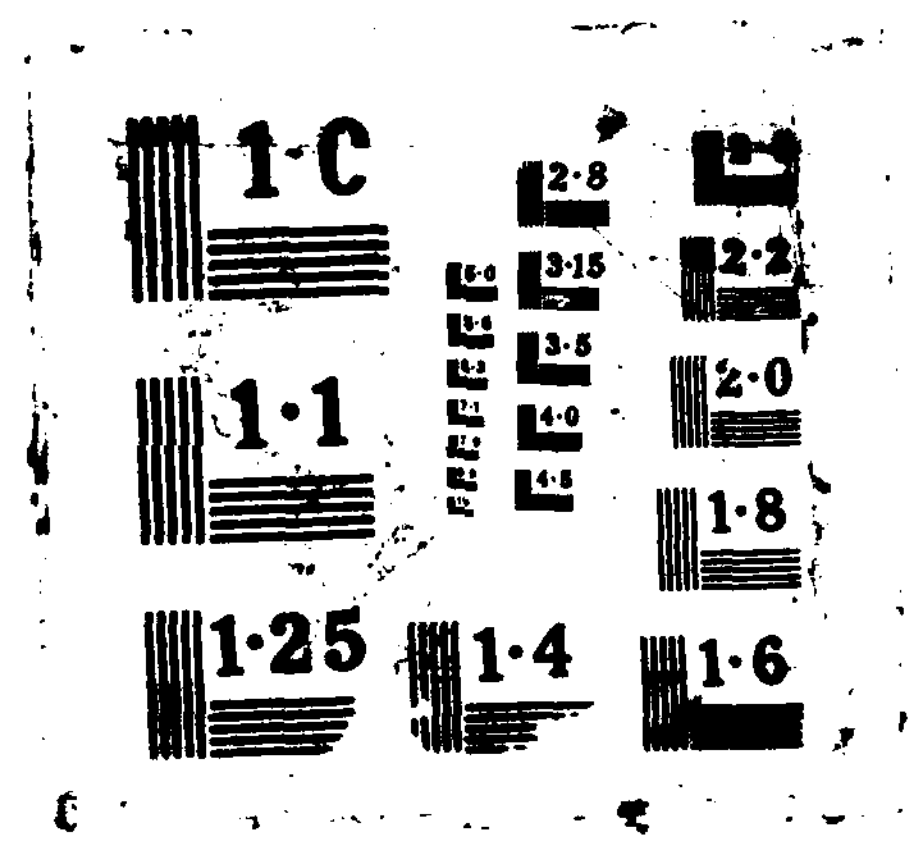
1·0
1·1
1·25
1·4
1·6
1·8
2·0
2·2
2·8
3·15
3·5
4·0
4·5

ADF300949

AD (13)

DTIC FILE COPY

AD-A185 440

MEMORANDUM REPORT BRL-MR-3606

MECHANICAL PROPERTY EVALUATION OF A SERIES OF COMMERCIAL TUNGSTEN ALLOYS

WILLIAM J. BRUCHEY, JR.
DENISE M. MONTIEL

JUNE 1987

US ARMY BALLISTIC RESEARCH LABORATORY
ABERDEEN PROVING GROUND, MARYLAND

87

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE

READ INSTRUCTIONS BEFORE COMPLETING FORM

1. REPORT NUMBER ARBRL-MR-	2. GOVT ACCESSION NO. AD-A185 440
3. RECIPIENT'S CATALOG NUMBER	
4. TITLE (and Subtitle) Mechanical Property Evaluation of a Series of Commercial Tungsten Alloys	5. TYPE OF REPORT & PERIOD COVERED
	6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) William J. Bruchey, Jr. Denise M. Montiel	8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS USA Ballistic Research Laboratory Terminal Ballistics Division, AMXBR-TBD Aberdeen Proving Ground, MD 21005-5066	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 1L161102AH43
11. CONTROLLING OFFICE NAME AND ADDRESS USA Ballistic Research Laboratory Terminal Ballistics Division, AMXBR-TBD Aberdeen Proving Ground, MD 21005-5066	12. REPORT DATE
	13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) Unclassified
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE

16. DISTRIBUTION STATEMENT (of this Report)

Approved for public release; distribution unlimited.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

18. SUPPLEMENTARY NOTES

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

Tungsten
Penetrator Materials
Tungsten Alloys
Ballistics
Mechanical Properties

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

A series of commercially available tungsten alloys ranging in tungsten content from 75% to 95% were evaluated. Typical tensile and compressive engineering properties are reported. These tests were conducted in support of penetrator ballistic test programs.

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

TABLE OF CONTENTS

LIST OF FIGURES

I. INTRODUCTION

During the conduct of a kinetic energy penetrator design study, the Penetration Mechanics Branch experienced unexpected ballistic performance variations from a series of tungsten materials. These materials contained 75% to 95% tungsten in a nickel-iron matrix. Examination of the firing data records did not reveal any unusual behavior which could be associated with either the penetrator design or the impact geometry. It was decided that the mechanical properties of the material should be determined independently of the manufacturer's advertised data.

Because there was some concern that the materials were actually at fault, the manufacturer agreed to supply a replacement material at no charge. Mechanical property tests were run on both the new and original batches of material to determine if the material had been improperly processed, or whether the manufacturer had changed the processing history for the material between the time of the last tests and the present ones.

This report covers the mechanical property data gathered by the Solid Mechanics Branch. At a later date, these results will be combined with ballistic performance data to determine the extent that the materials accounted for test variations.

II. EXPERIMENTAL PROCEDURES

The mechanical tests were conducted using an Instron electromechanical testing machine, with a load cell calibrated for a 10,000 Kg maximum load. The data was collected onto magnetic tapes with the aid of a Hewlett Packard data logger; programs written for the data logger were utilized to further reduce, analyze and plot the data.

All tensile specimens were of the SMB-1 type, illustrated in Figure 1. Two rosette strain gages were bonded to the center of the specimen, 180 apart. A one-inch extensometer was also incorporated into the setup to measure the strain-to-failure as accurately as possible. The crosshead speed used in every case was a rate of .02 cm/minute.

The compression specimens were all configured as shown in Figure 1. Three rosette strain gages were used in each instance, bonded with a 120 separation at the center of the specimen. Six of the specimens, Test Nos. 336-341, were tested at a crosshead speed of .005 cm/min, and four tests, Nos. 361-364, were run at a rate of .01 cm/min.

III. RESULTS

Following are the tensile and compressive properties of various tungsten materials supplied to the Solid Mechanics Branch for evaluation. Table I is a summary of the measured engineering properties for each of the materials tested. In the table, the abbreviation "SW" refers to the percent swaging to which the material was subjected. Figures 2-24 are the actual engineering stress-strain curves for each of the materials listed in Table I. All of the test specimens were provided by the AAI Corporation.

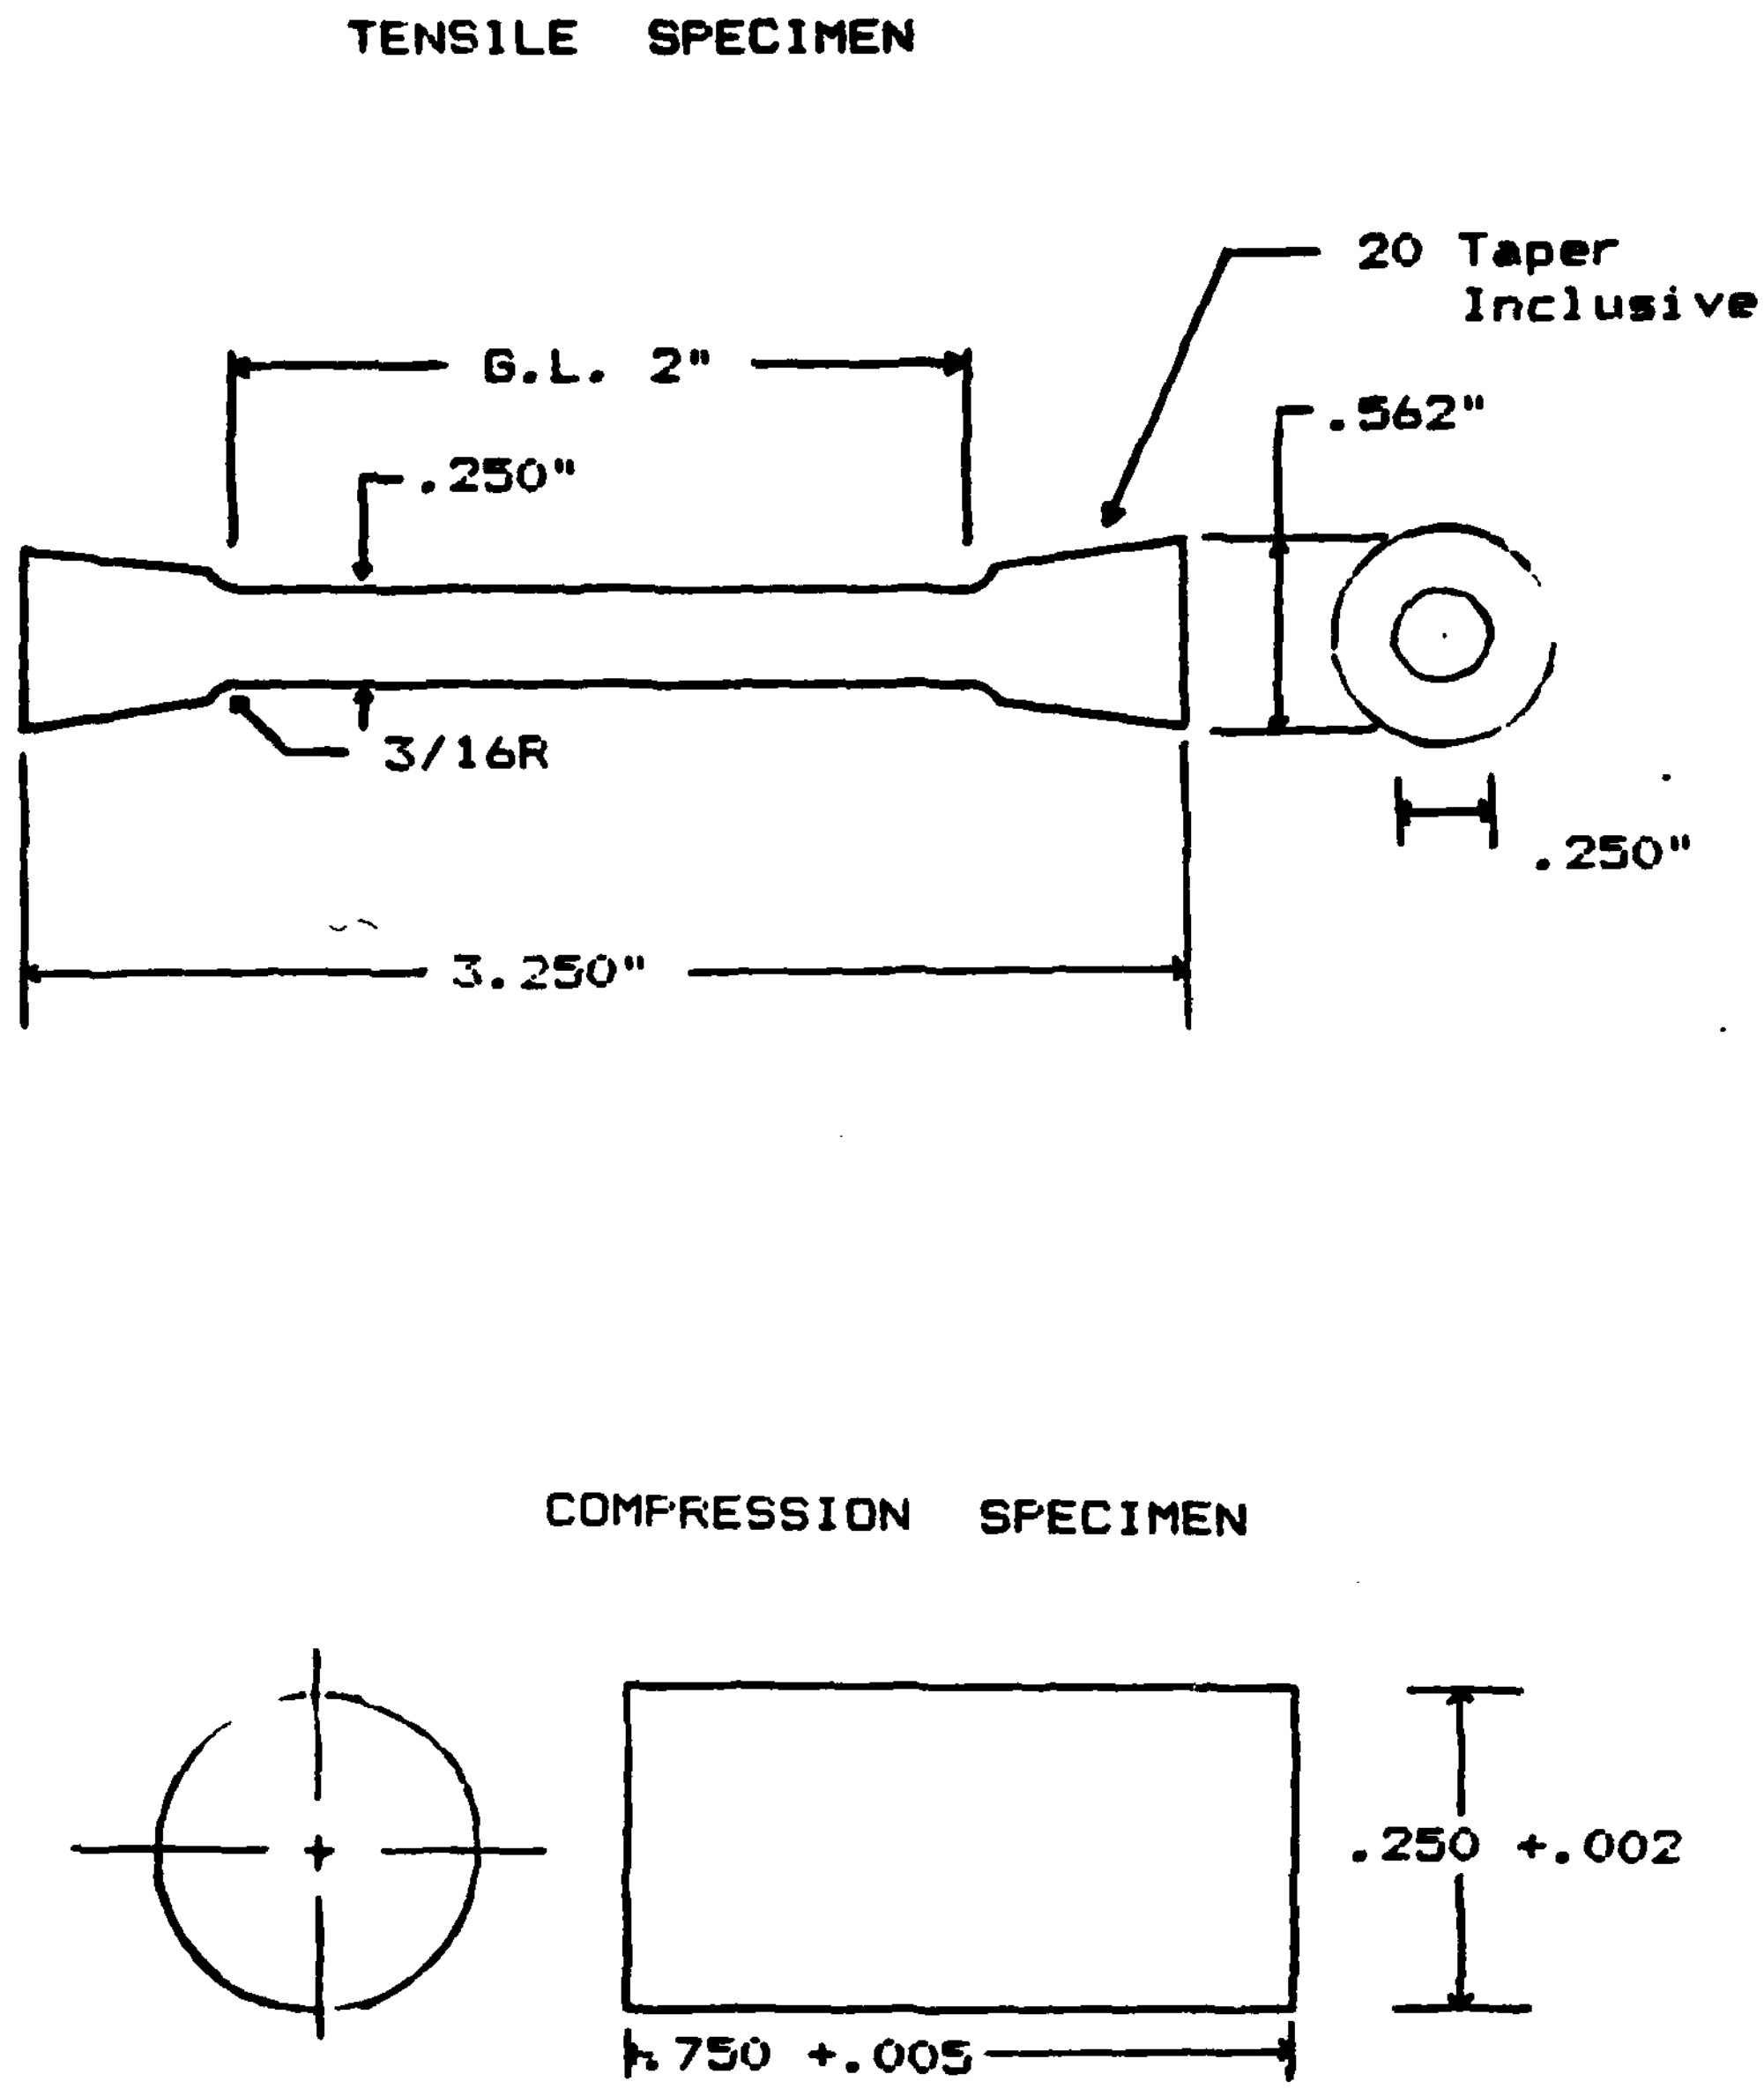

Figure 1. Test Specimen Configurations

(AAI) SPECIMEN REFERENCE NO.	TEST NO.	TENSILE	COMPRESSION	YIELD MPa .2%	YOUNG'S MODULUS GPa	BULK MODULUS GPa	POISSON'S RATIO	PLASTIC POISSON's RATIO	ULTIMATE STRESS MPa	ULTIMATE STRAIN %	FRACTURE STRESS MPa	FRACTURE STRAIN %
376 #1	324	X			298	278	.323	.465	830	14.28	825	15.71
376 #2	325	X			302	276	.319	.481	833	13.89	828	15.28
Tungsten 75% WA #1	326	X		507	267	230	.309	.449	764	14.96	764	14.96
75% WA #2	327	X		510	248	277	.351	.490	765	15.63	765	15.63
75% WA #3	334	X		493	244	275	.354	.456	738	18.20	738	18.20
75% WA 14% SW	357	X		907	260	260	.334	.491	960	6.98	950	6.98
"	358	X		924	275	261	.324	.466	970	5.12	960	7.40
75%	337		X	523	303	255	.303	.520				
"	340		X	517	291	226	.287	.479				
75% WA 21% SW	359	X		1,023	285	242	.304	.441	1,043	4.42	1,030	6.33
"	360	X		1,014	281	243	.308	.478	1,044	3.79	1,015	7.05
75% WA 14% SW	361		X	772	299	252	.303	.514				
"	362		X	724	287	220	.283	.455				
Tungsten 90% (R) WA #1	331	X		587	280	291	.341	.473	834	9.97	834	9.97
90% (R) WA #2	335	X		590	313	338	.347	.475	784	7.20	784	7.20
75% WA 21% SW	363		X	749	270	269	.334	.546				
"	364		X	707.	266	234	.313	.520				
Tungsten 90% (R) WA	336		X	578	340	294	.313	.515				
"	339		X	578	344	274	.294	.454				
Tungsten 95% WA #1	332	X		1,093	316	270	.305	.464	1,118	2.54	1,098	6.24
"	333	X		1,107	305	272	.314	.458	1,117	3.50	1,106	4.76
95%	338		X	820	343	263	.284	.545				
95%	341		X	810	345	267	.286	.493				

Table I. Tensile and Compression Data

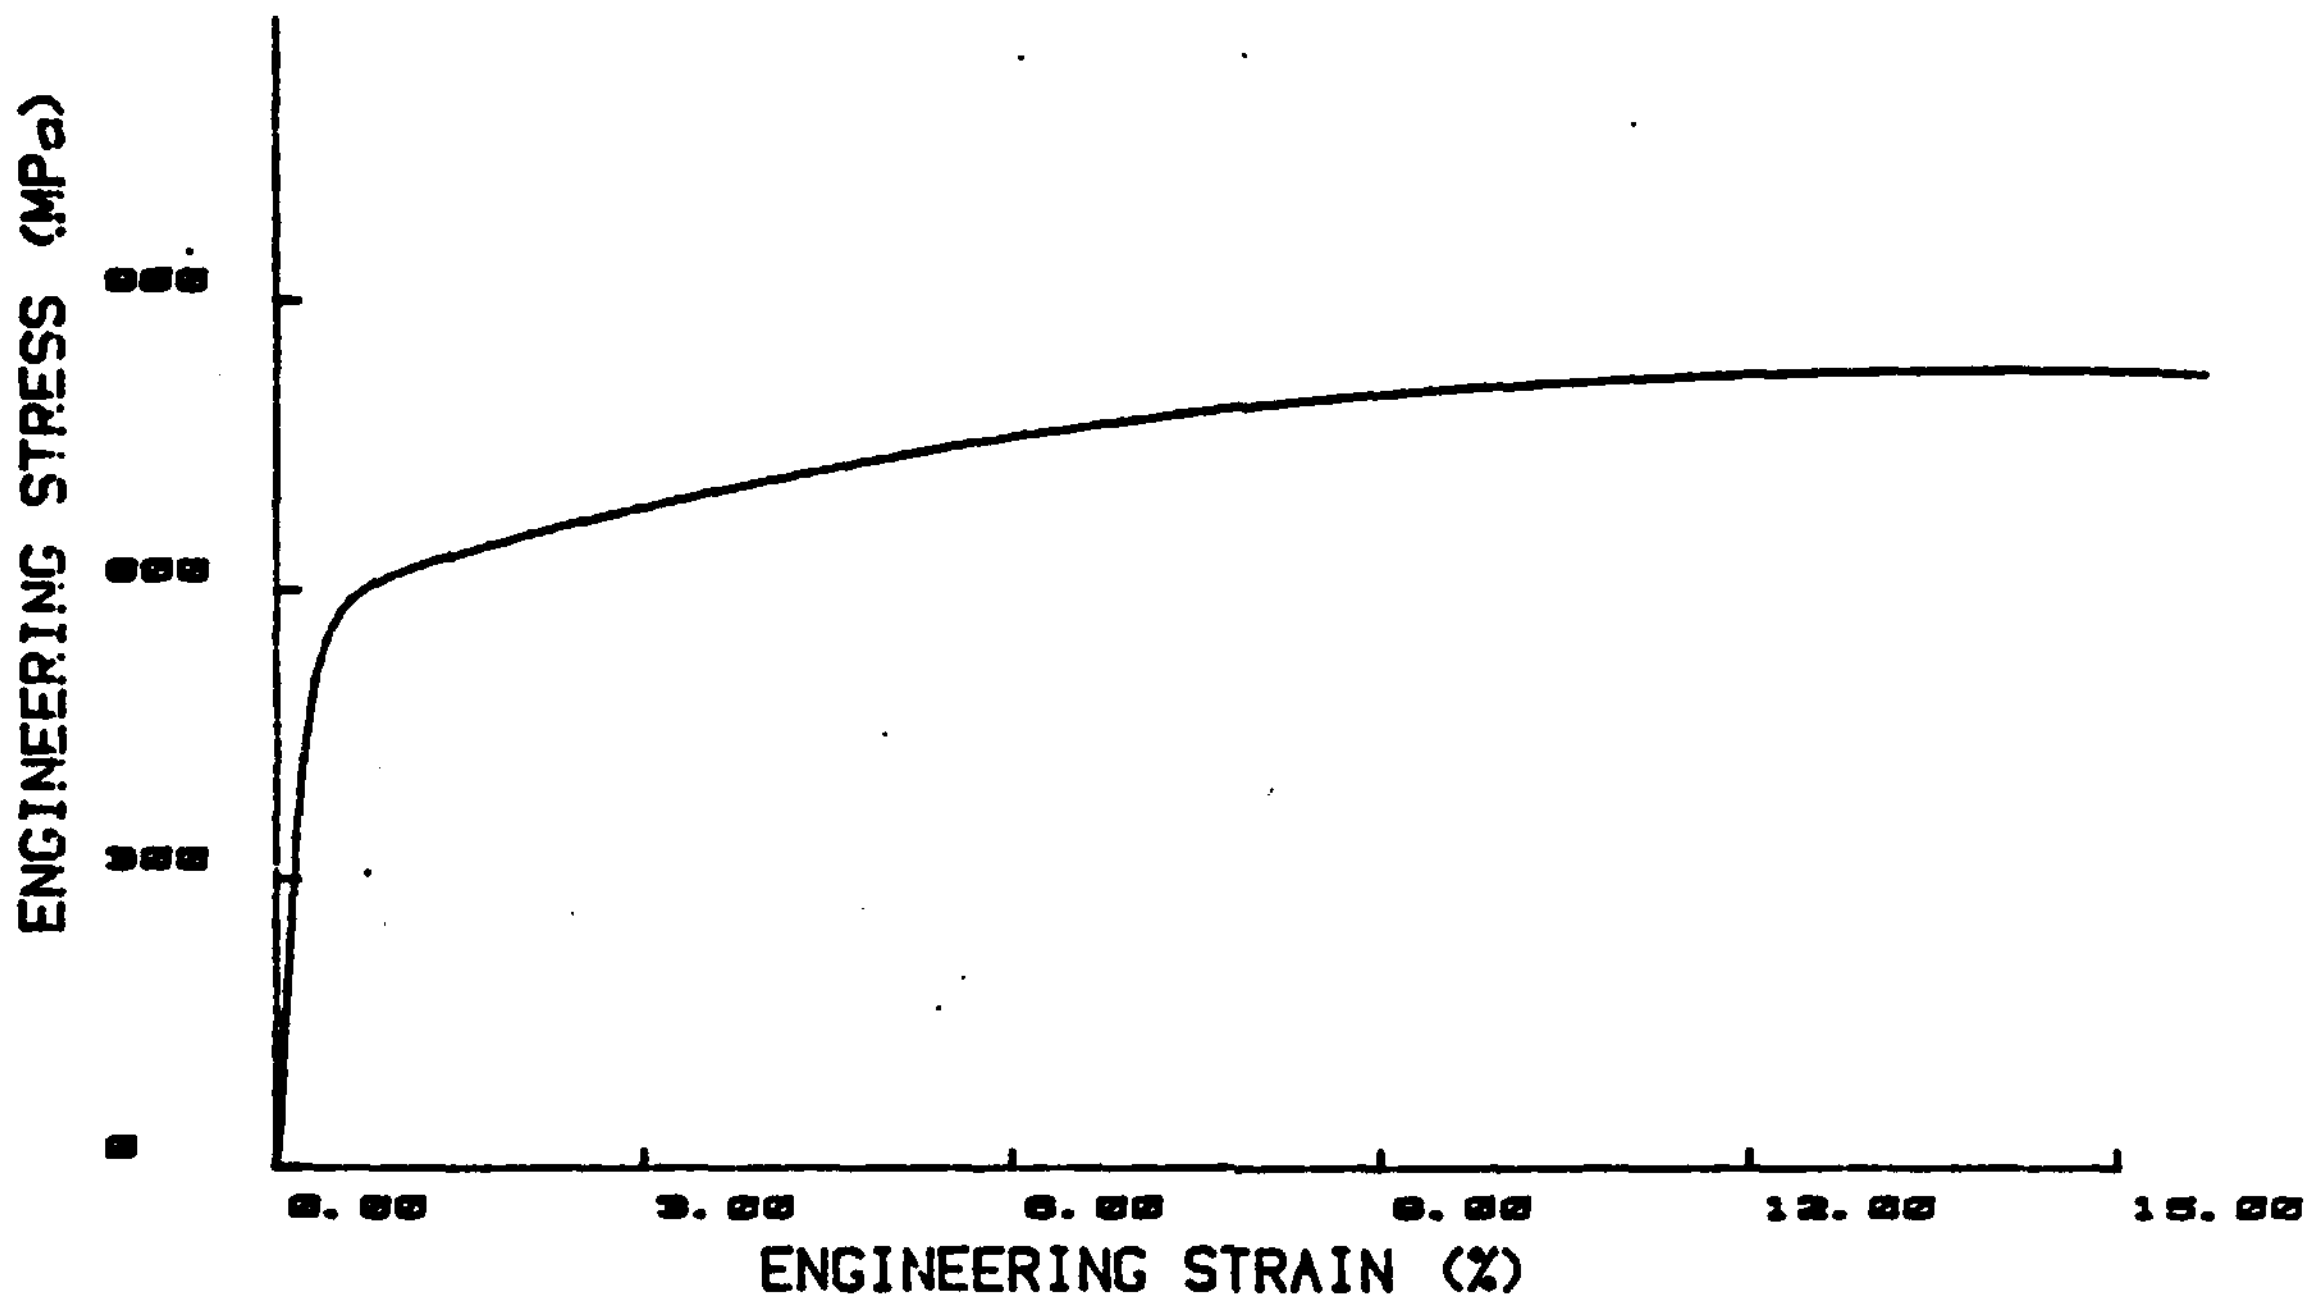

Figure 2. Uniaxial tensile stress-strain curve for initial lot 90% tungsten alloy, Specimen No. 324.

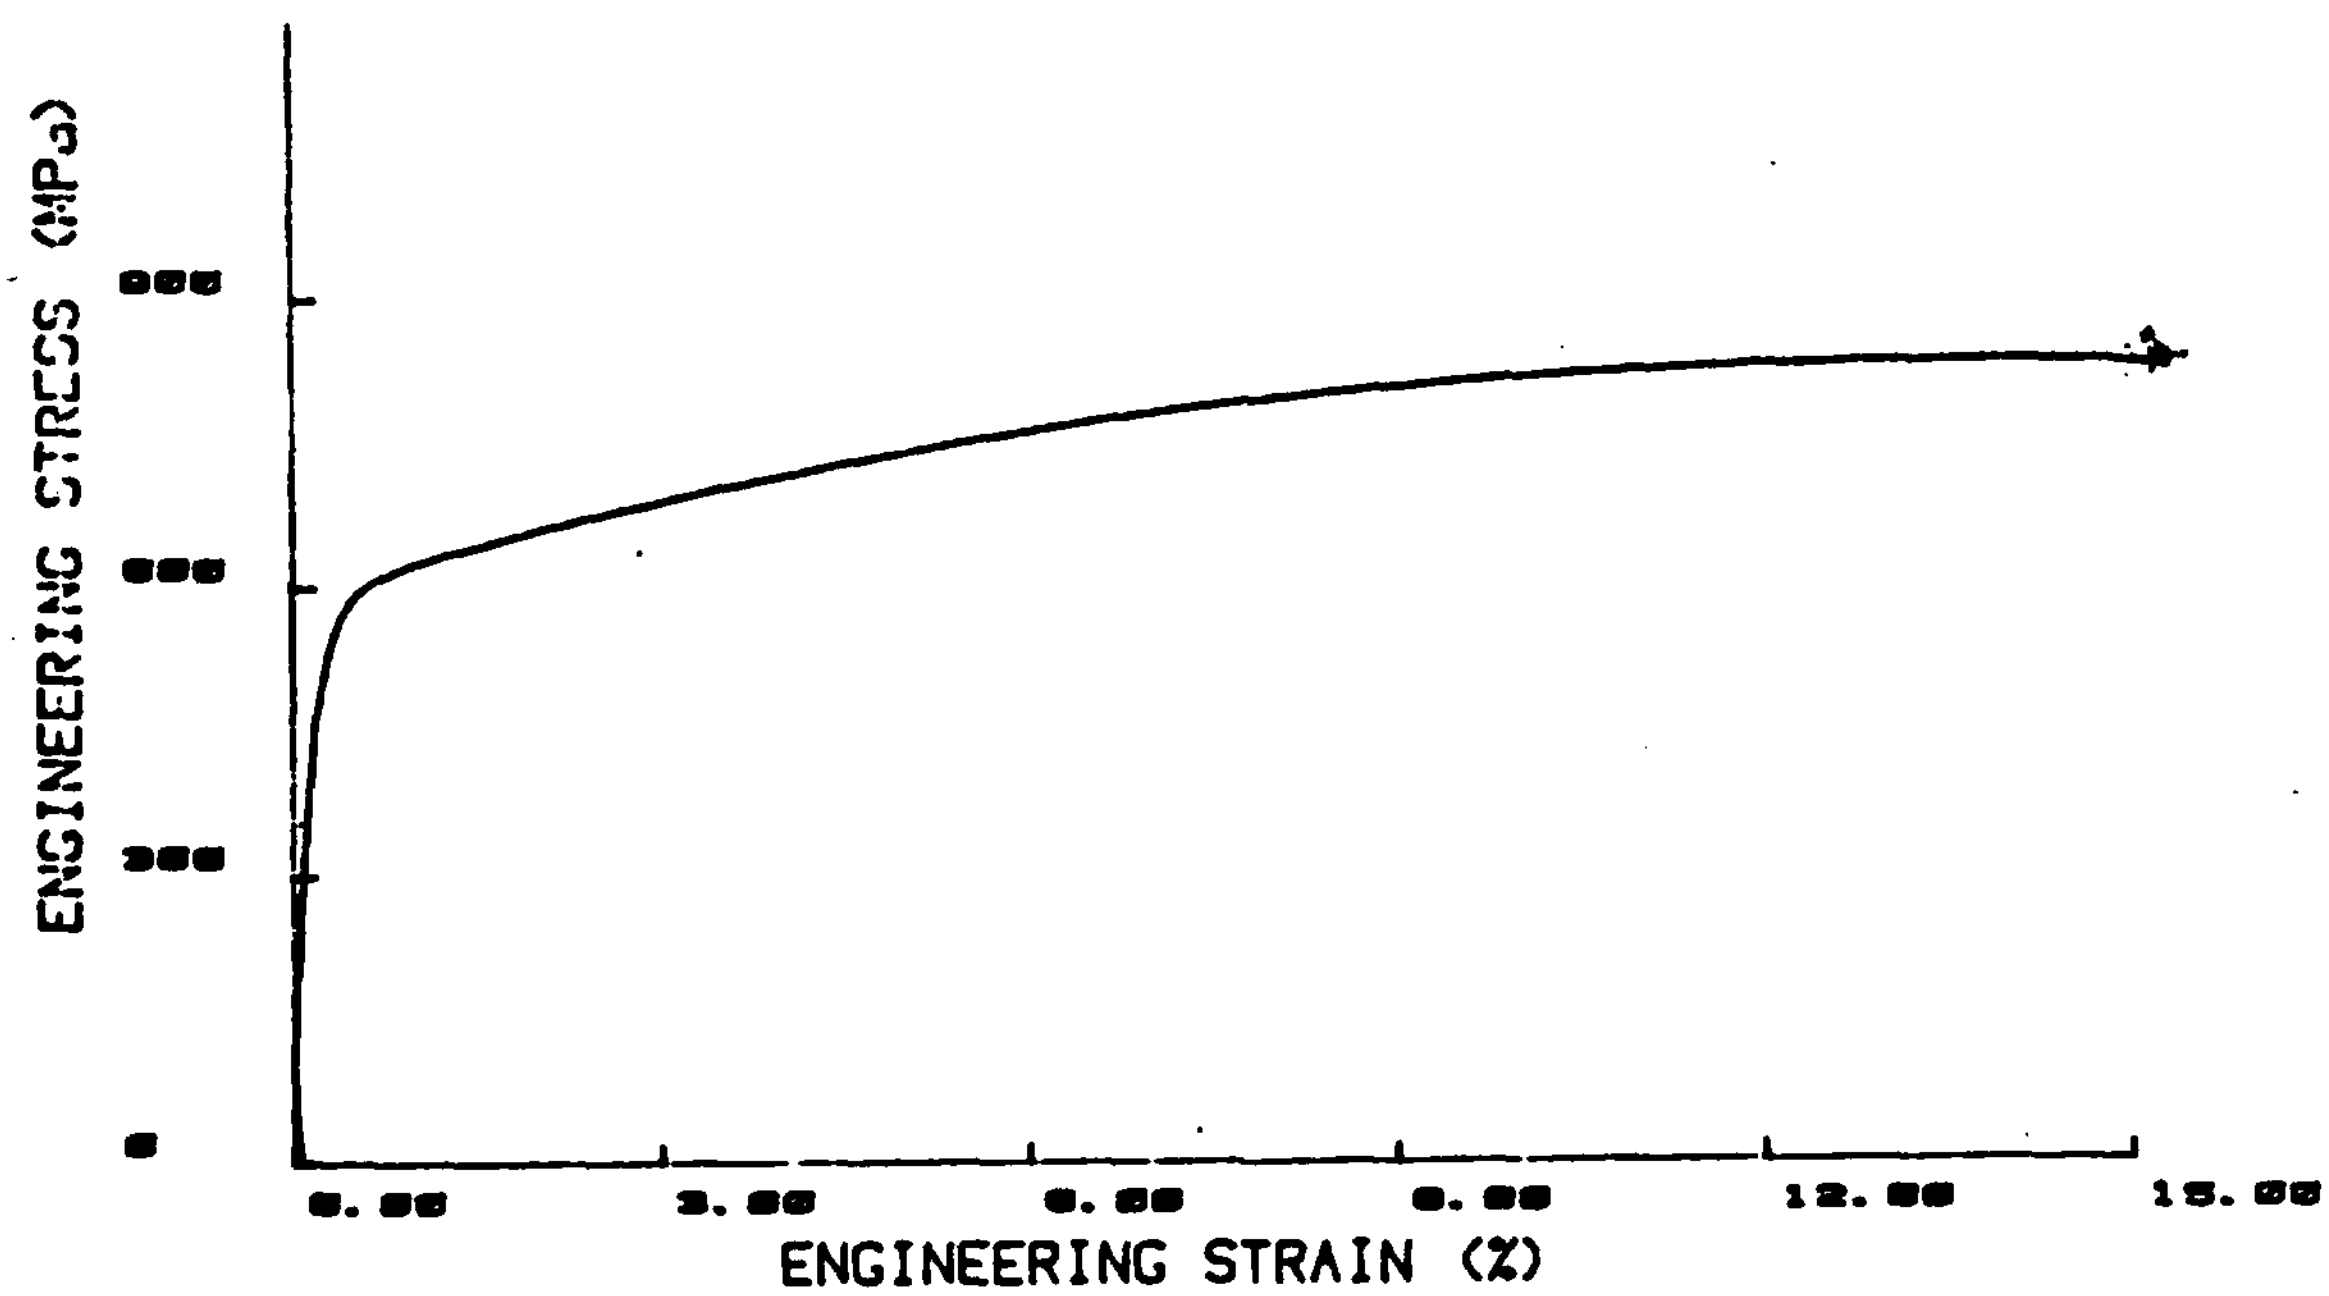

Figure 3. Uniaxial tensile stress-strain curve for initial lot 90% tungsten alloy, Specimen No. 325.

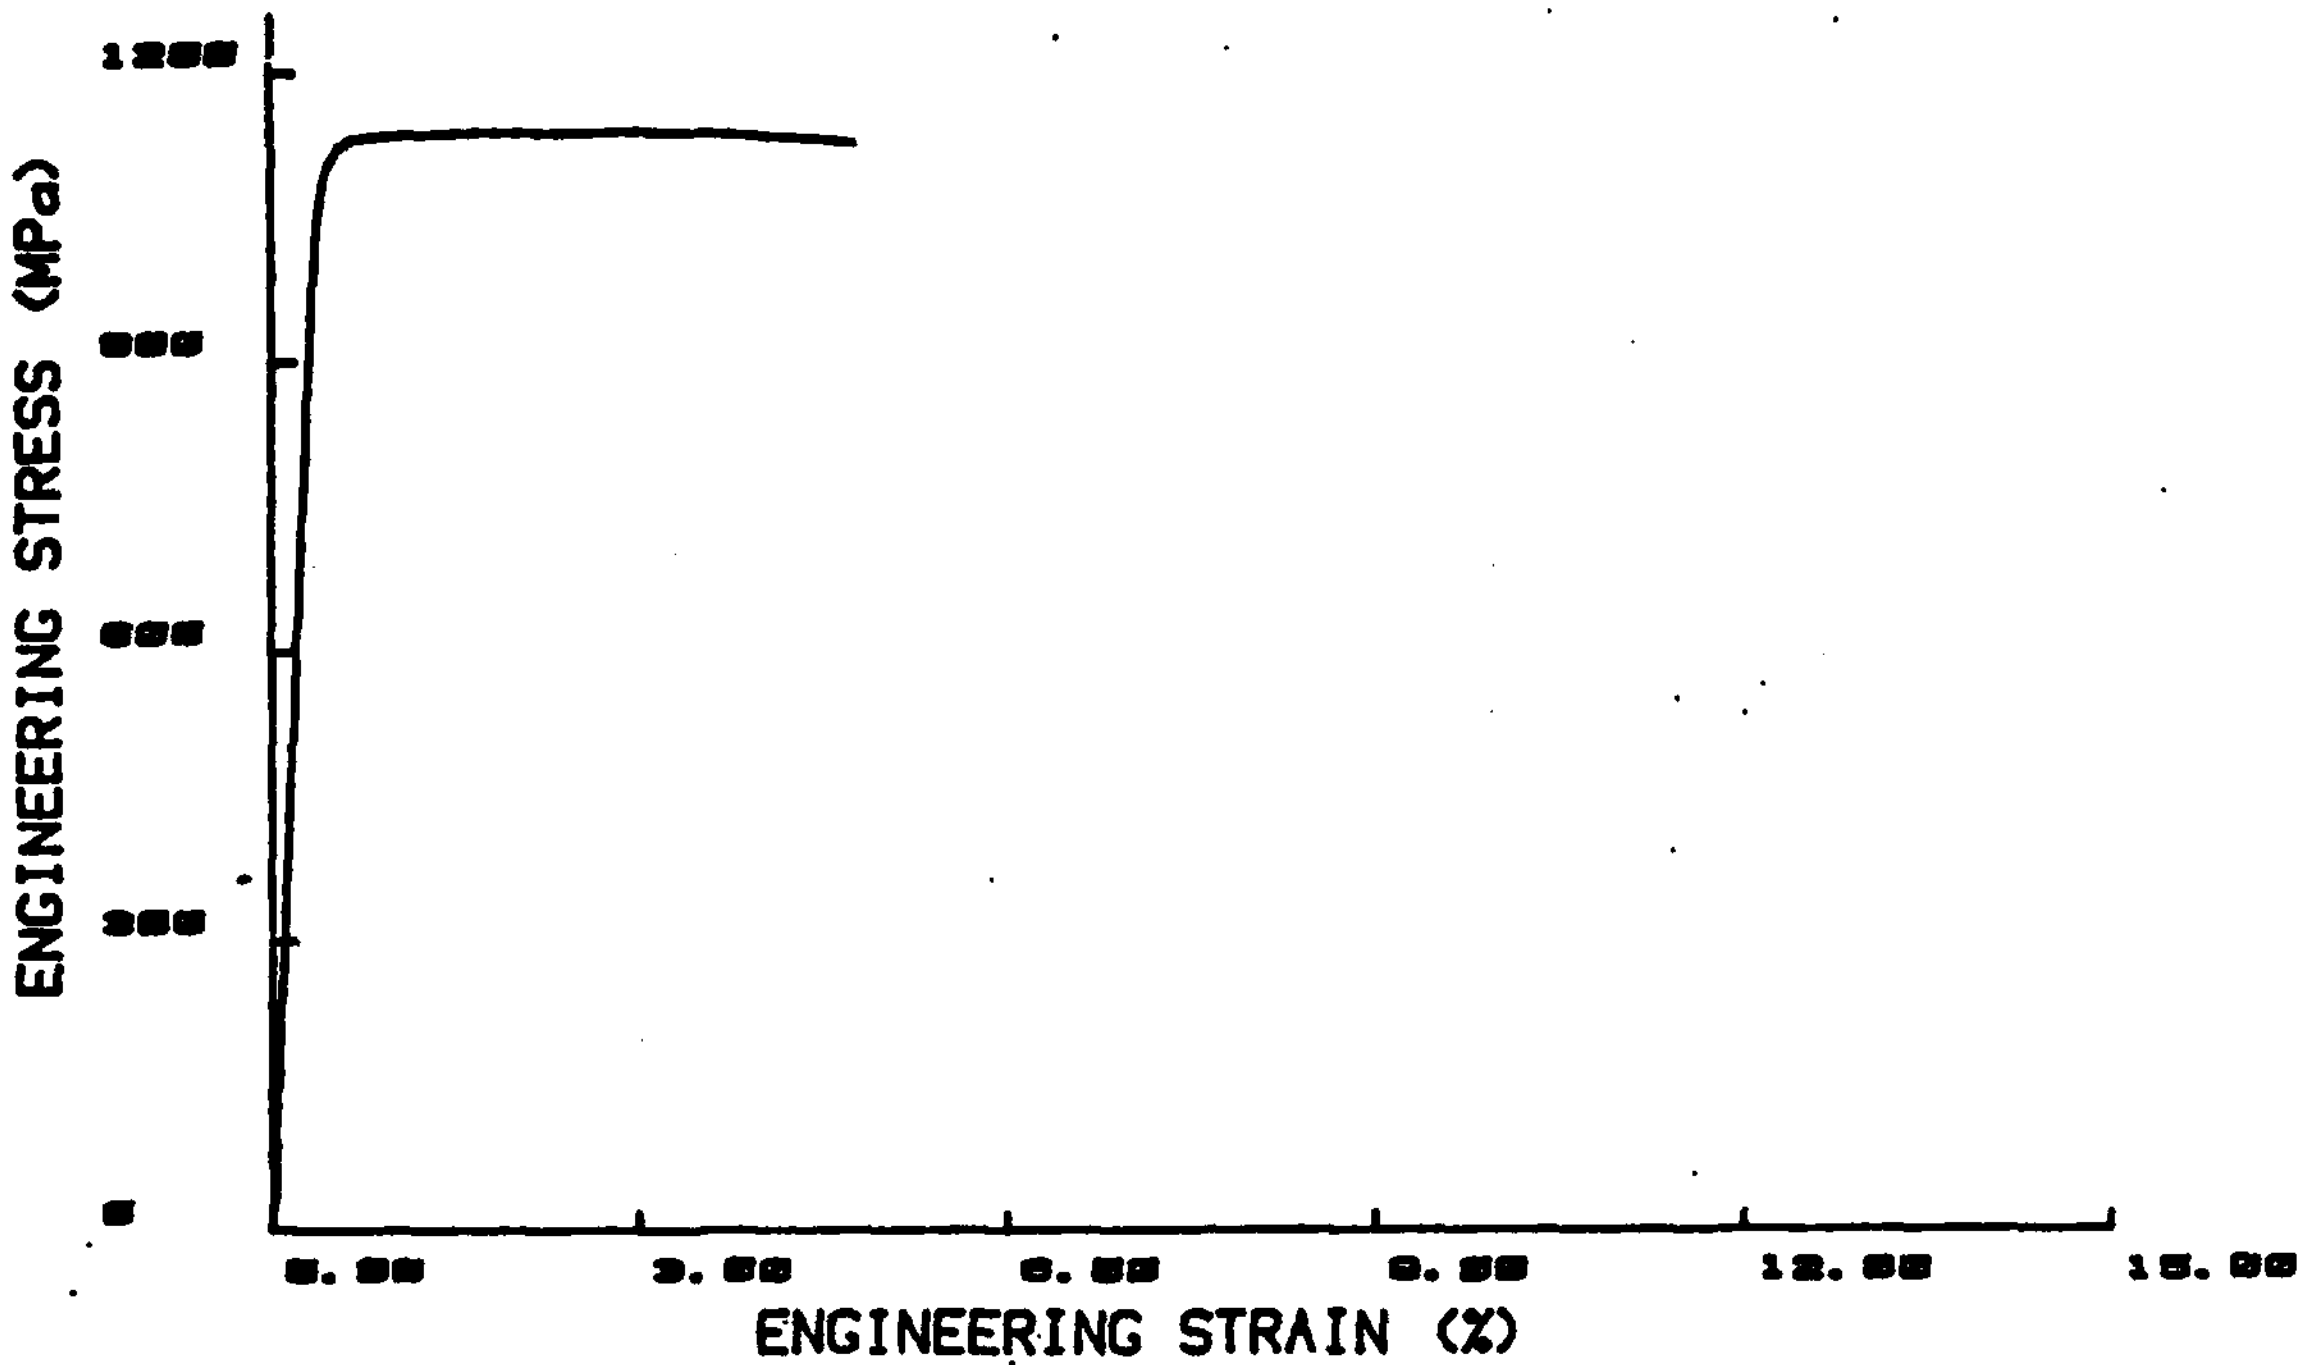

Figure 4. Uniaxial tensile stress-strain curve for a 95% tungsten alloy, Specimen No. 333.

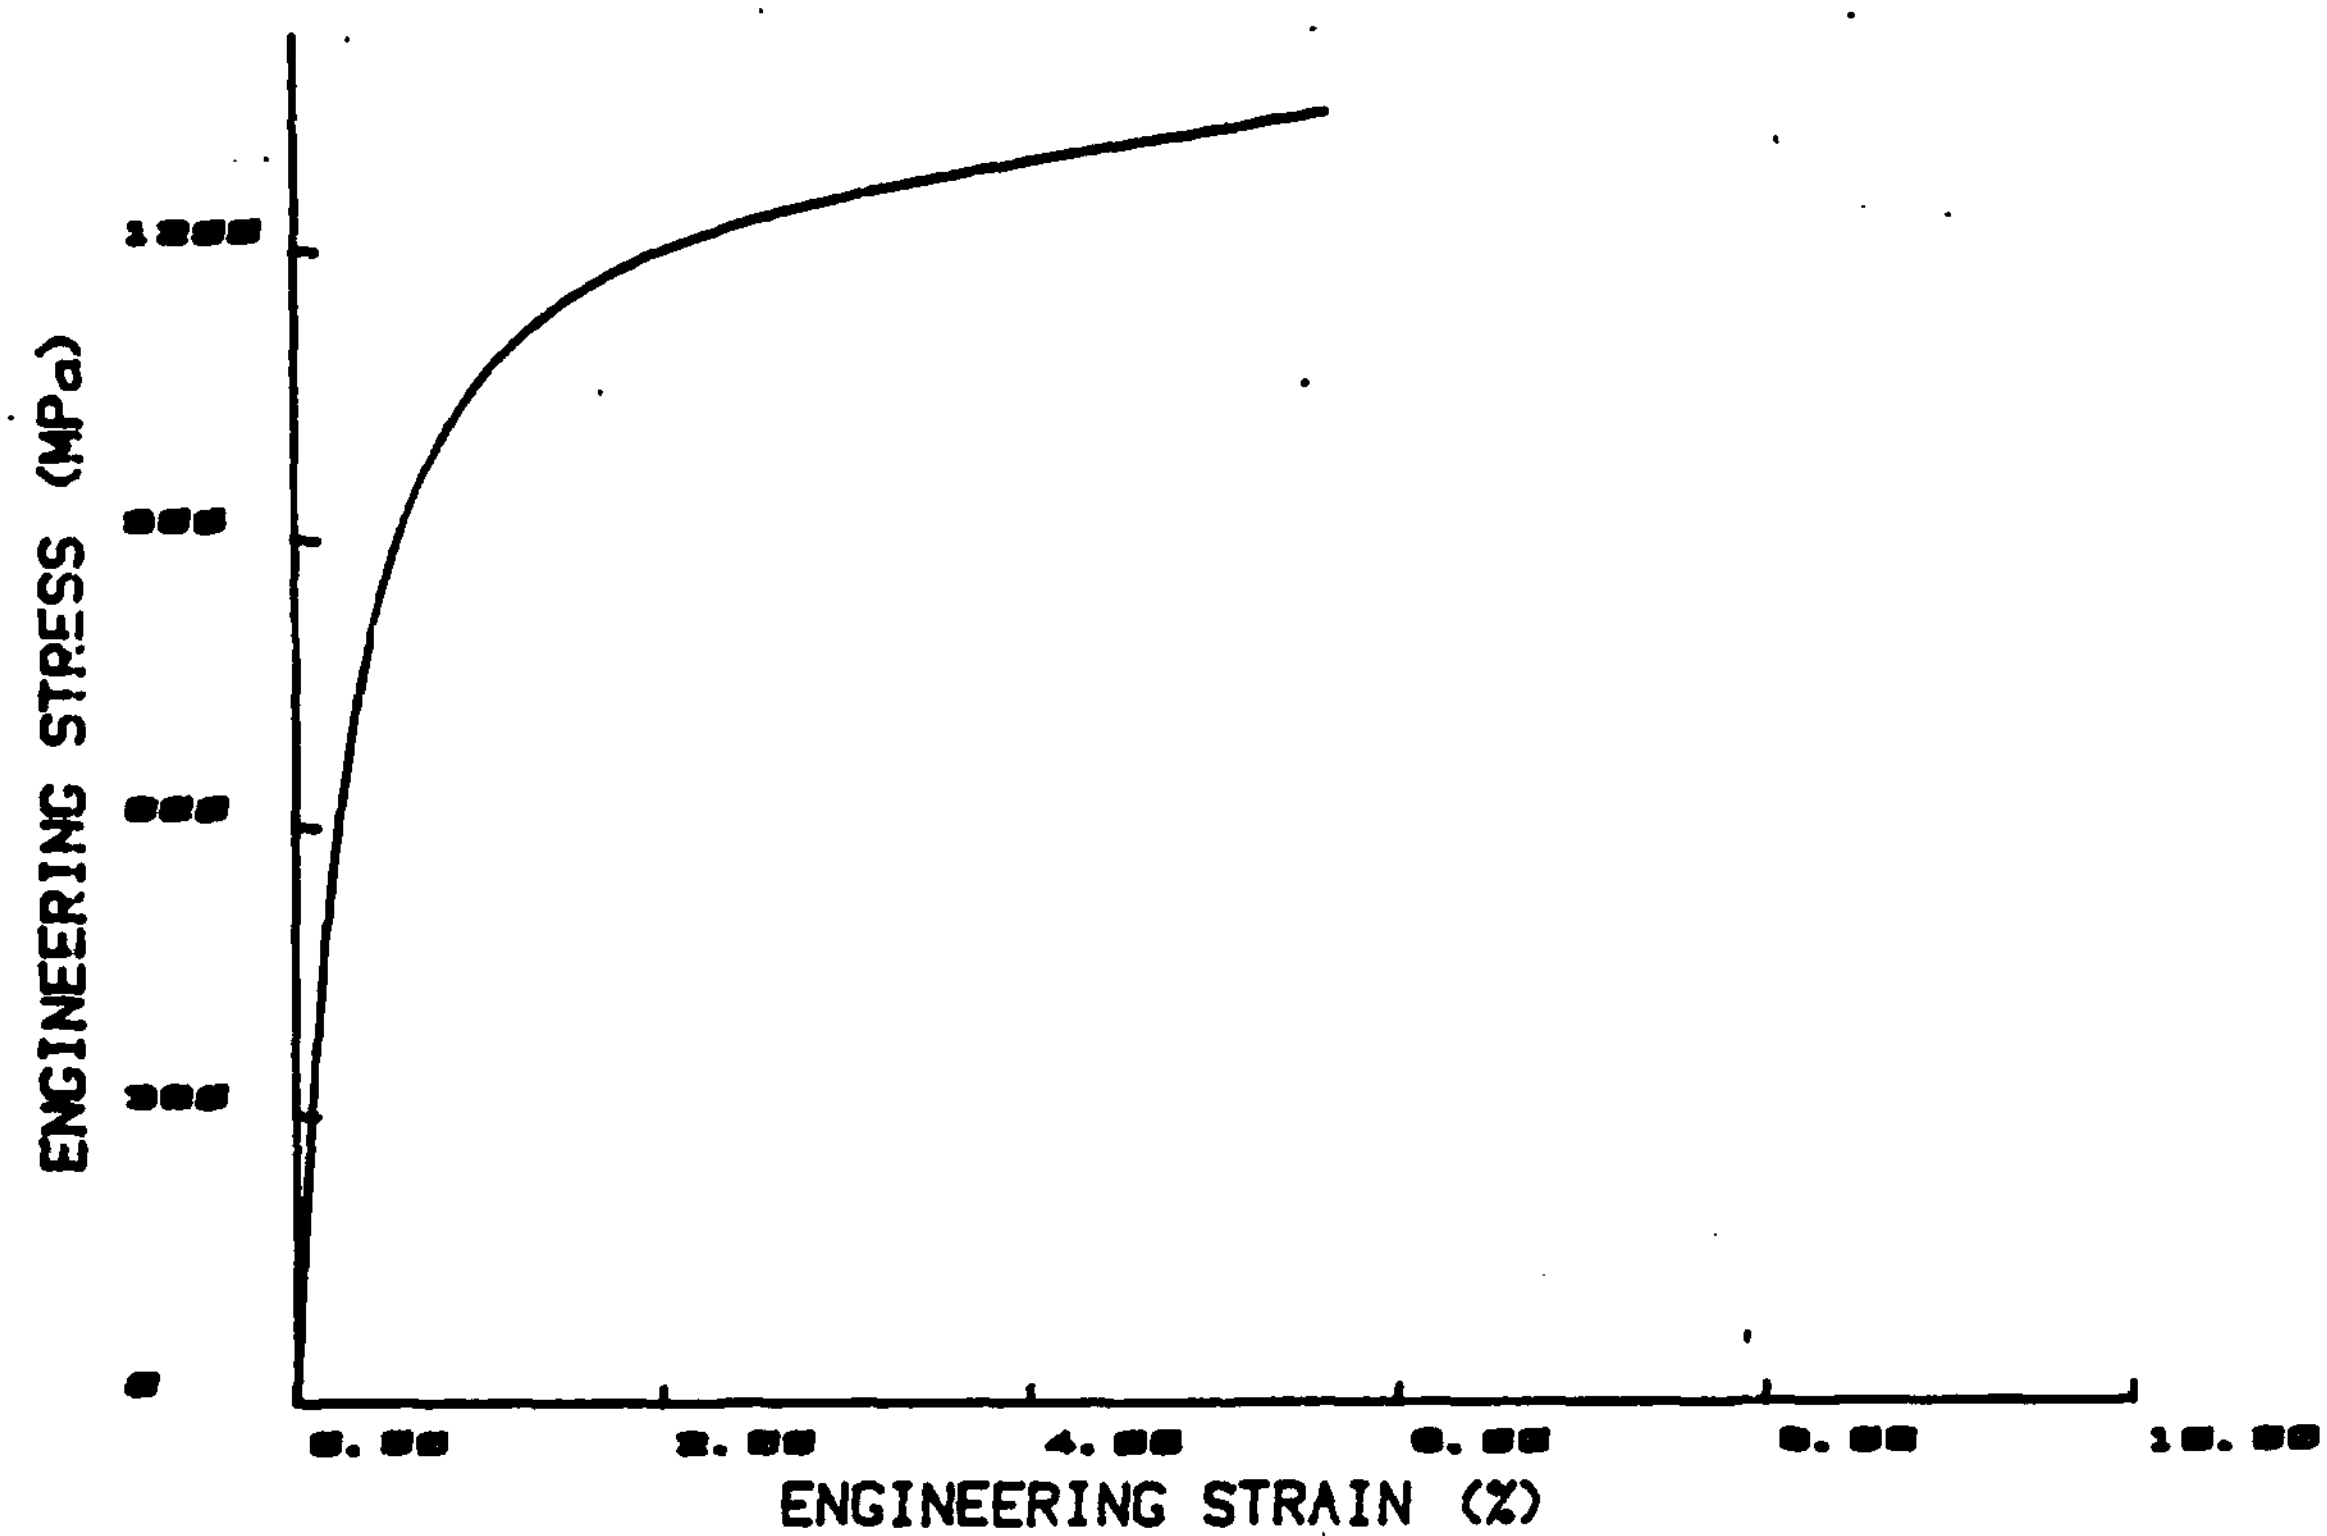

Figure 5. Uniaxial compressive stress-strain curve for a 95% tungsten alloy, Specimen No. 338.

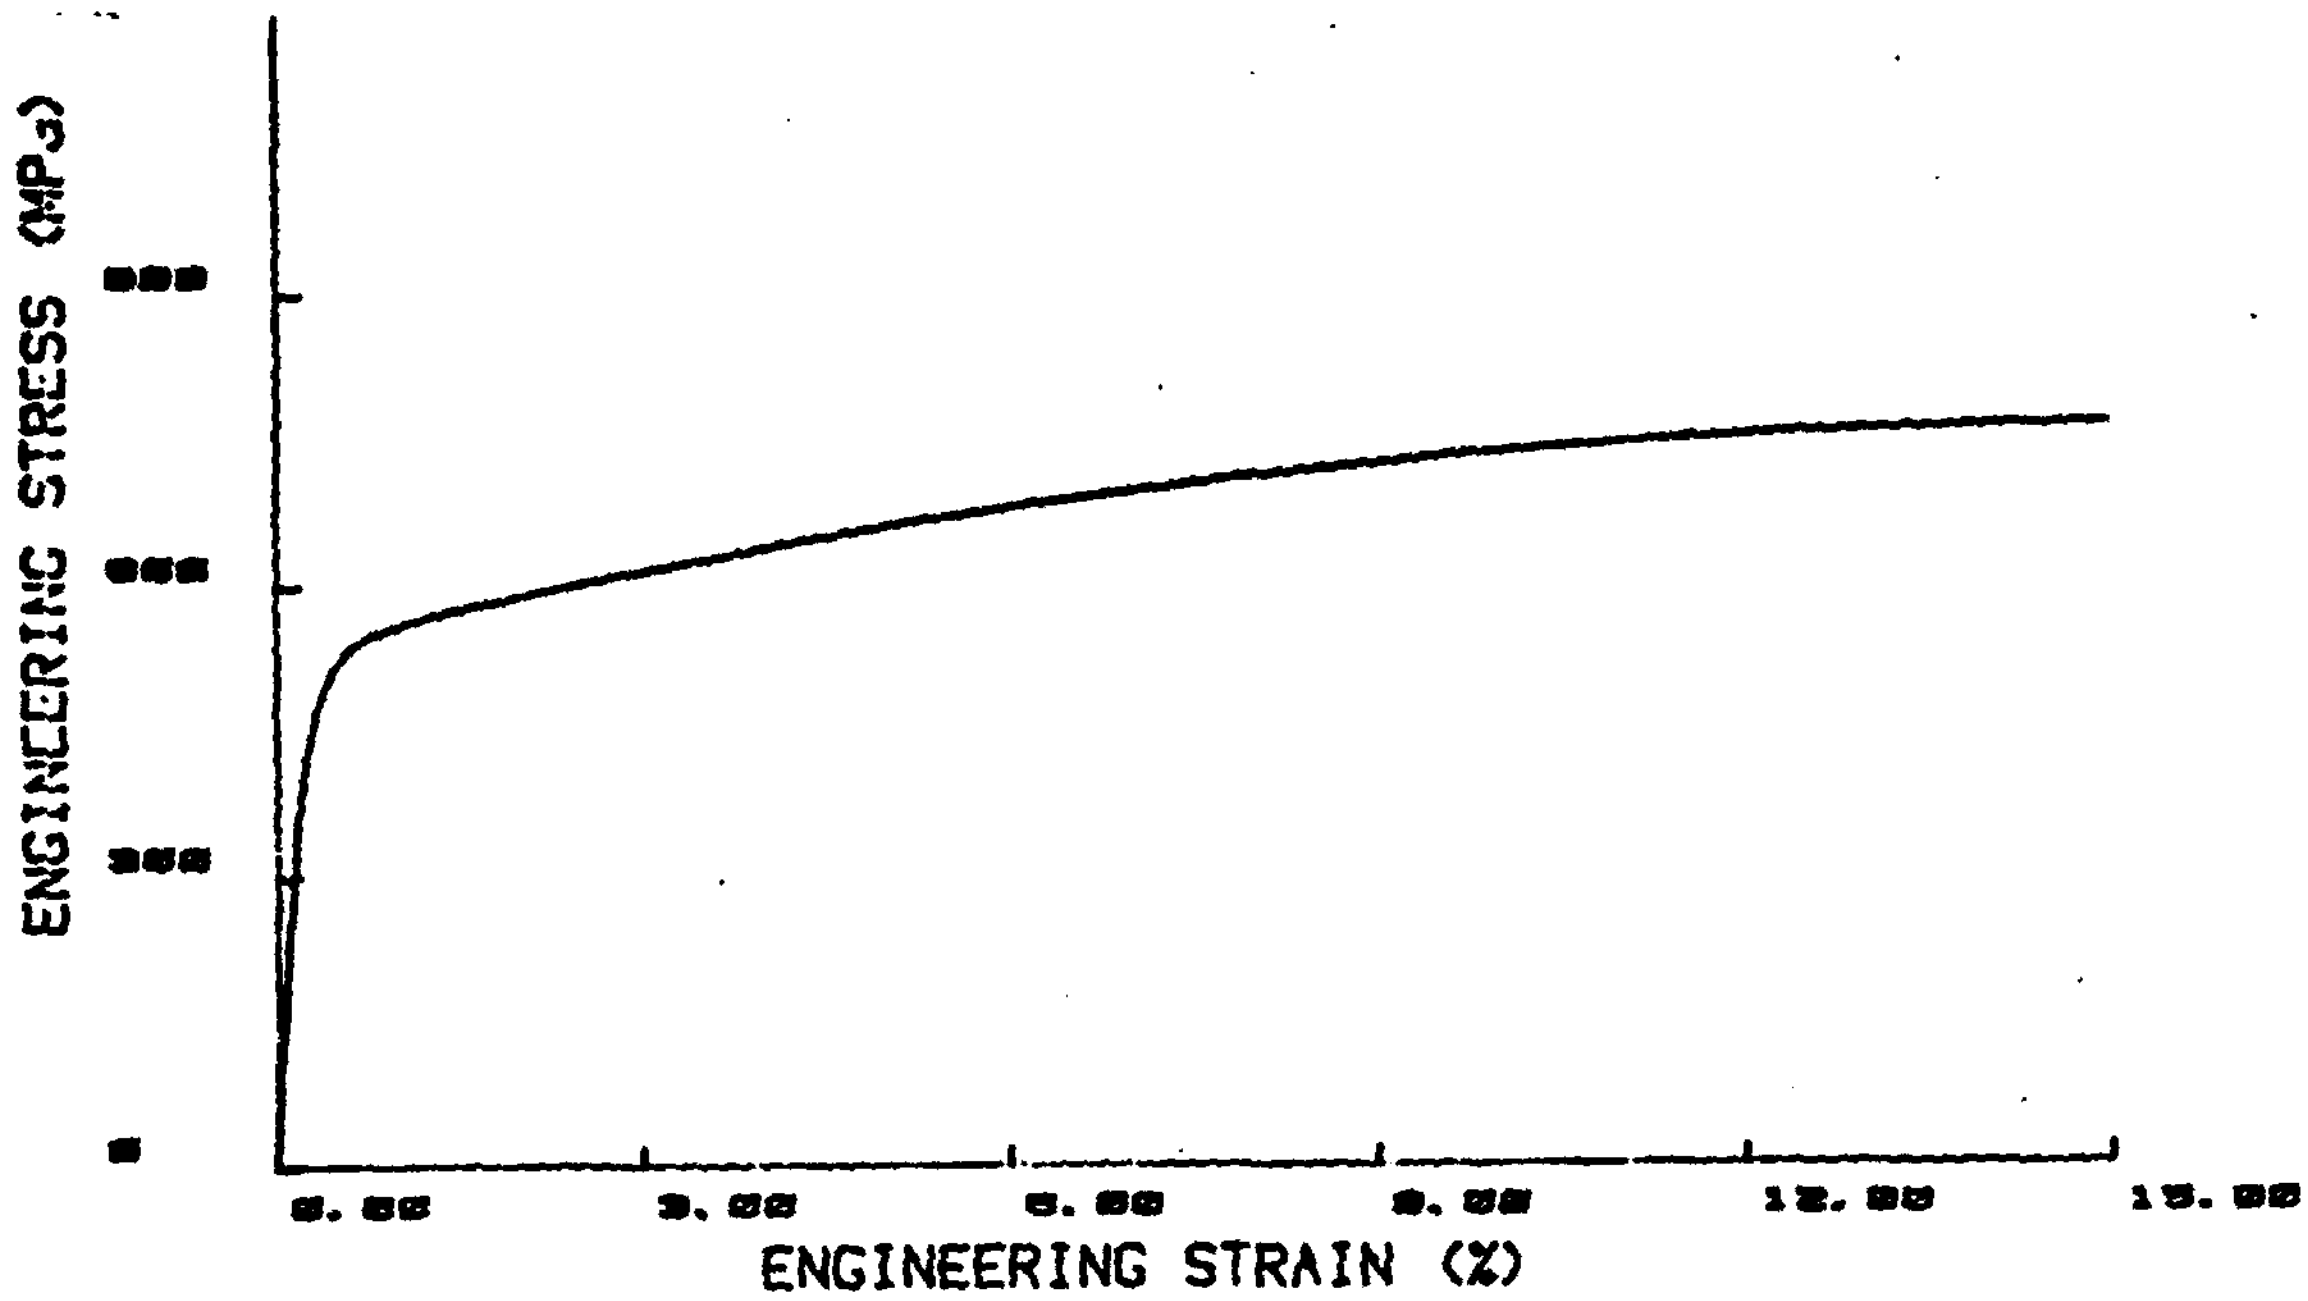

Figure 6. Uniaxial tensile stress-strain curve for an unswaged 75% tungsten alloy, Specimen No. 326.

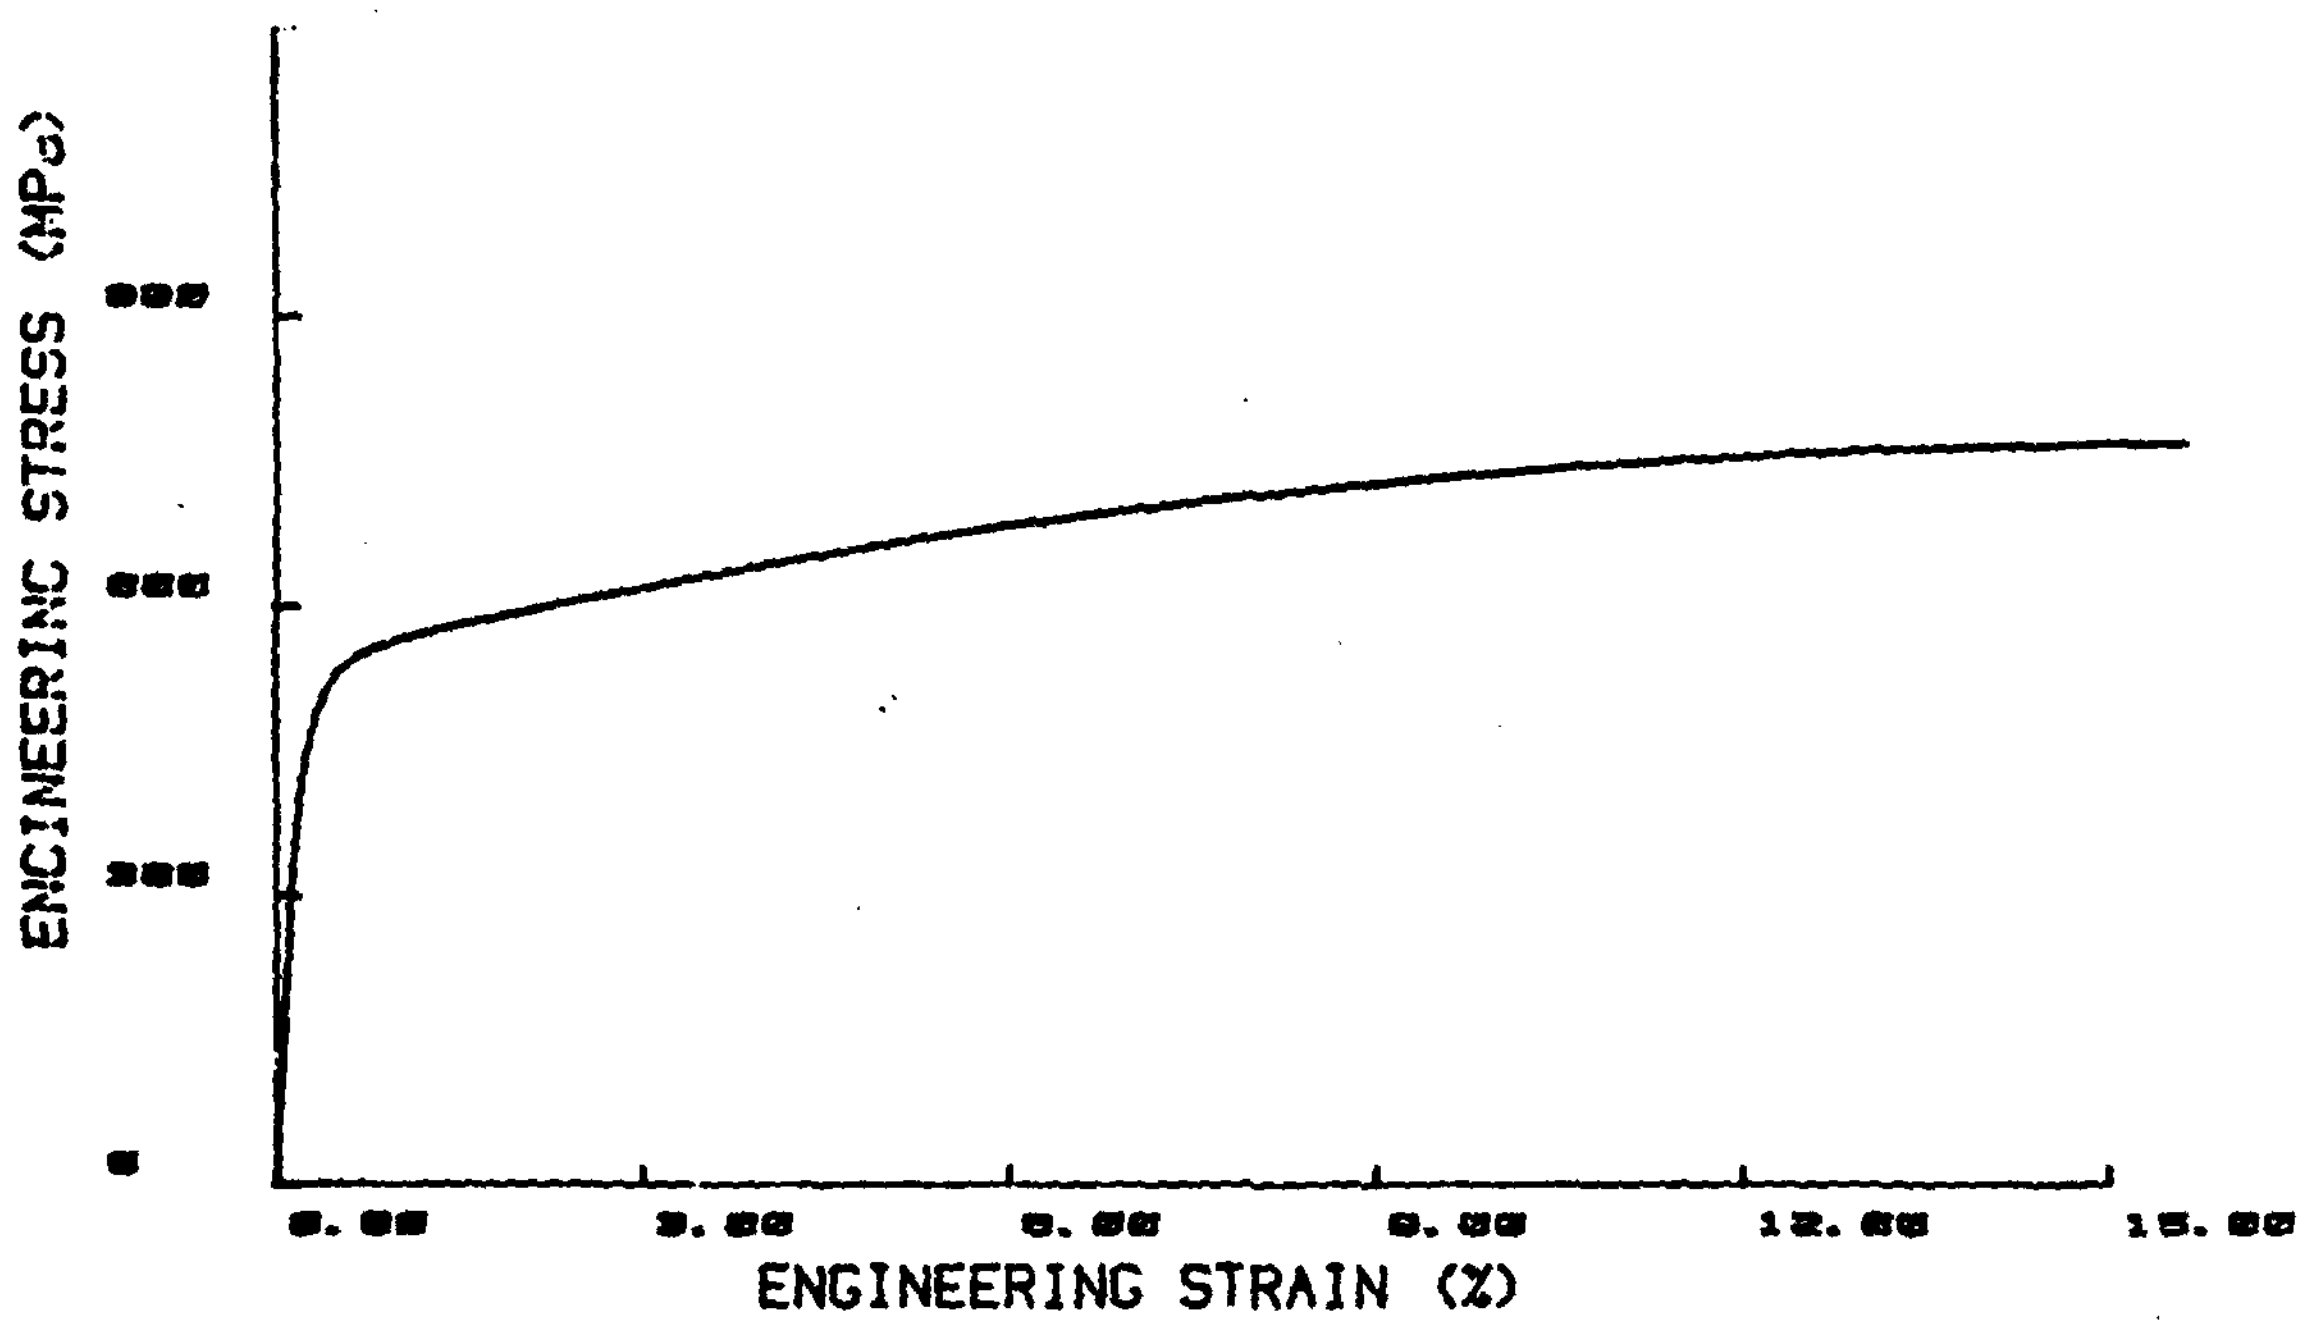

Figure 7. Uniaxial tensile stress-strain curve for an unswaged 75% tungsten alloy, Specimen No. 327.

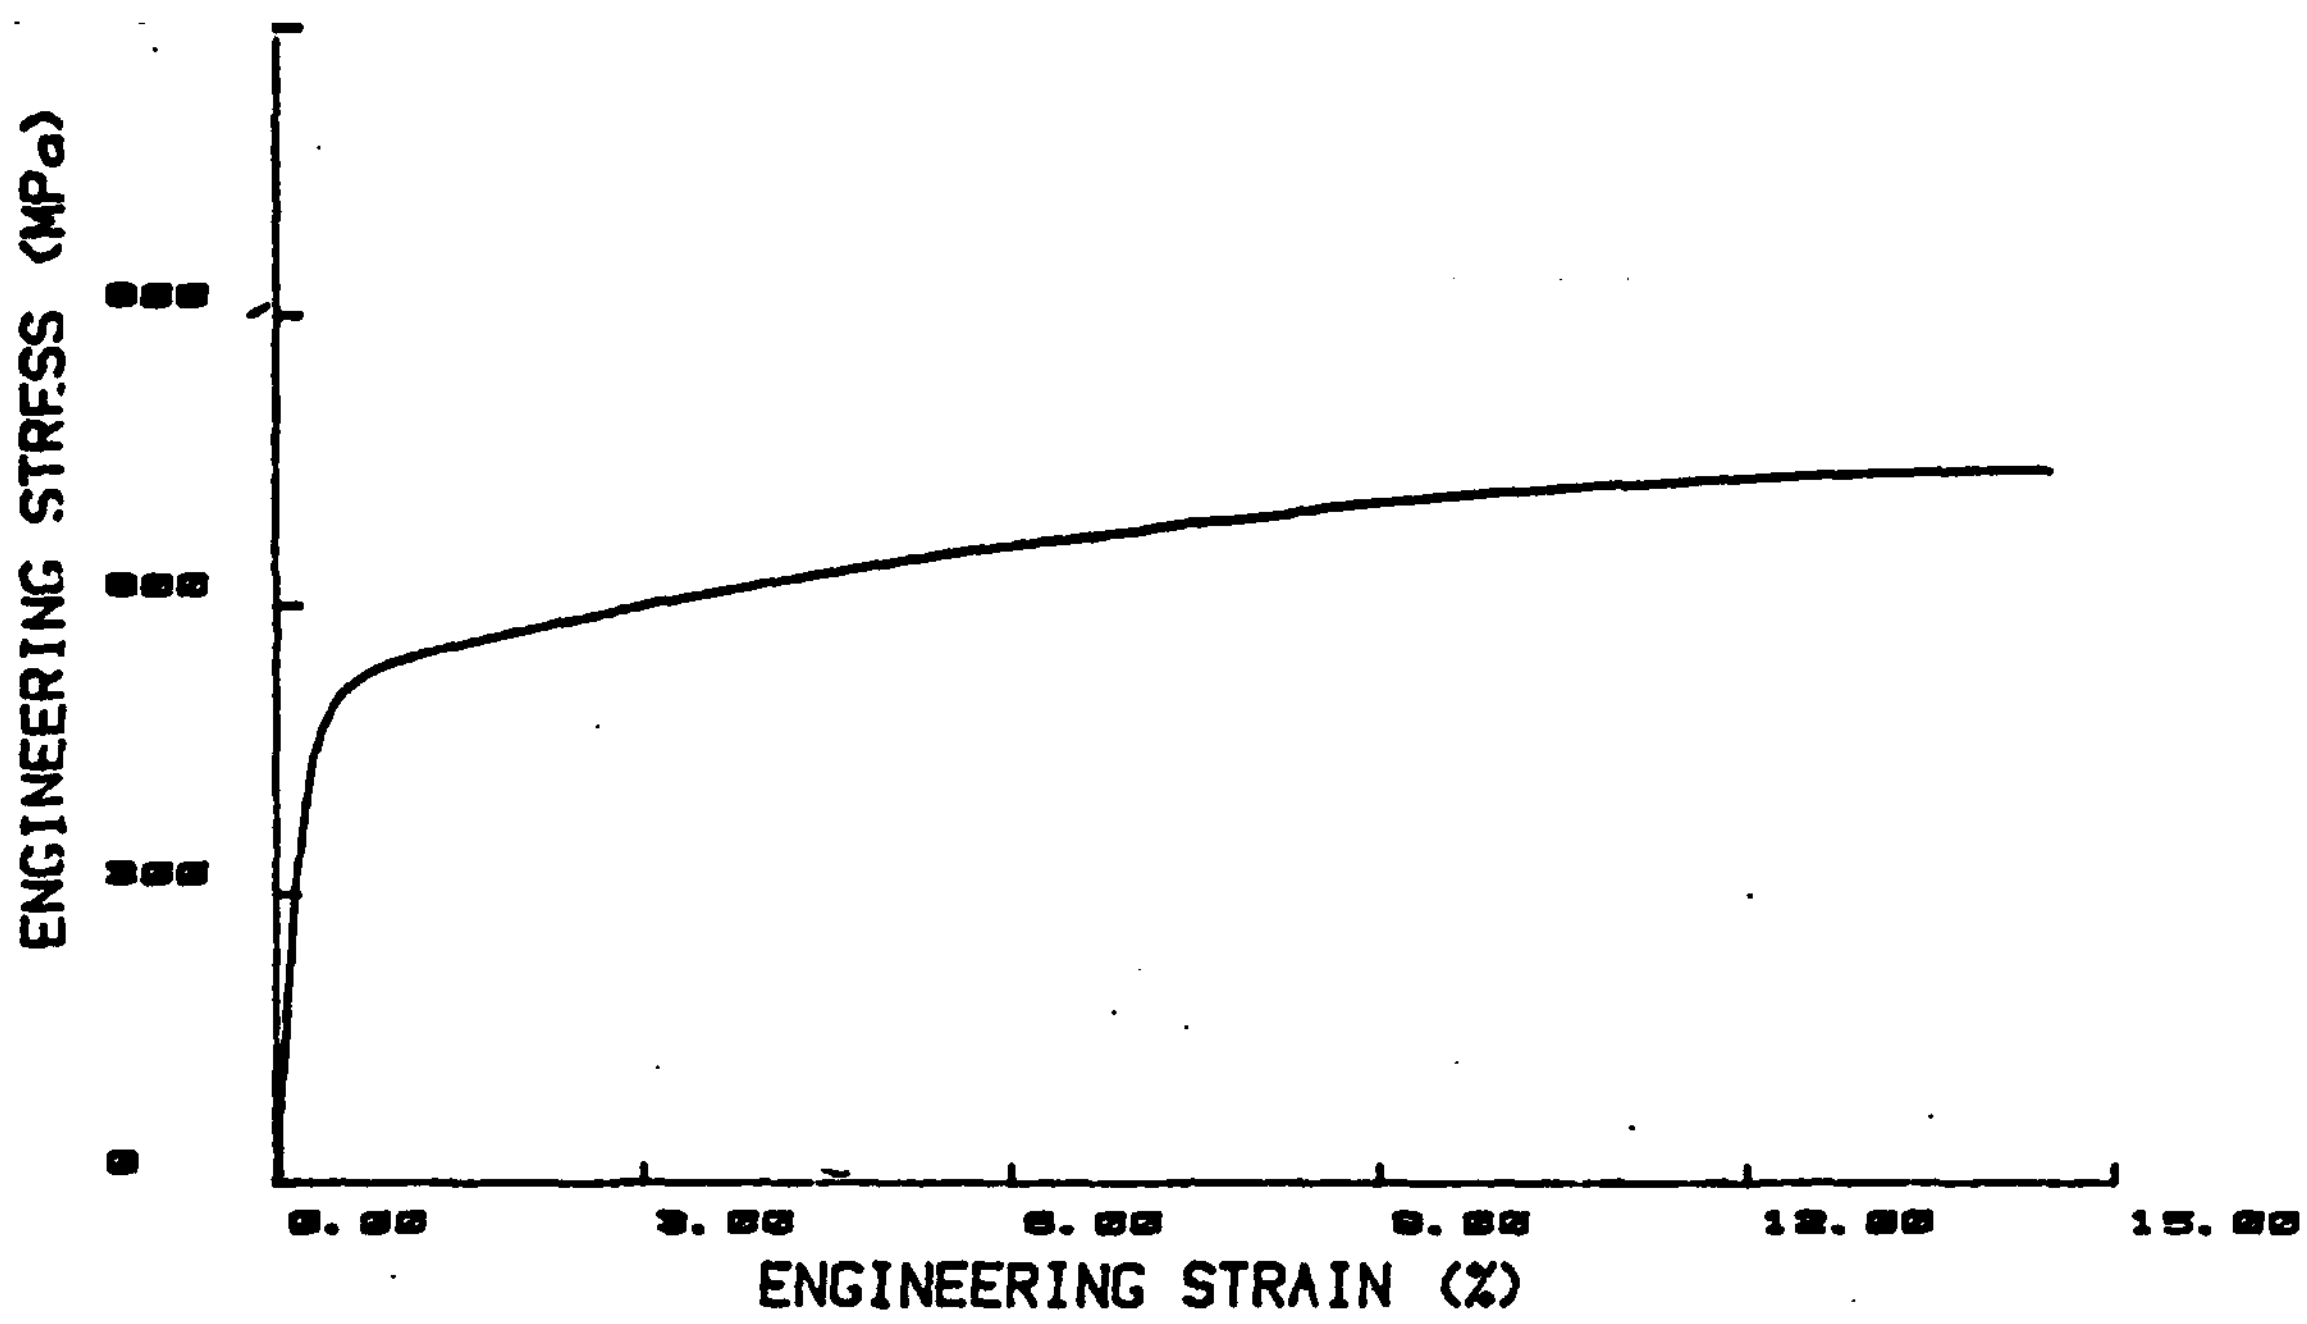

Figure 8. Uniaxial tensile stress-strain curve for an unswaged 75% tungsten alloy, Specimen No. 334.

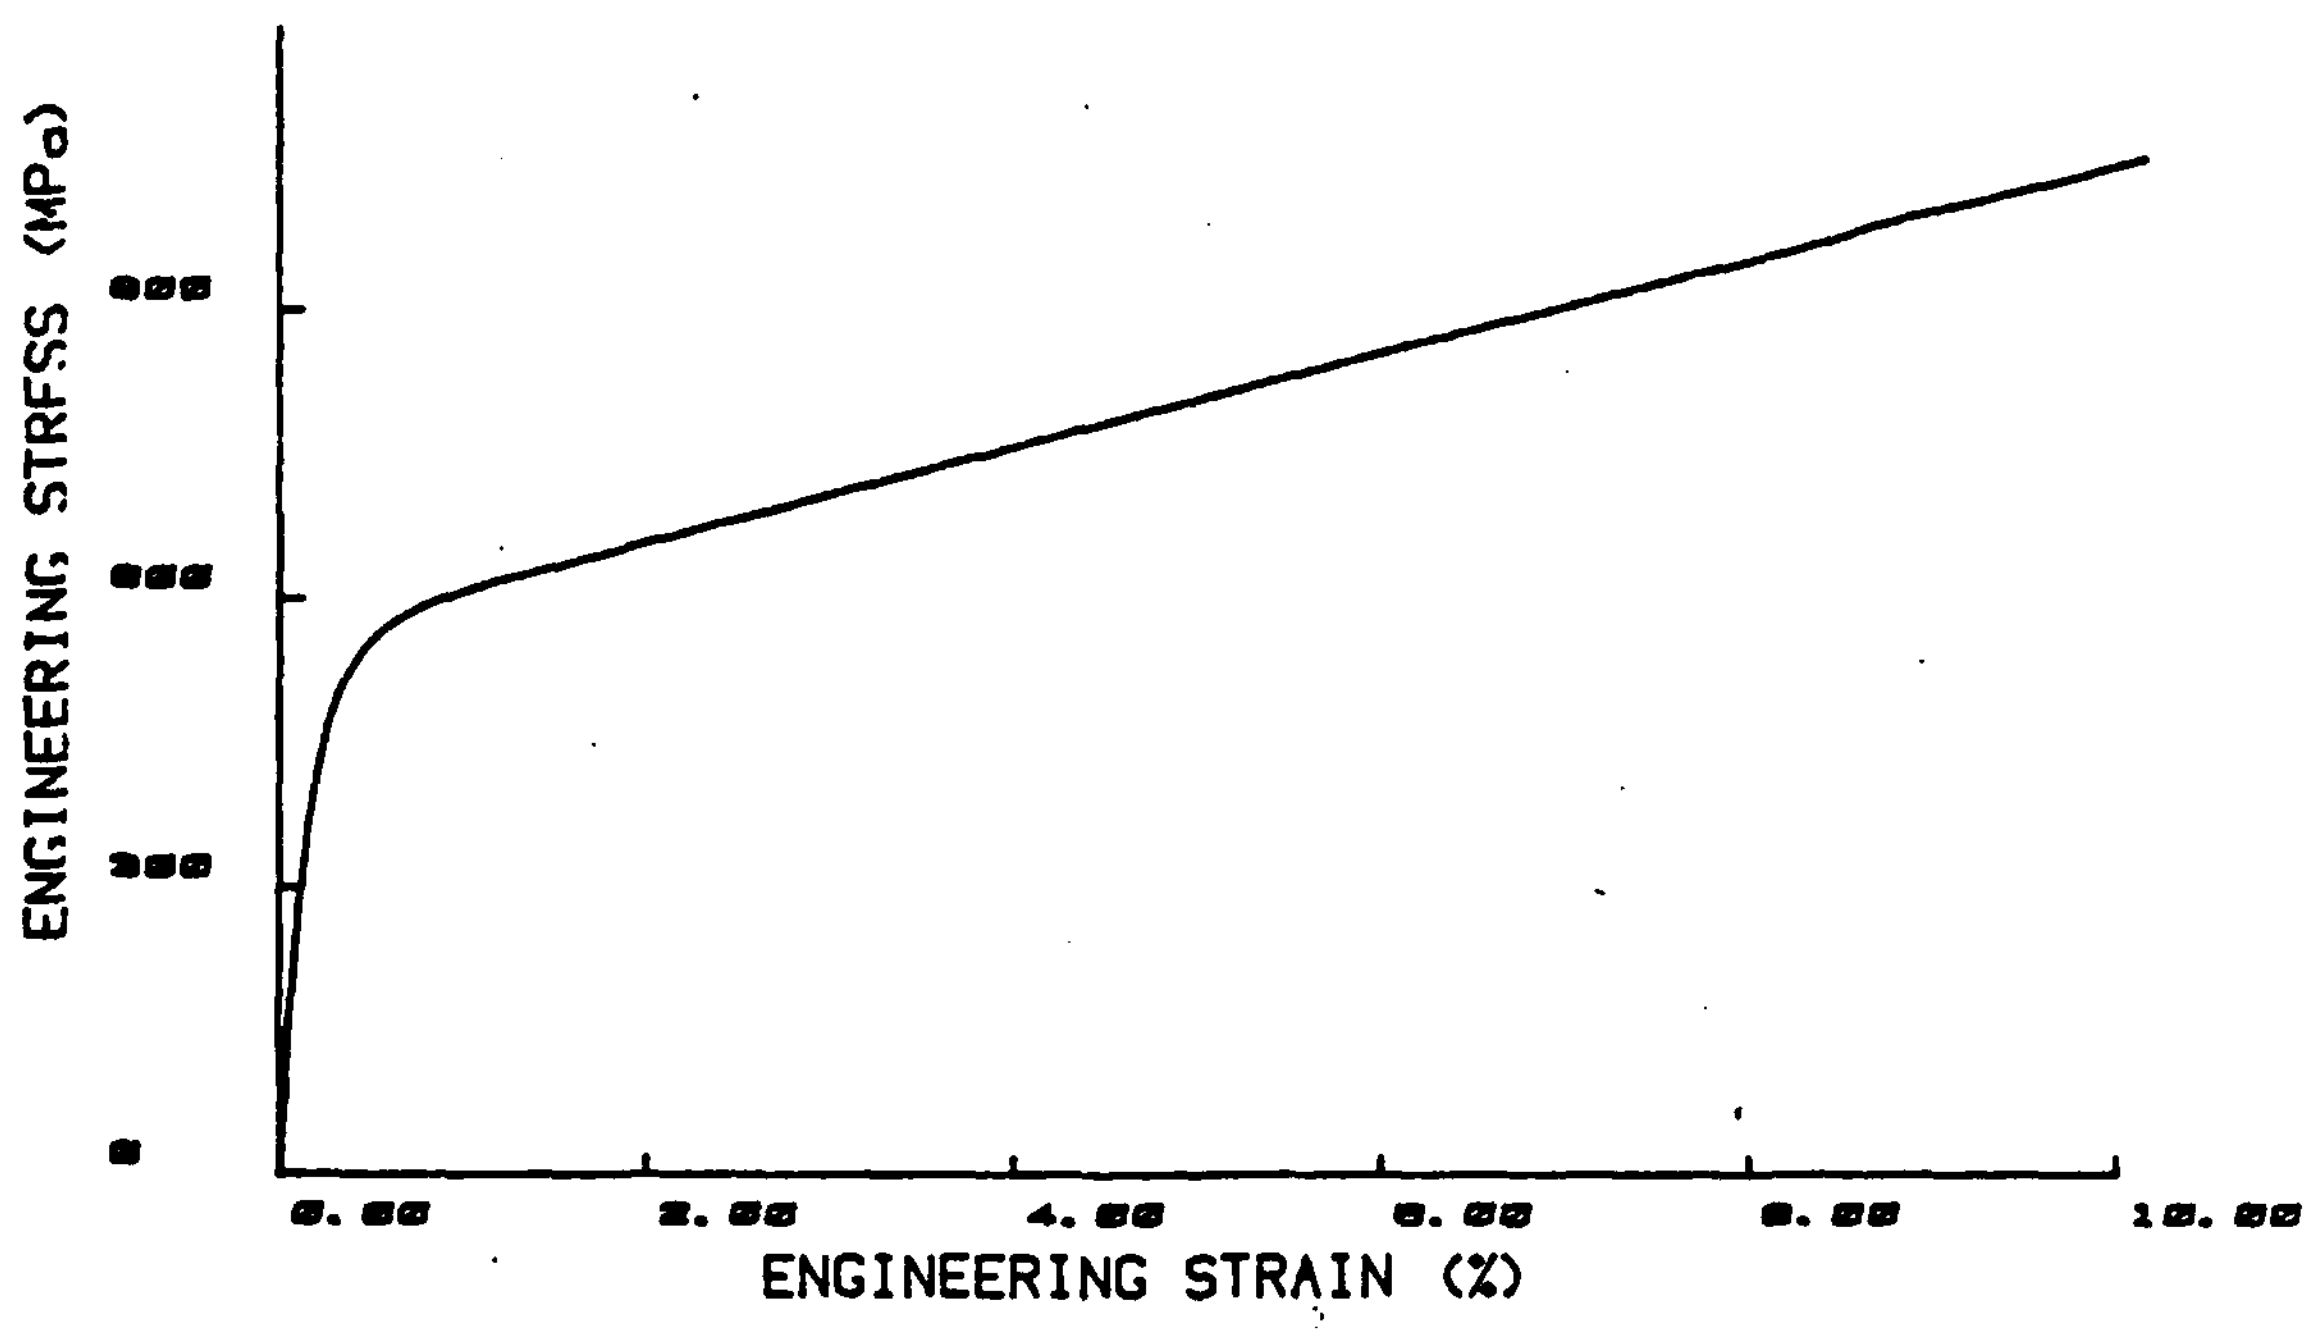

Figure 9. Uniaxial compressive stress-strain curve for an unswaged 75% tungsten alloy, Specimen No. 337.

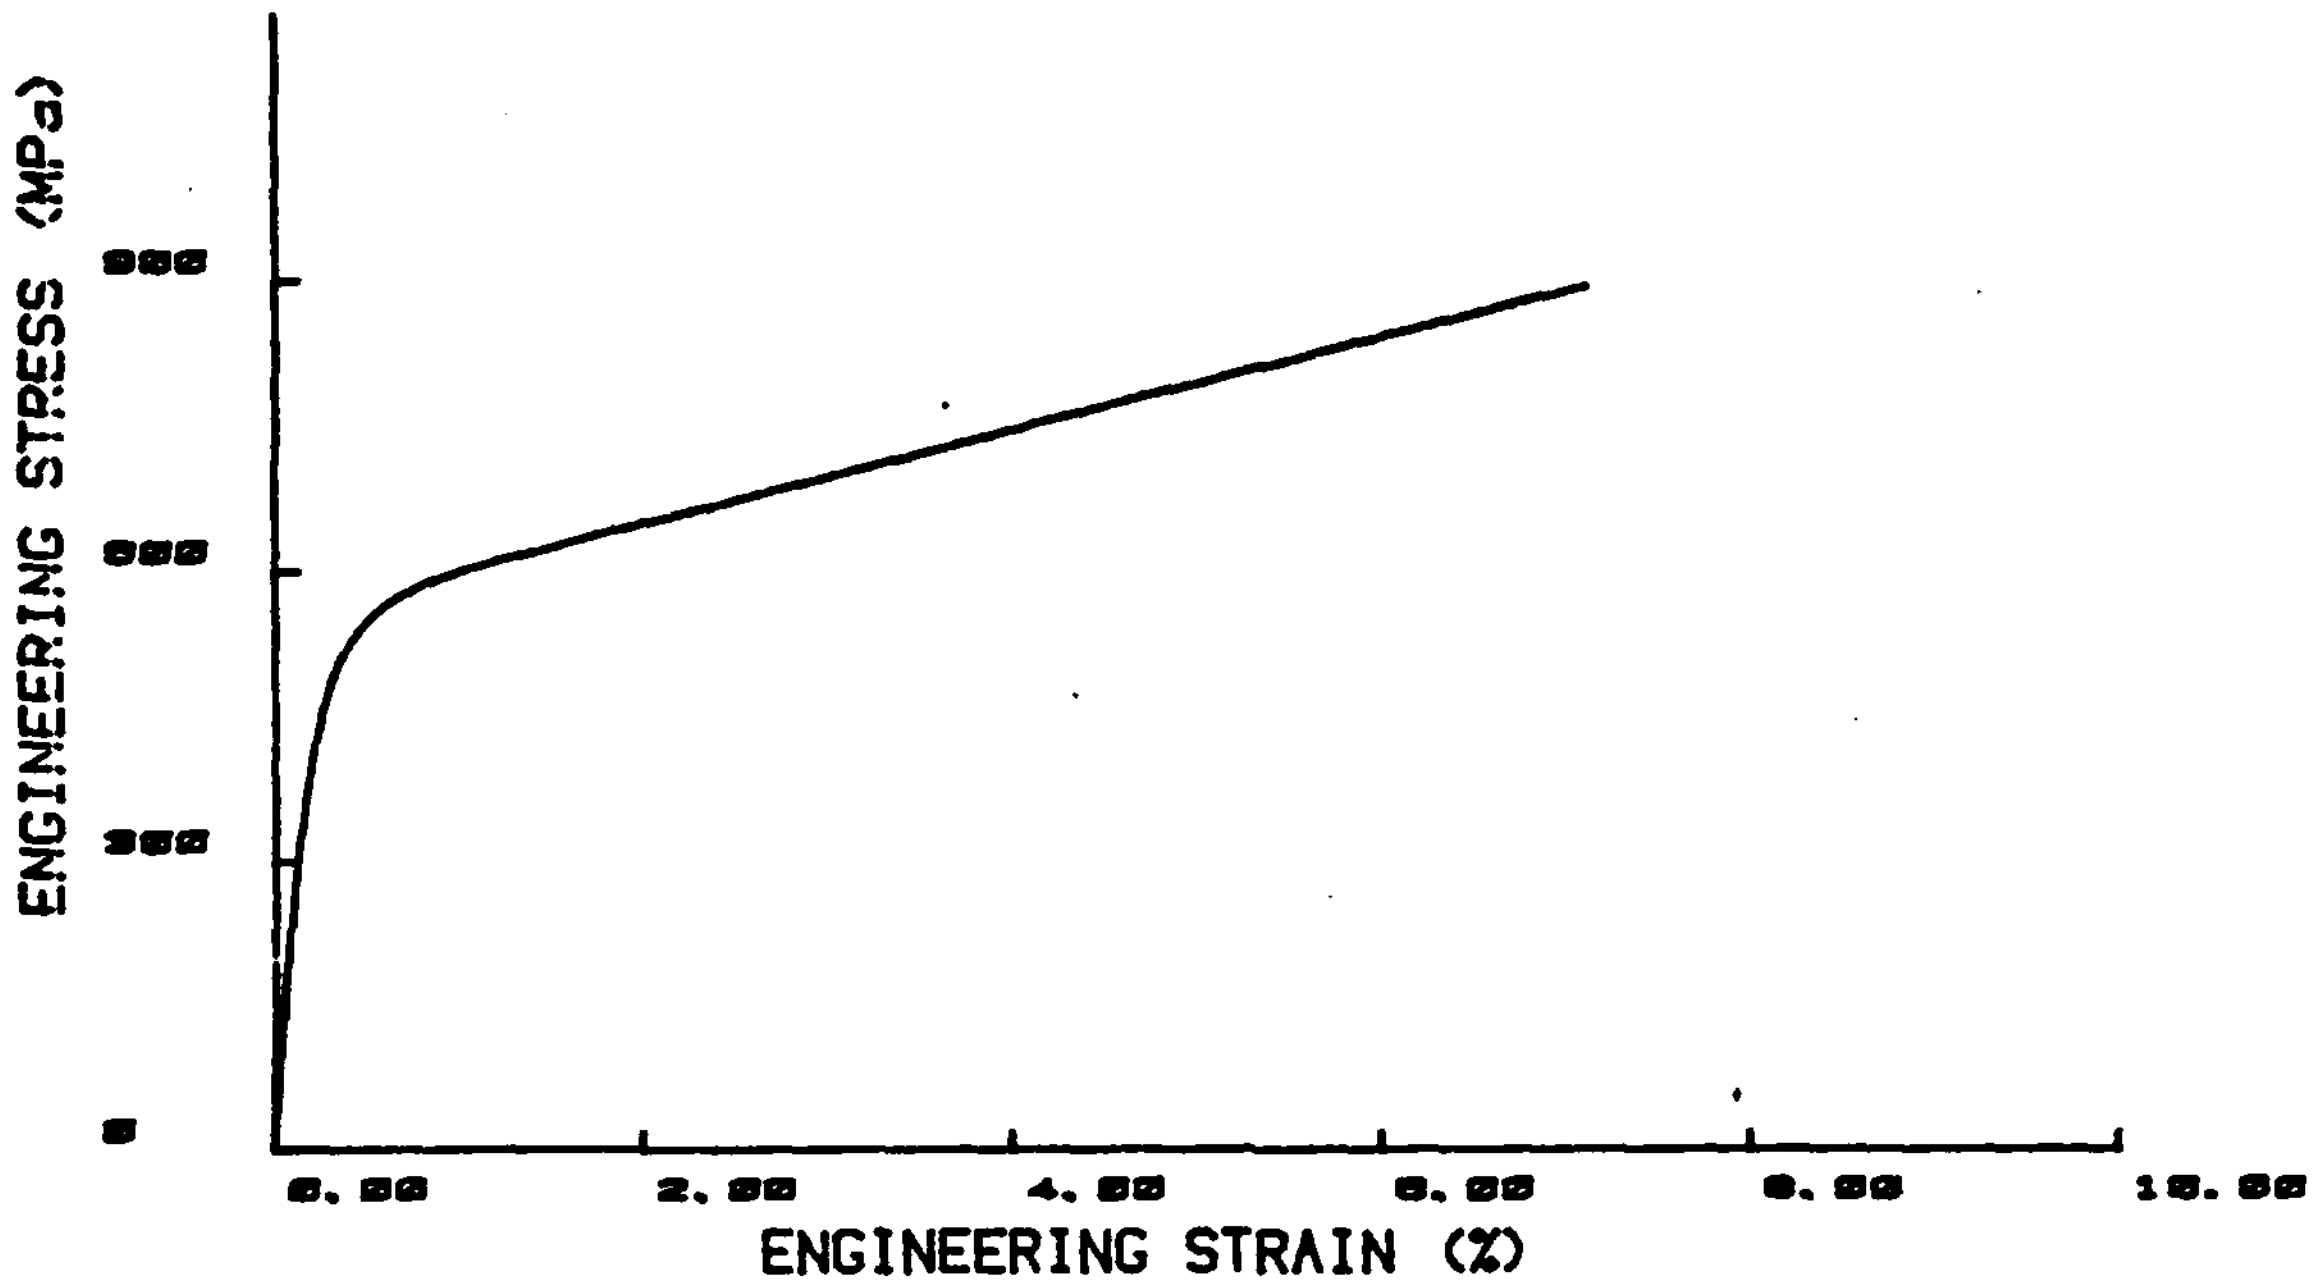

Figure 10. Uniaxial compressive stress-strain curve for an unswaged 75% tungsten alloy, Specimen No. 340.

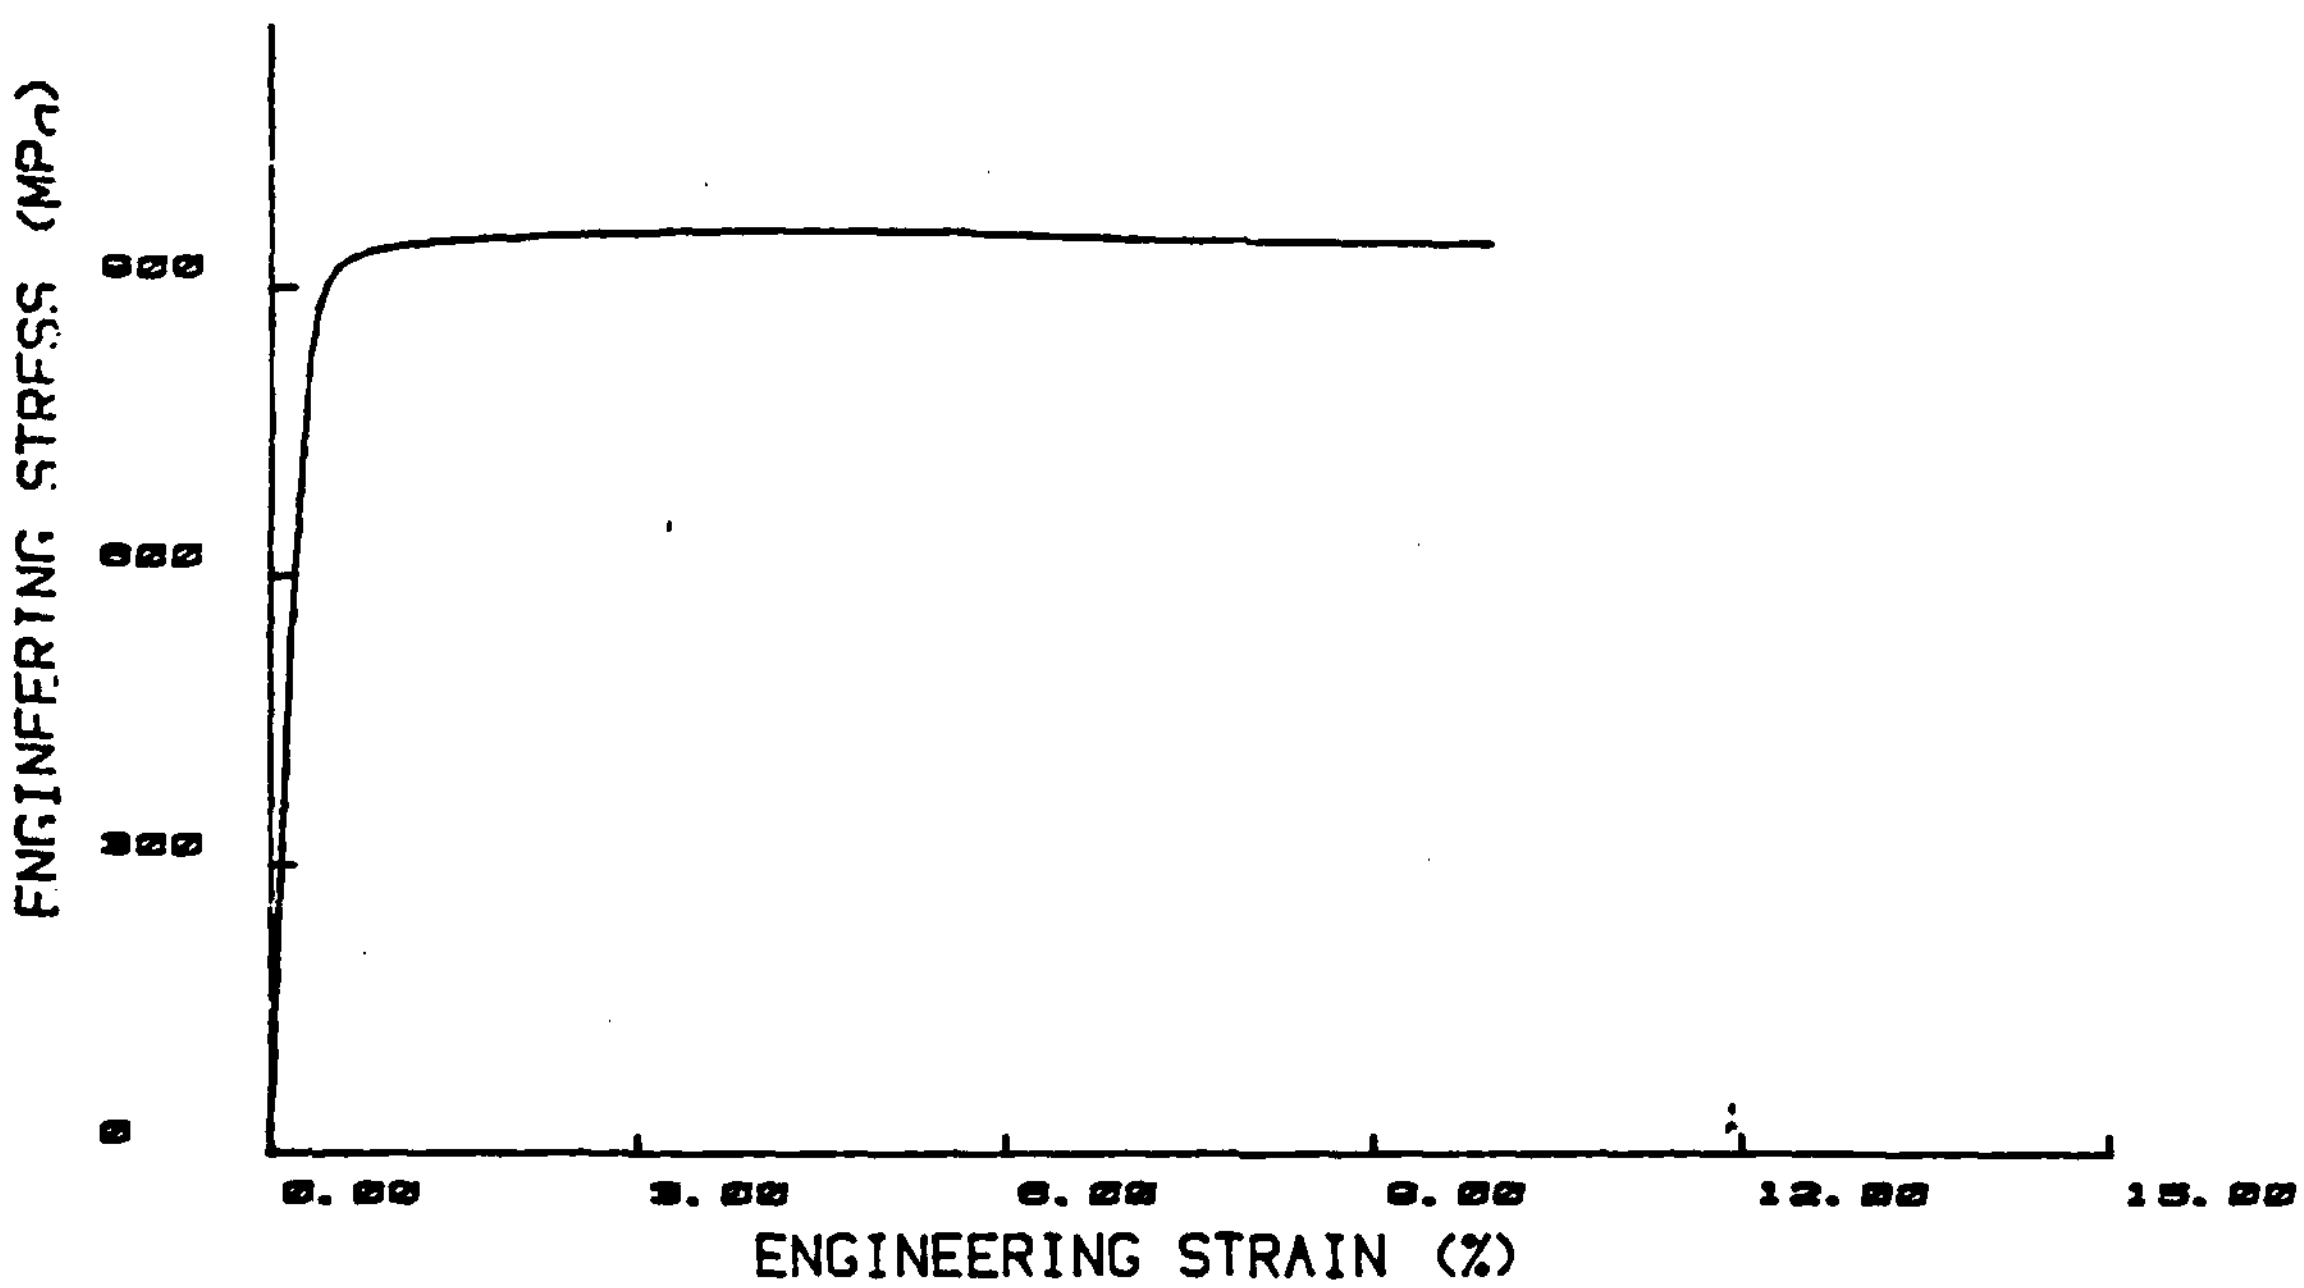

Figure 11. Uniaxial tensile stress-strain curve for a 75% tungsten alloy swaged 14%, Specimen No. 357.

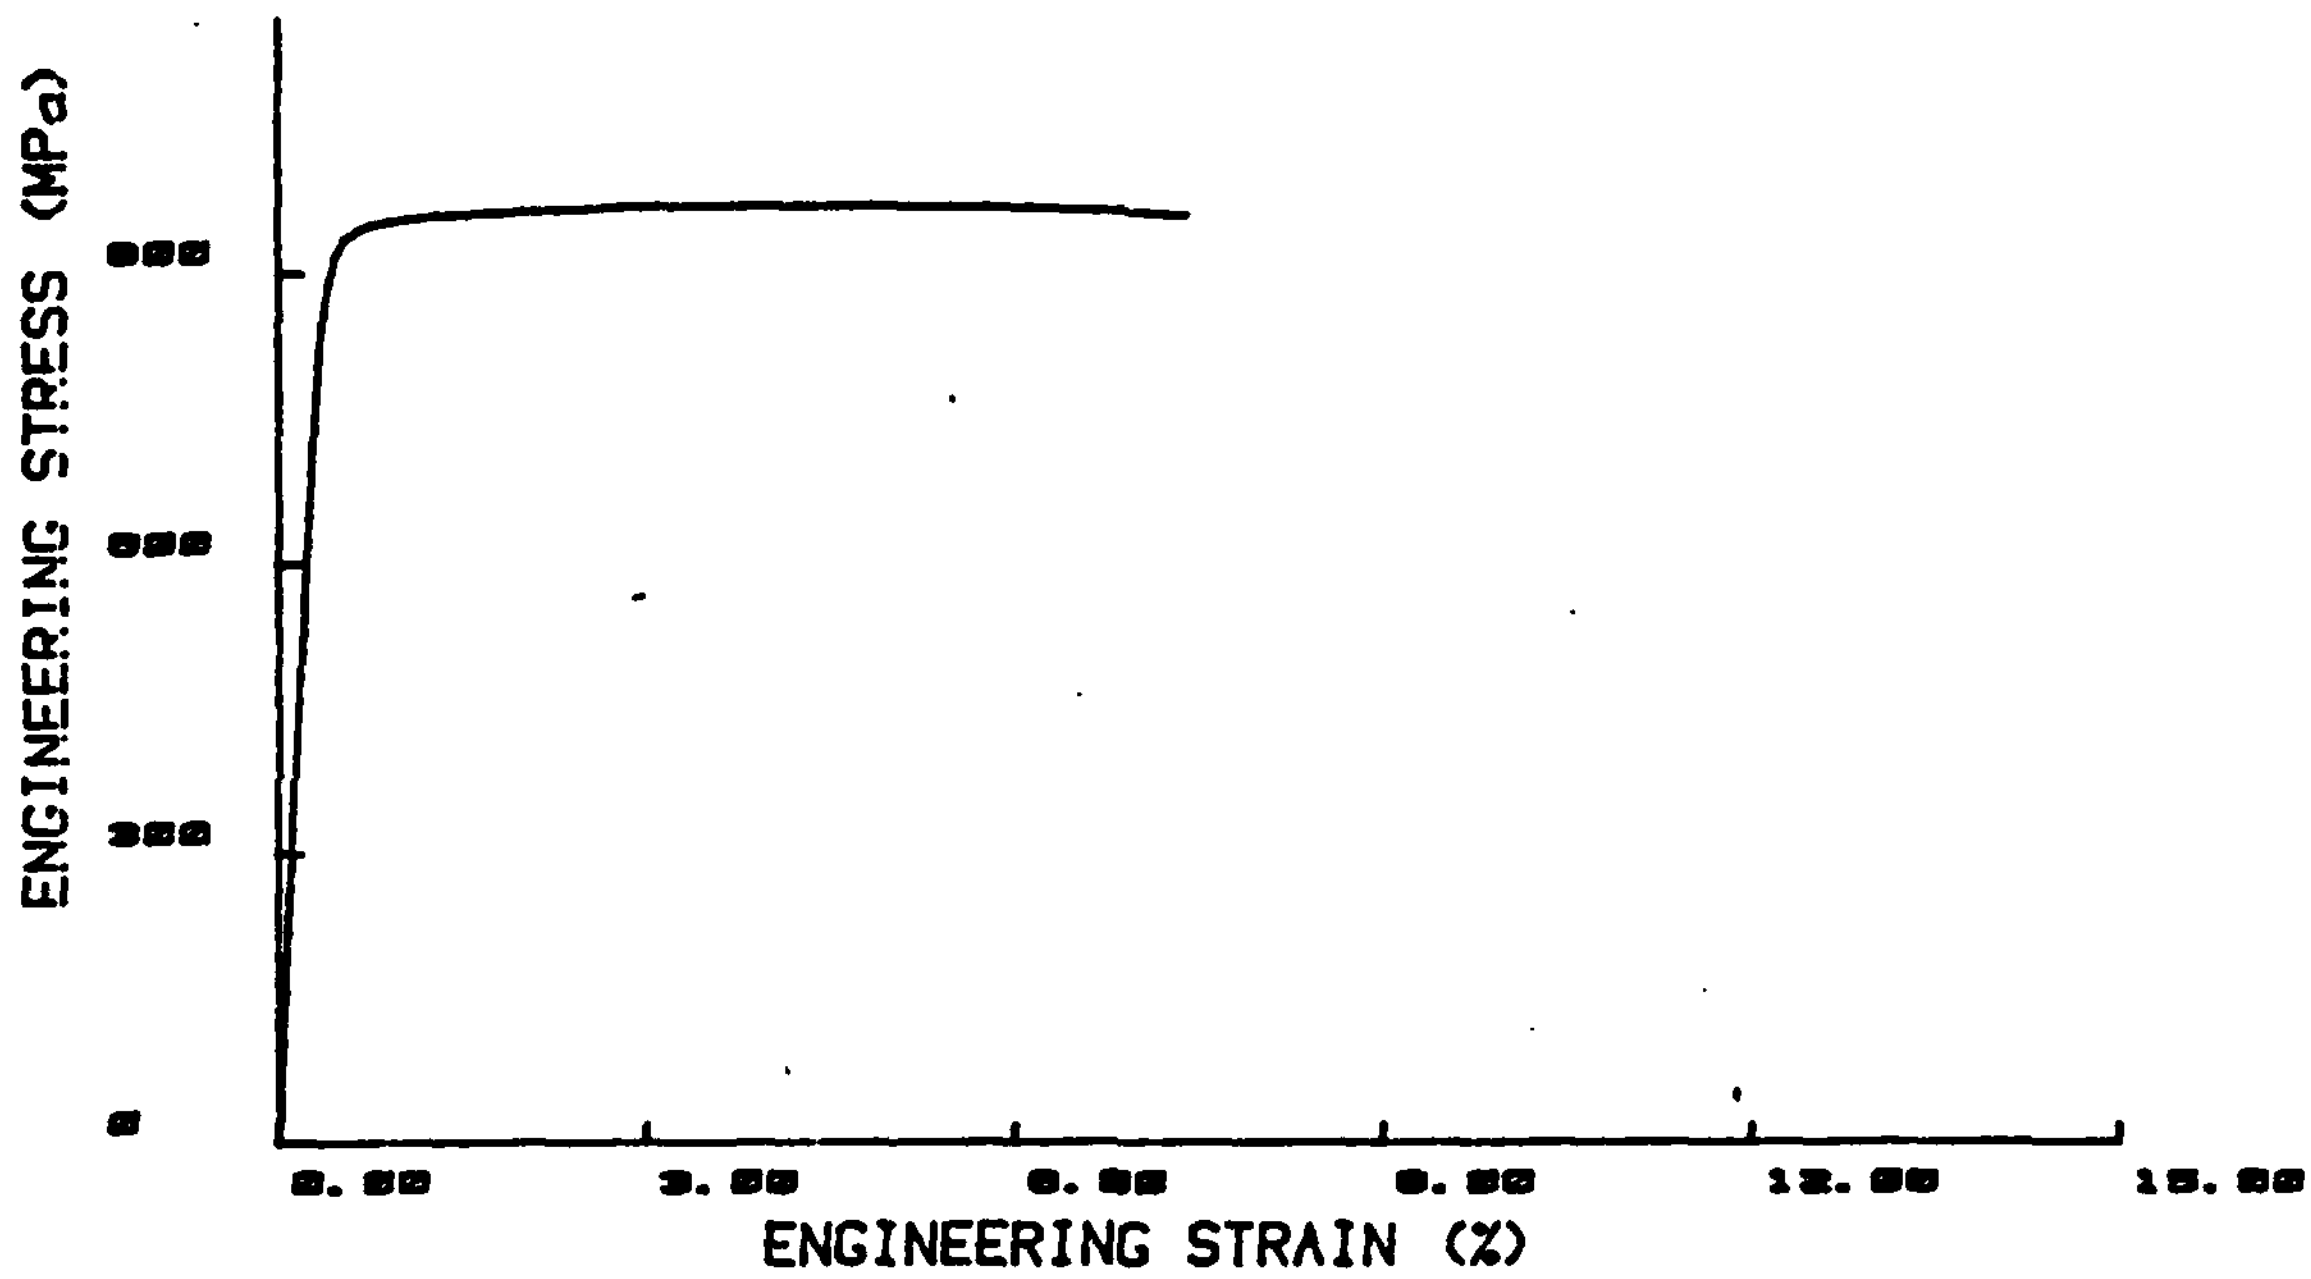

Figure 12. Uniaxial tensile stress-strain curve for a 75% tungsten alloy swaged 14%, Specimen No. 358.

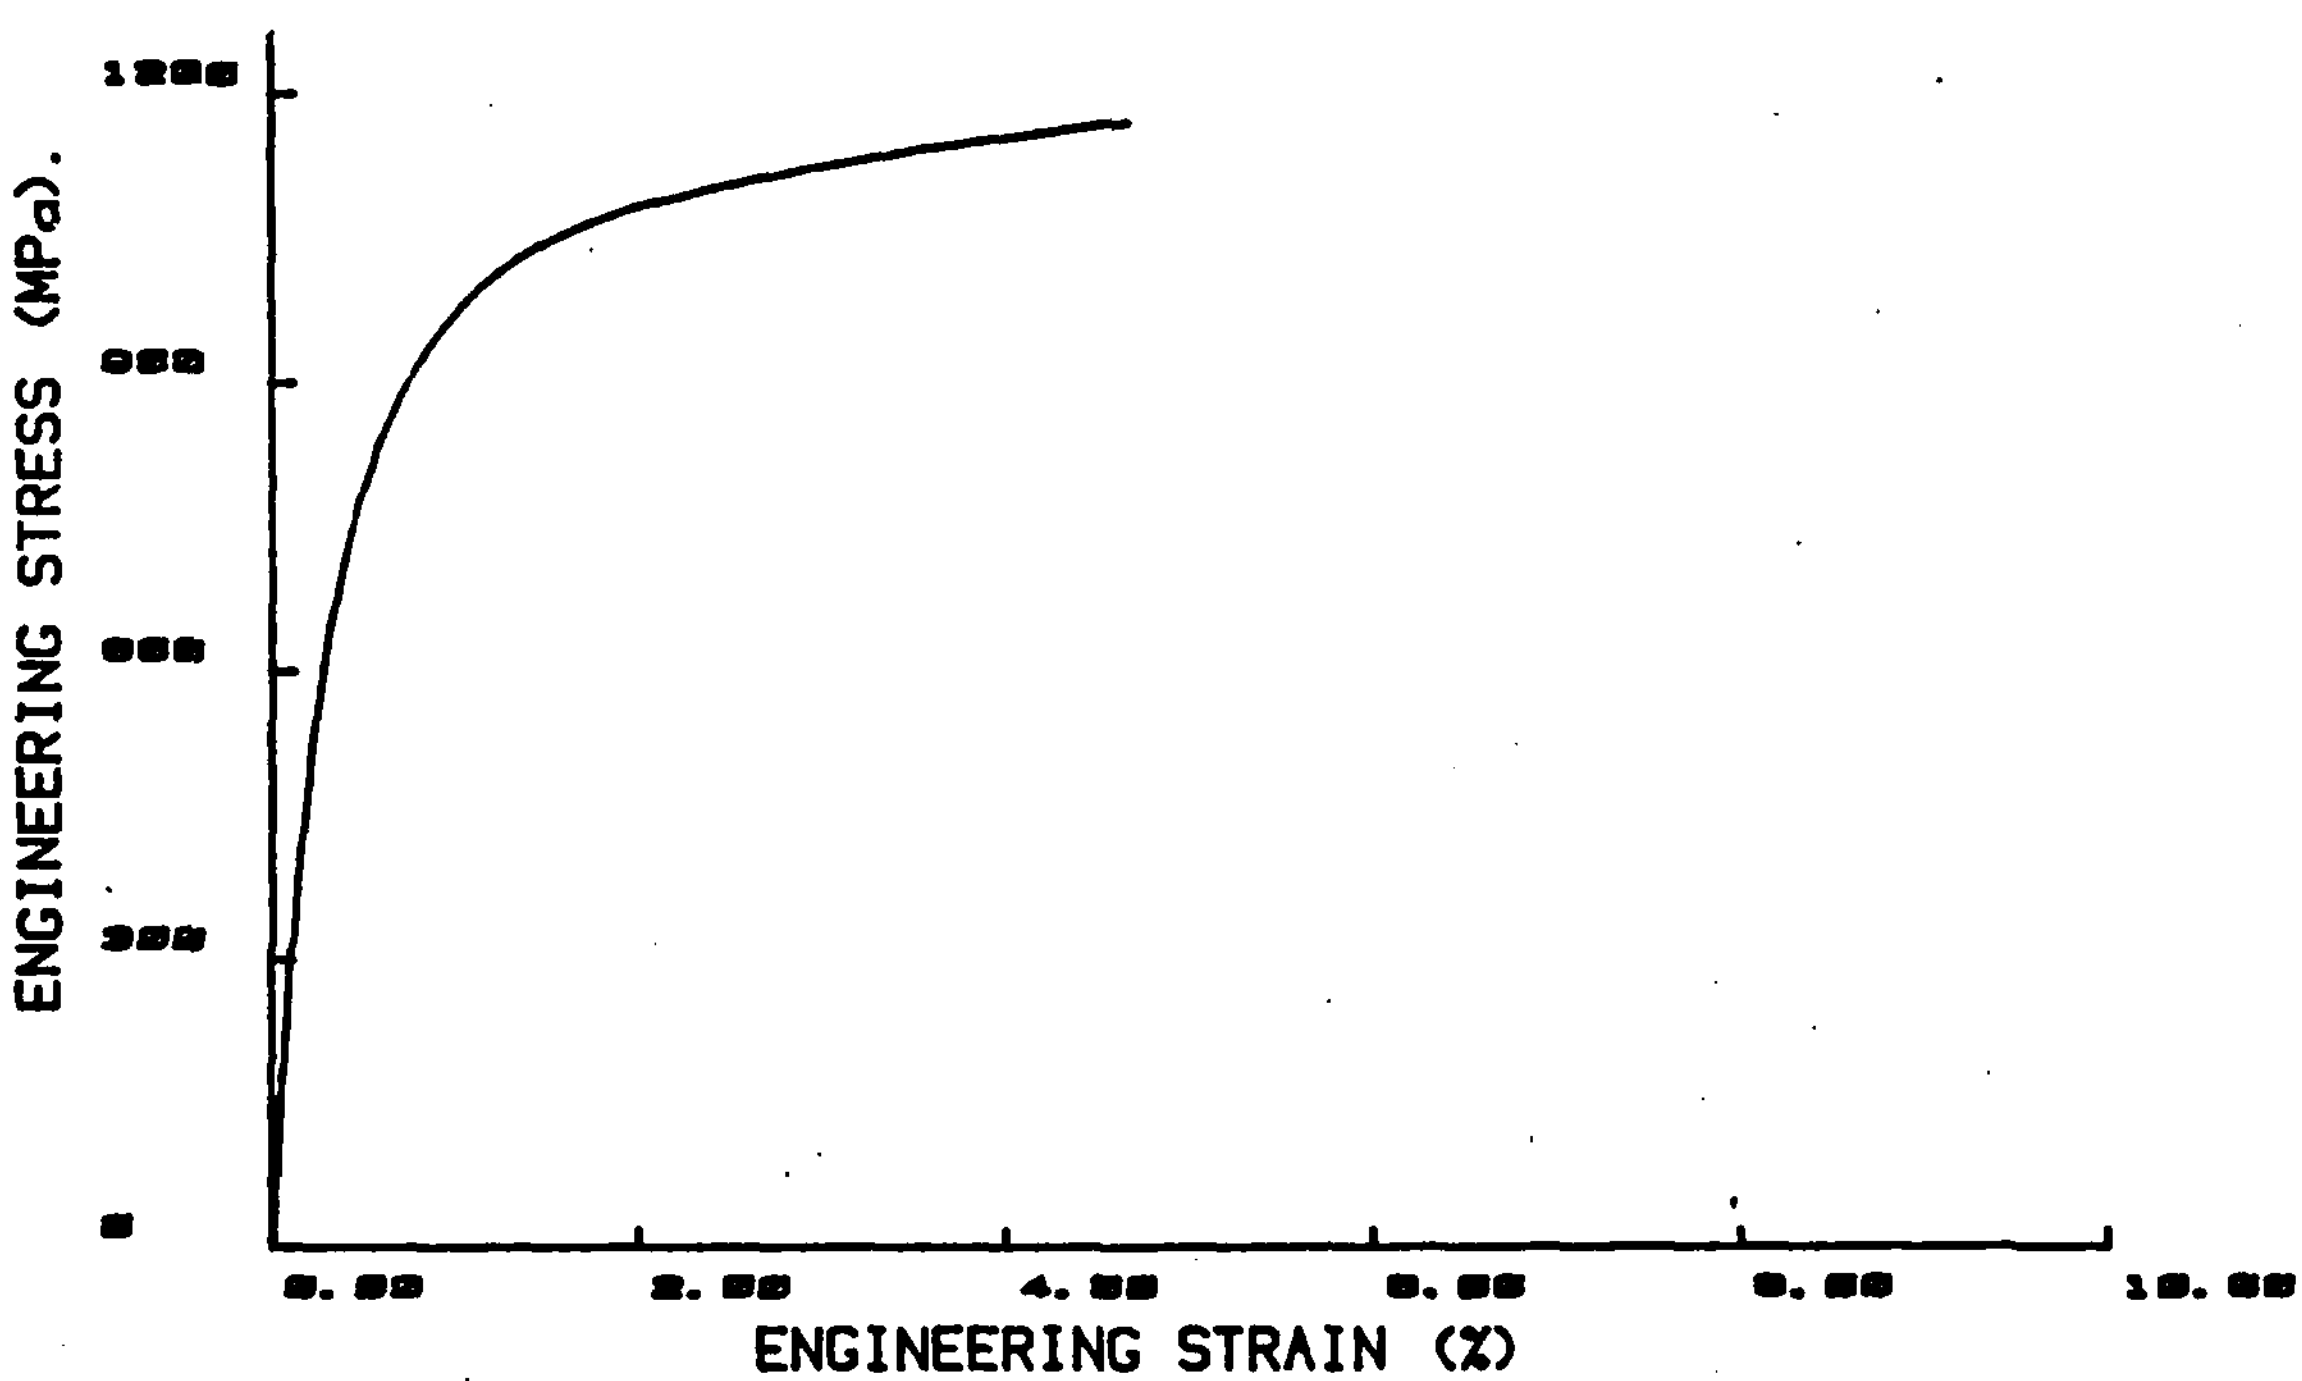

Figure 13. Uniaxial compressive stress-strain curve for a 75% tungsten alloy swaged 14%, Specimen No. 361.

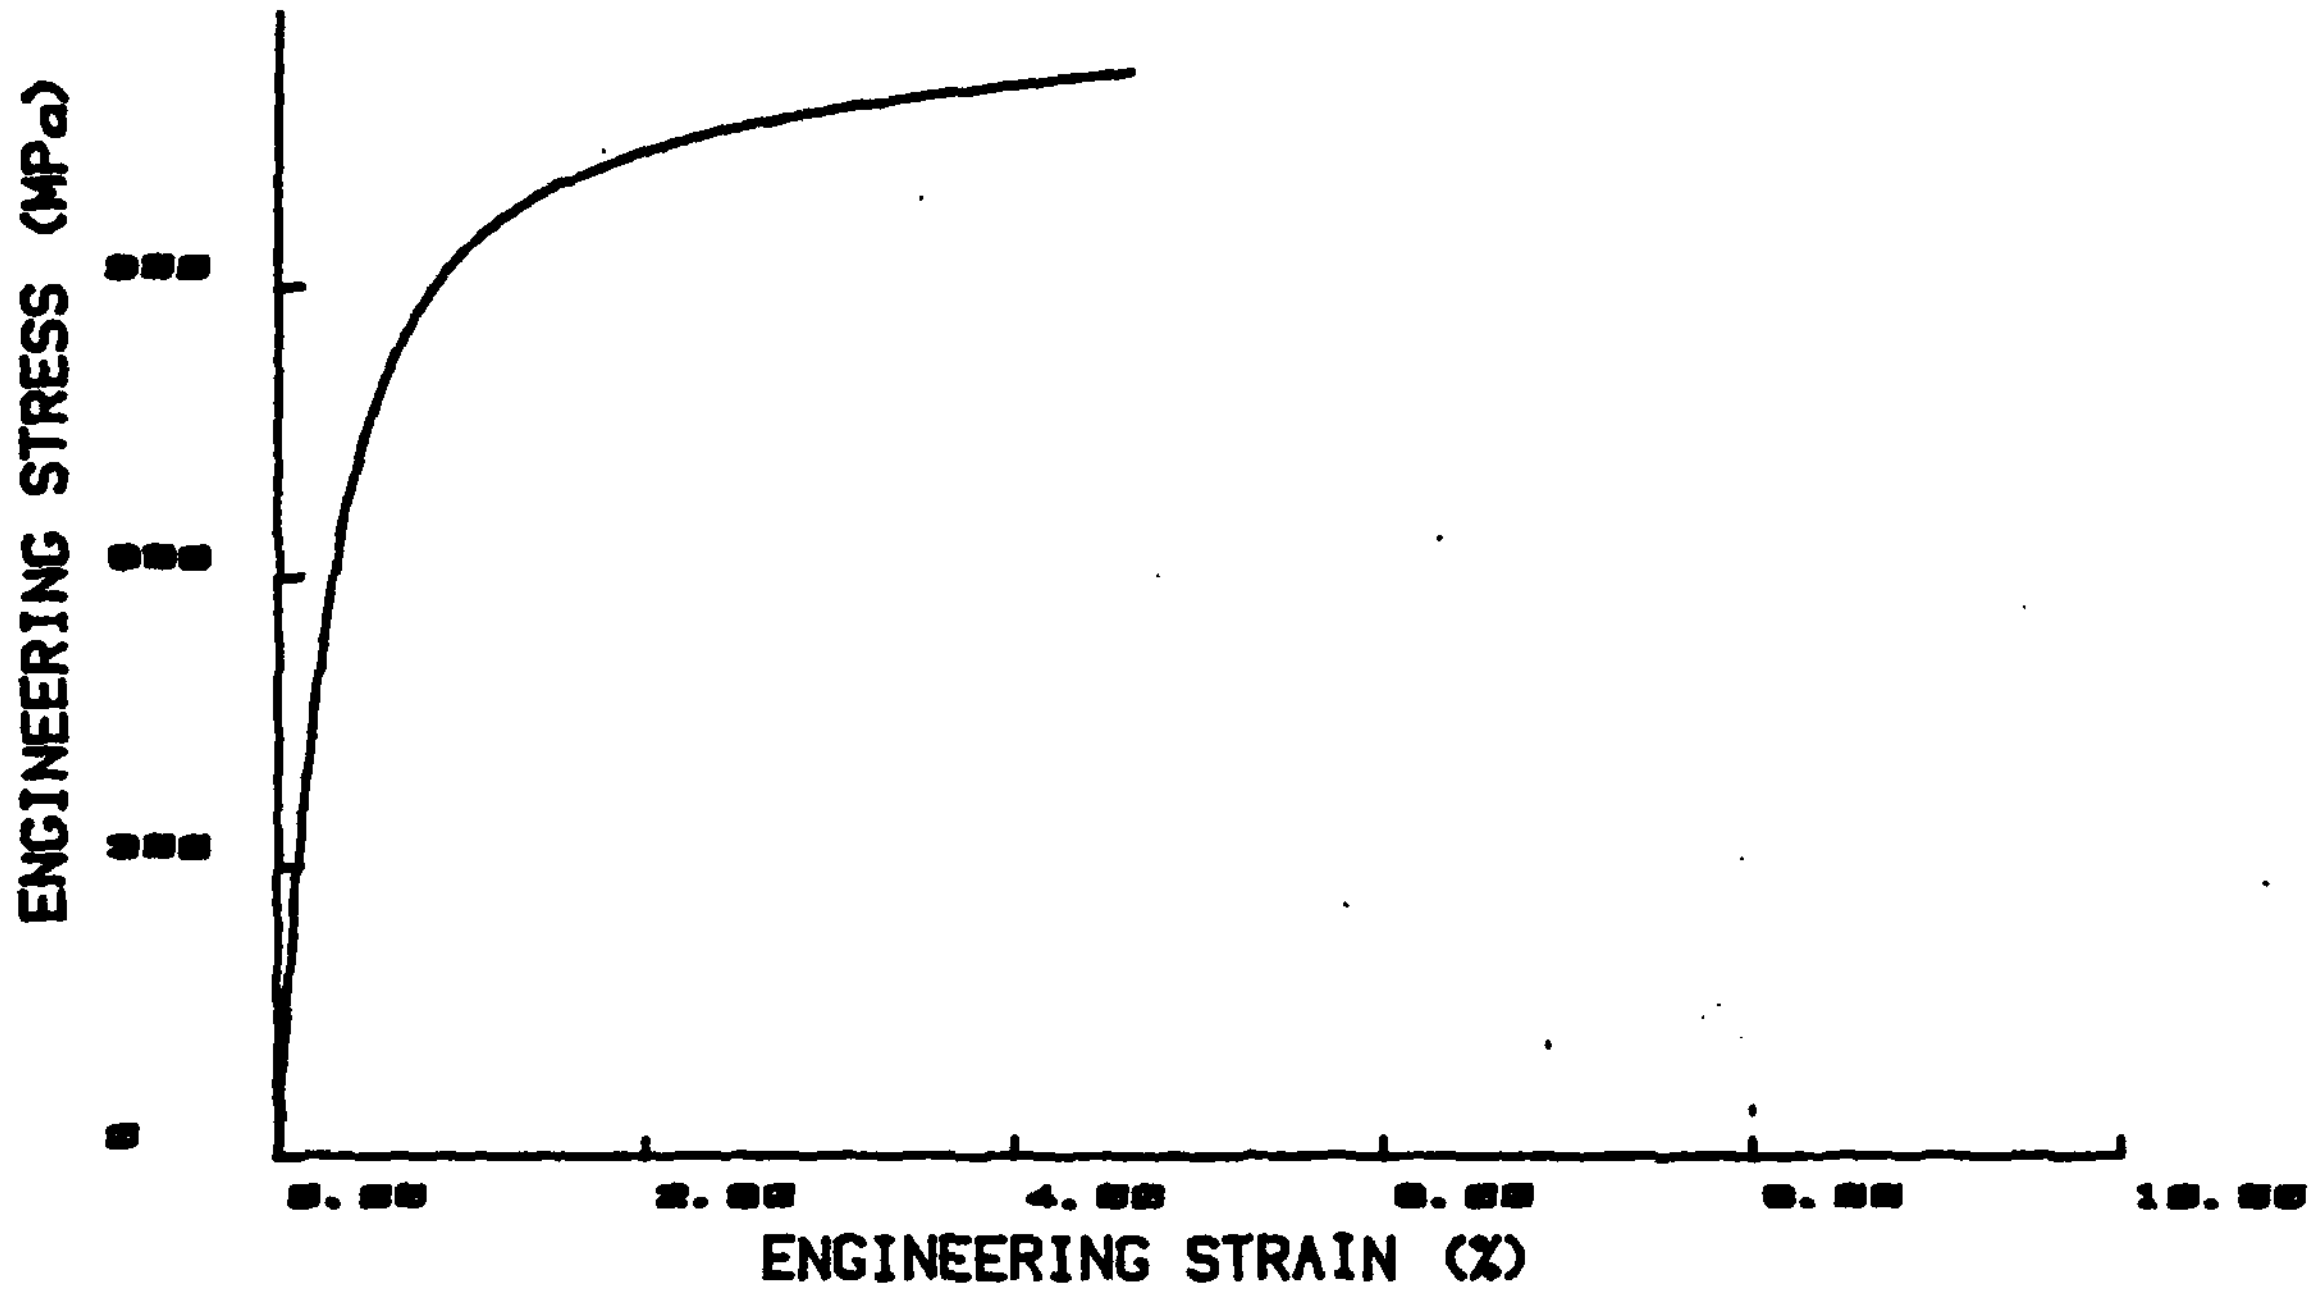

Figure 14. Uniaxial compressive stress-strain curve for a 75% tungsten alloy swaged 14%, Specimen No. 362.

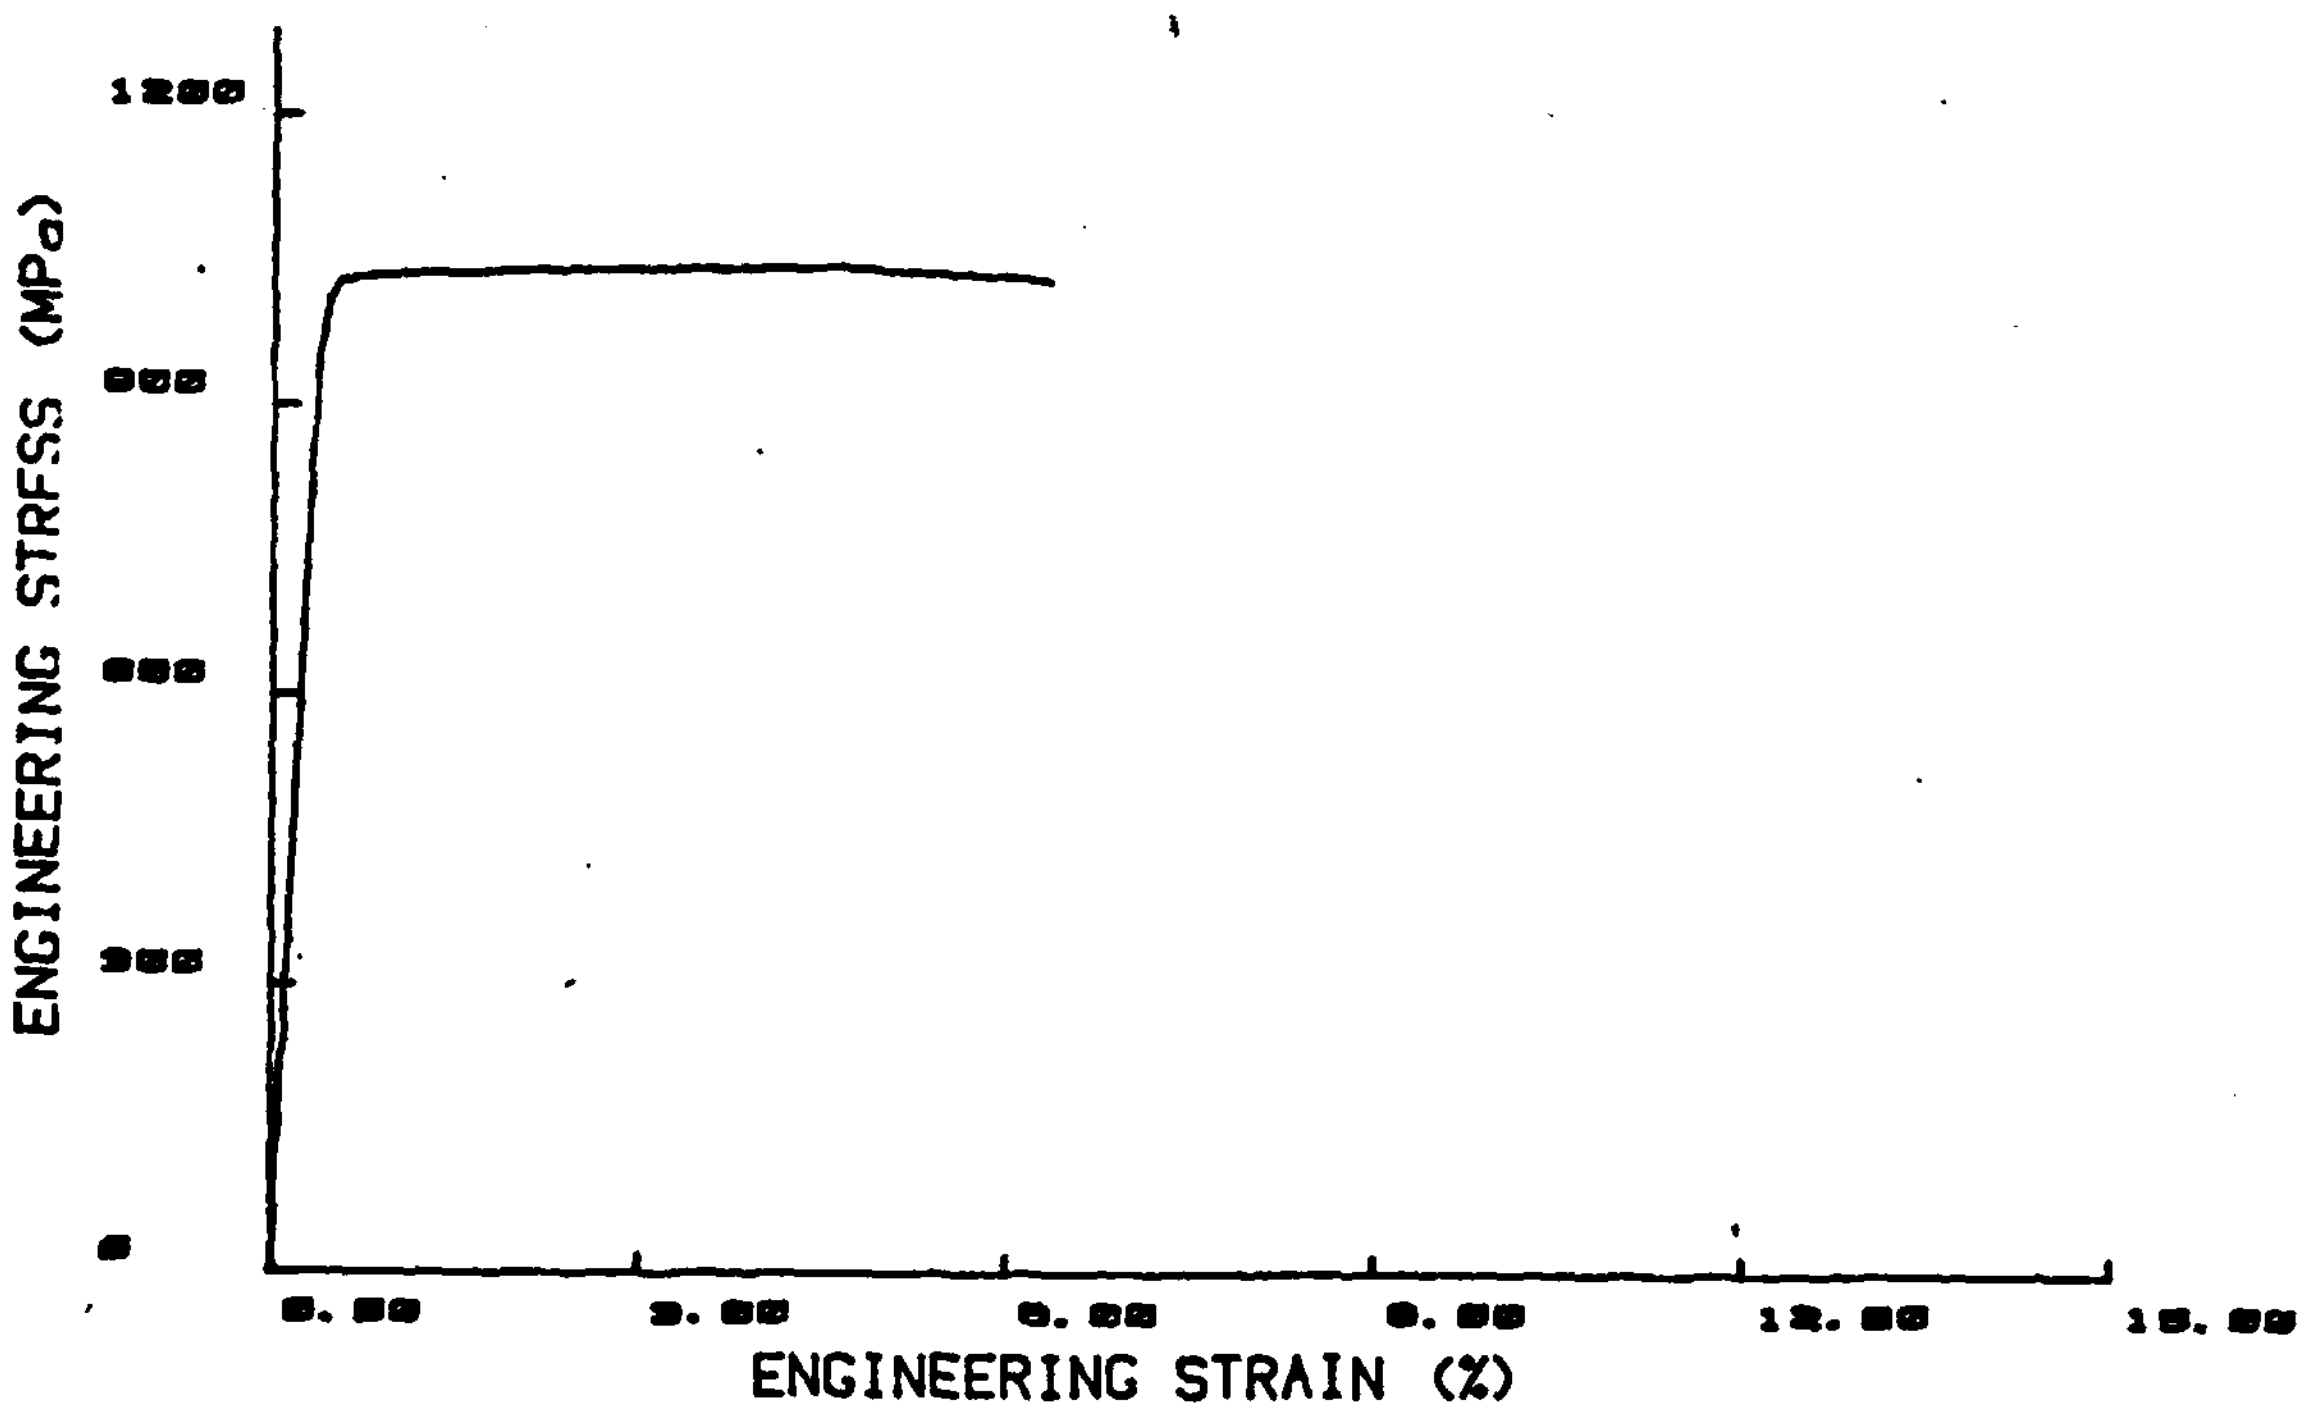

Figure 15. Uniaxial tensile stress-strain curve for a 75% tungsten alloy swaged 21%, Specimen No. 359.

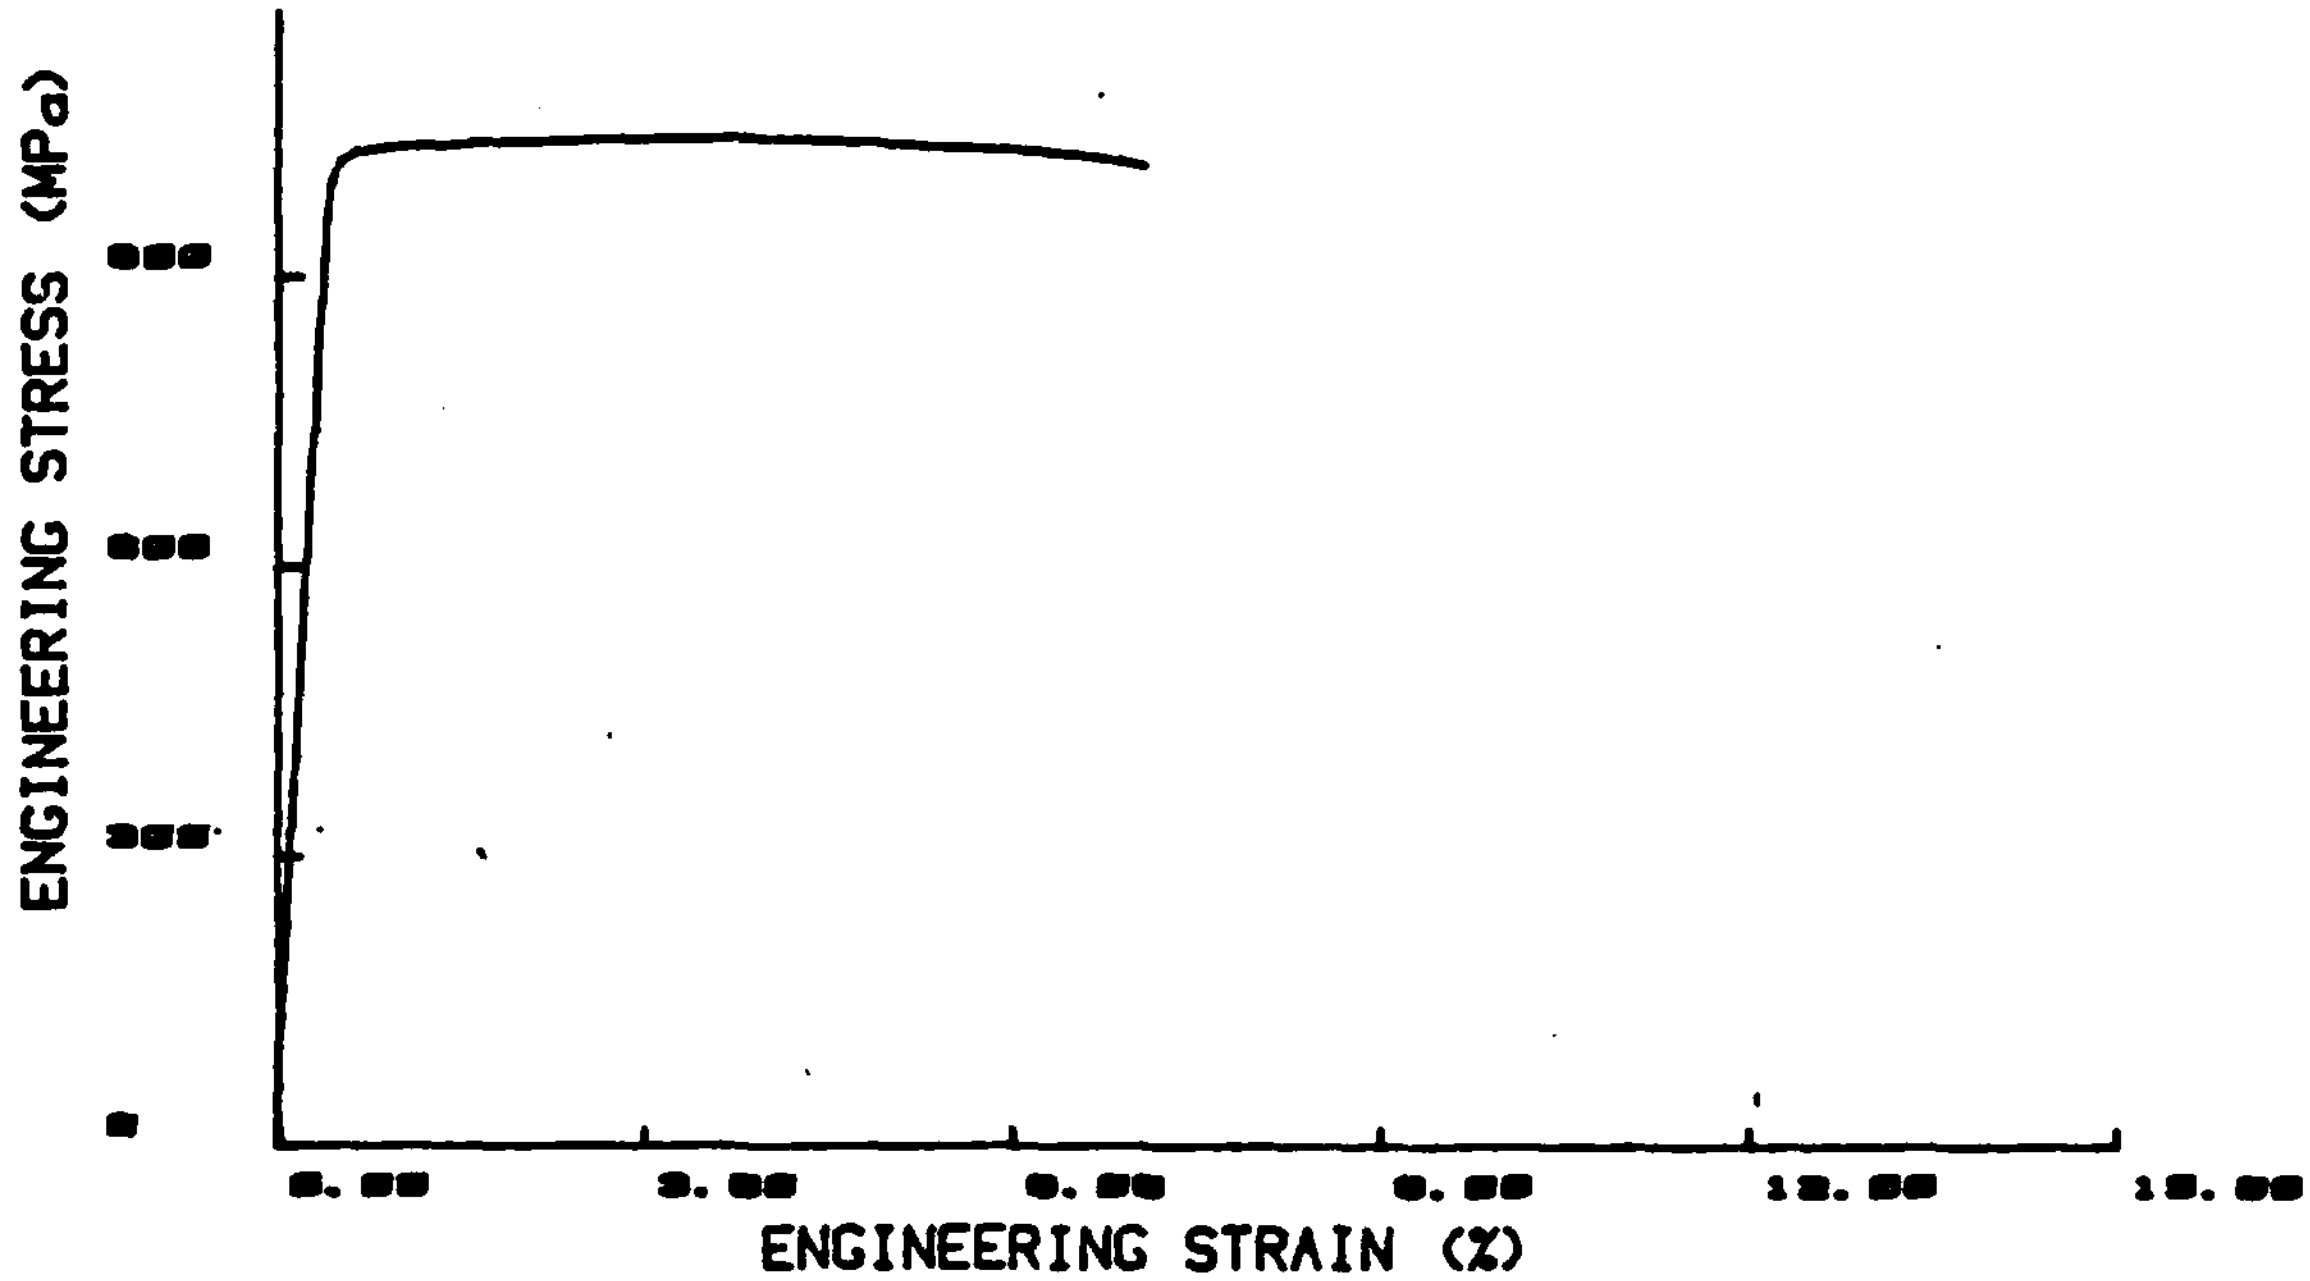

Figure 16. Uniaxial tensile stress-strain curve for a 75% tungsten alloy swaged 21%, Specimen No. 360.

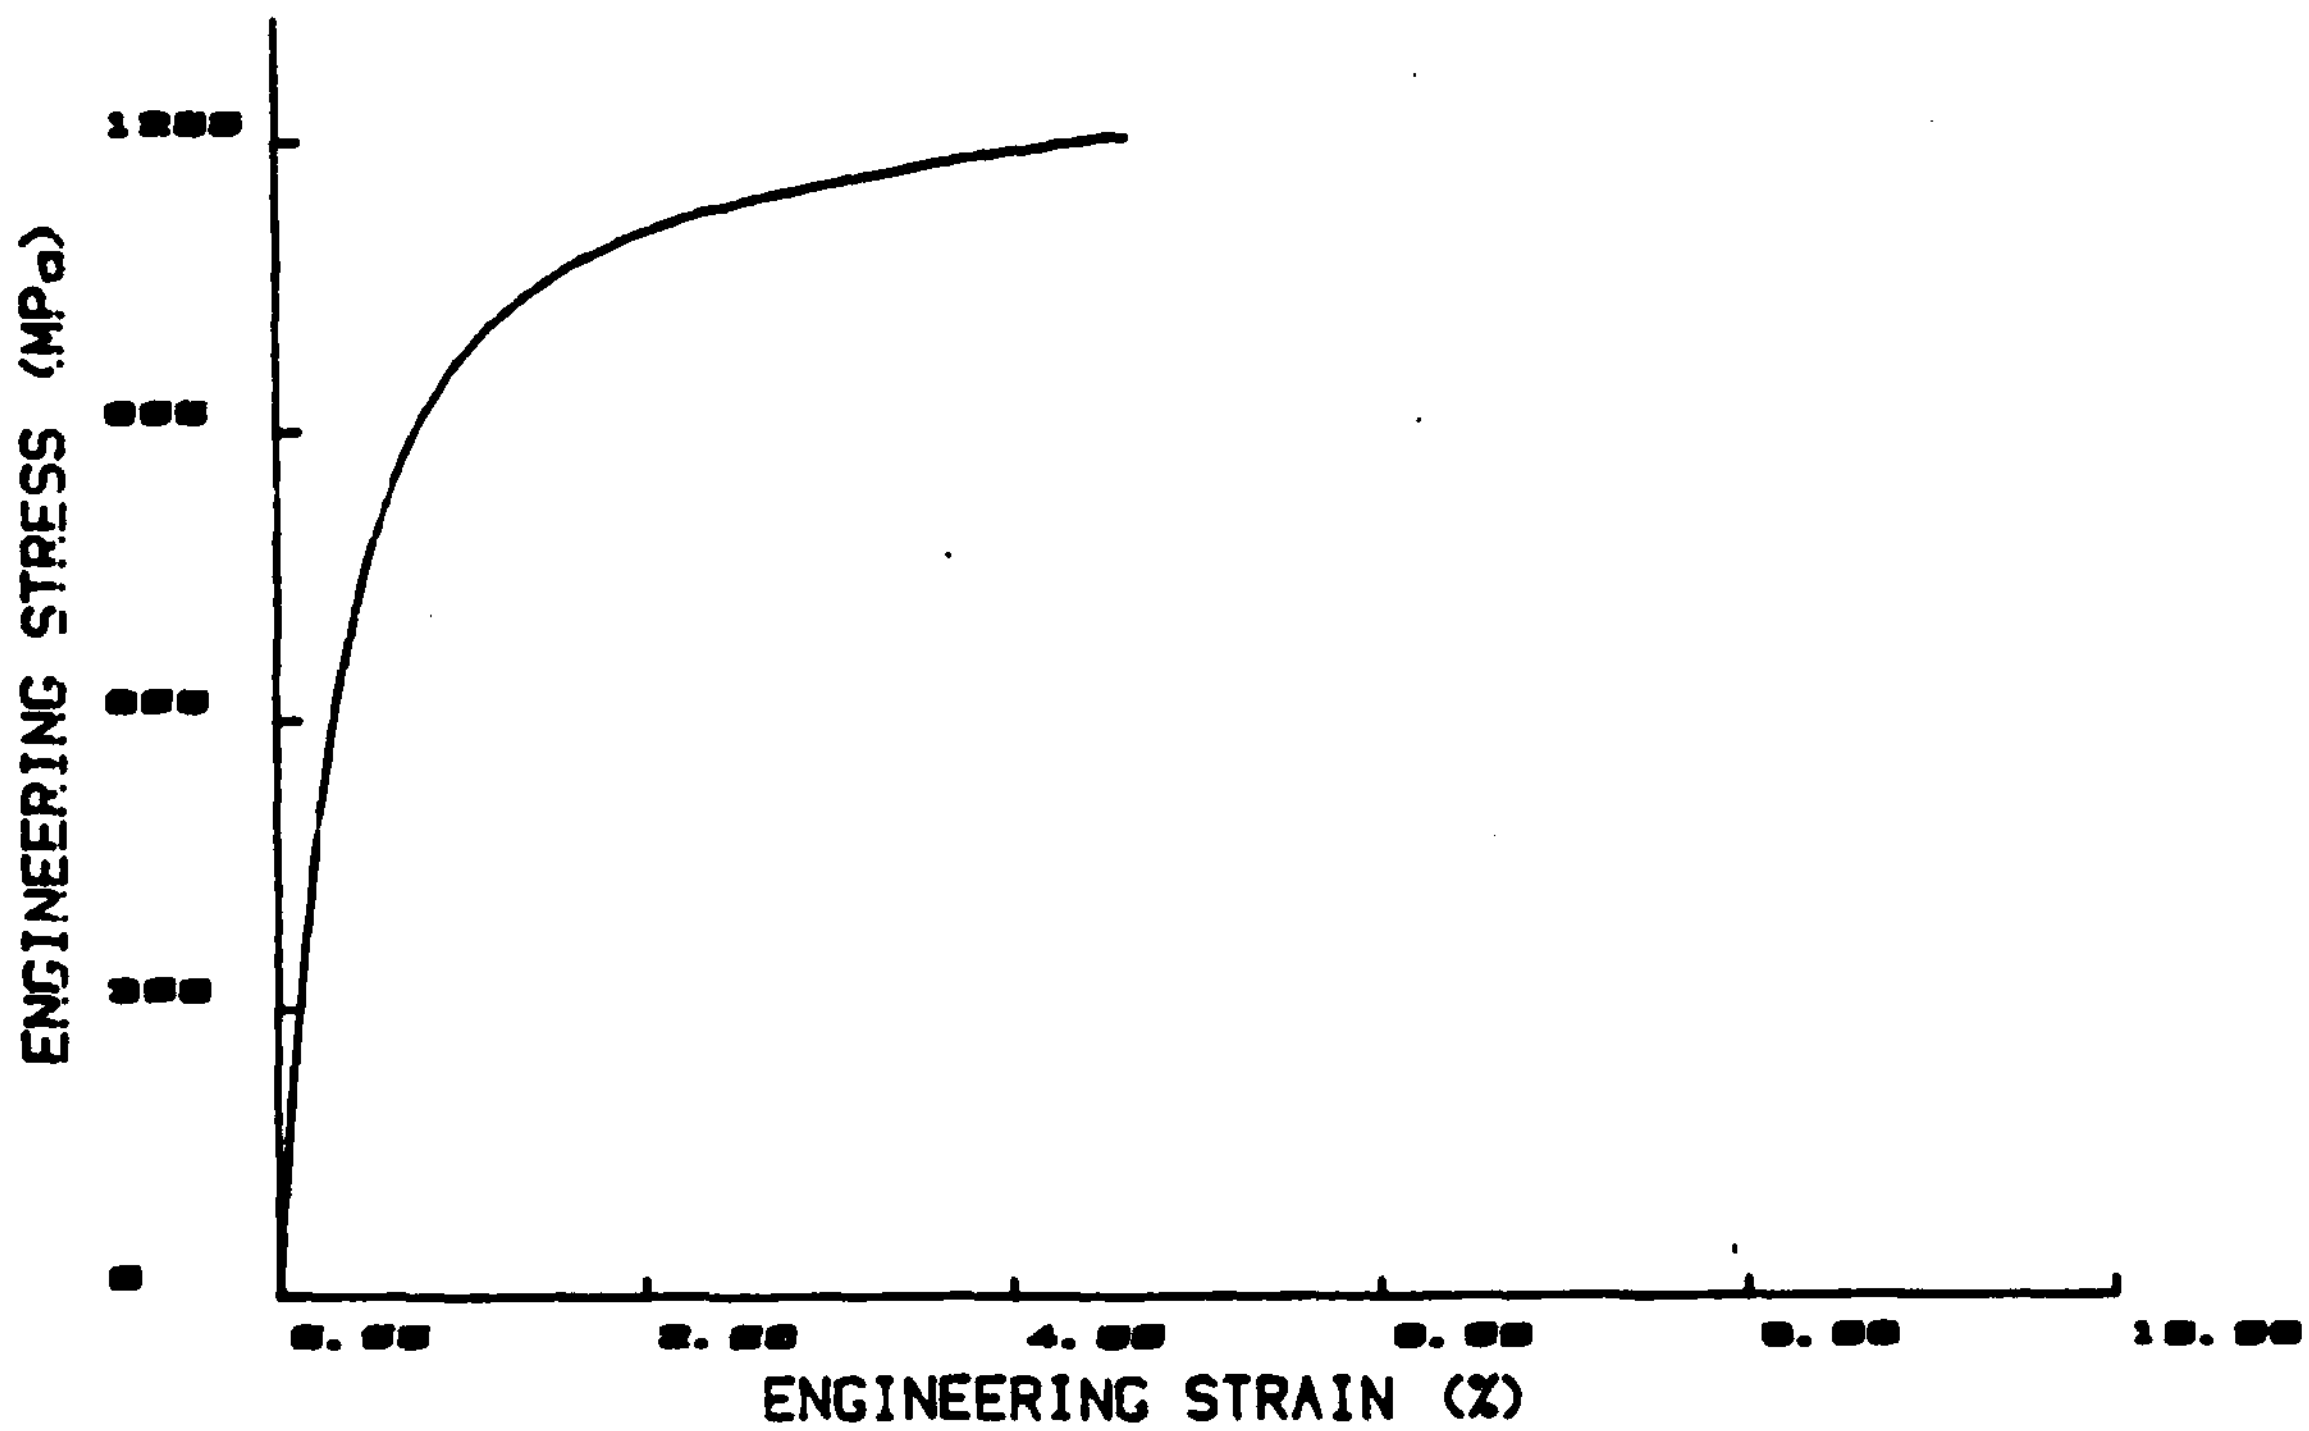

Figure 17. Uniaxial compressive stress-strain curve for a 75% tungsten alloy swaged 21%, Specimen No. 363.

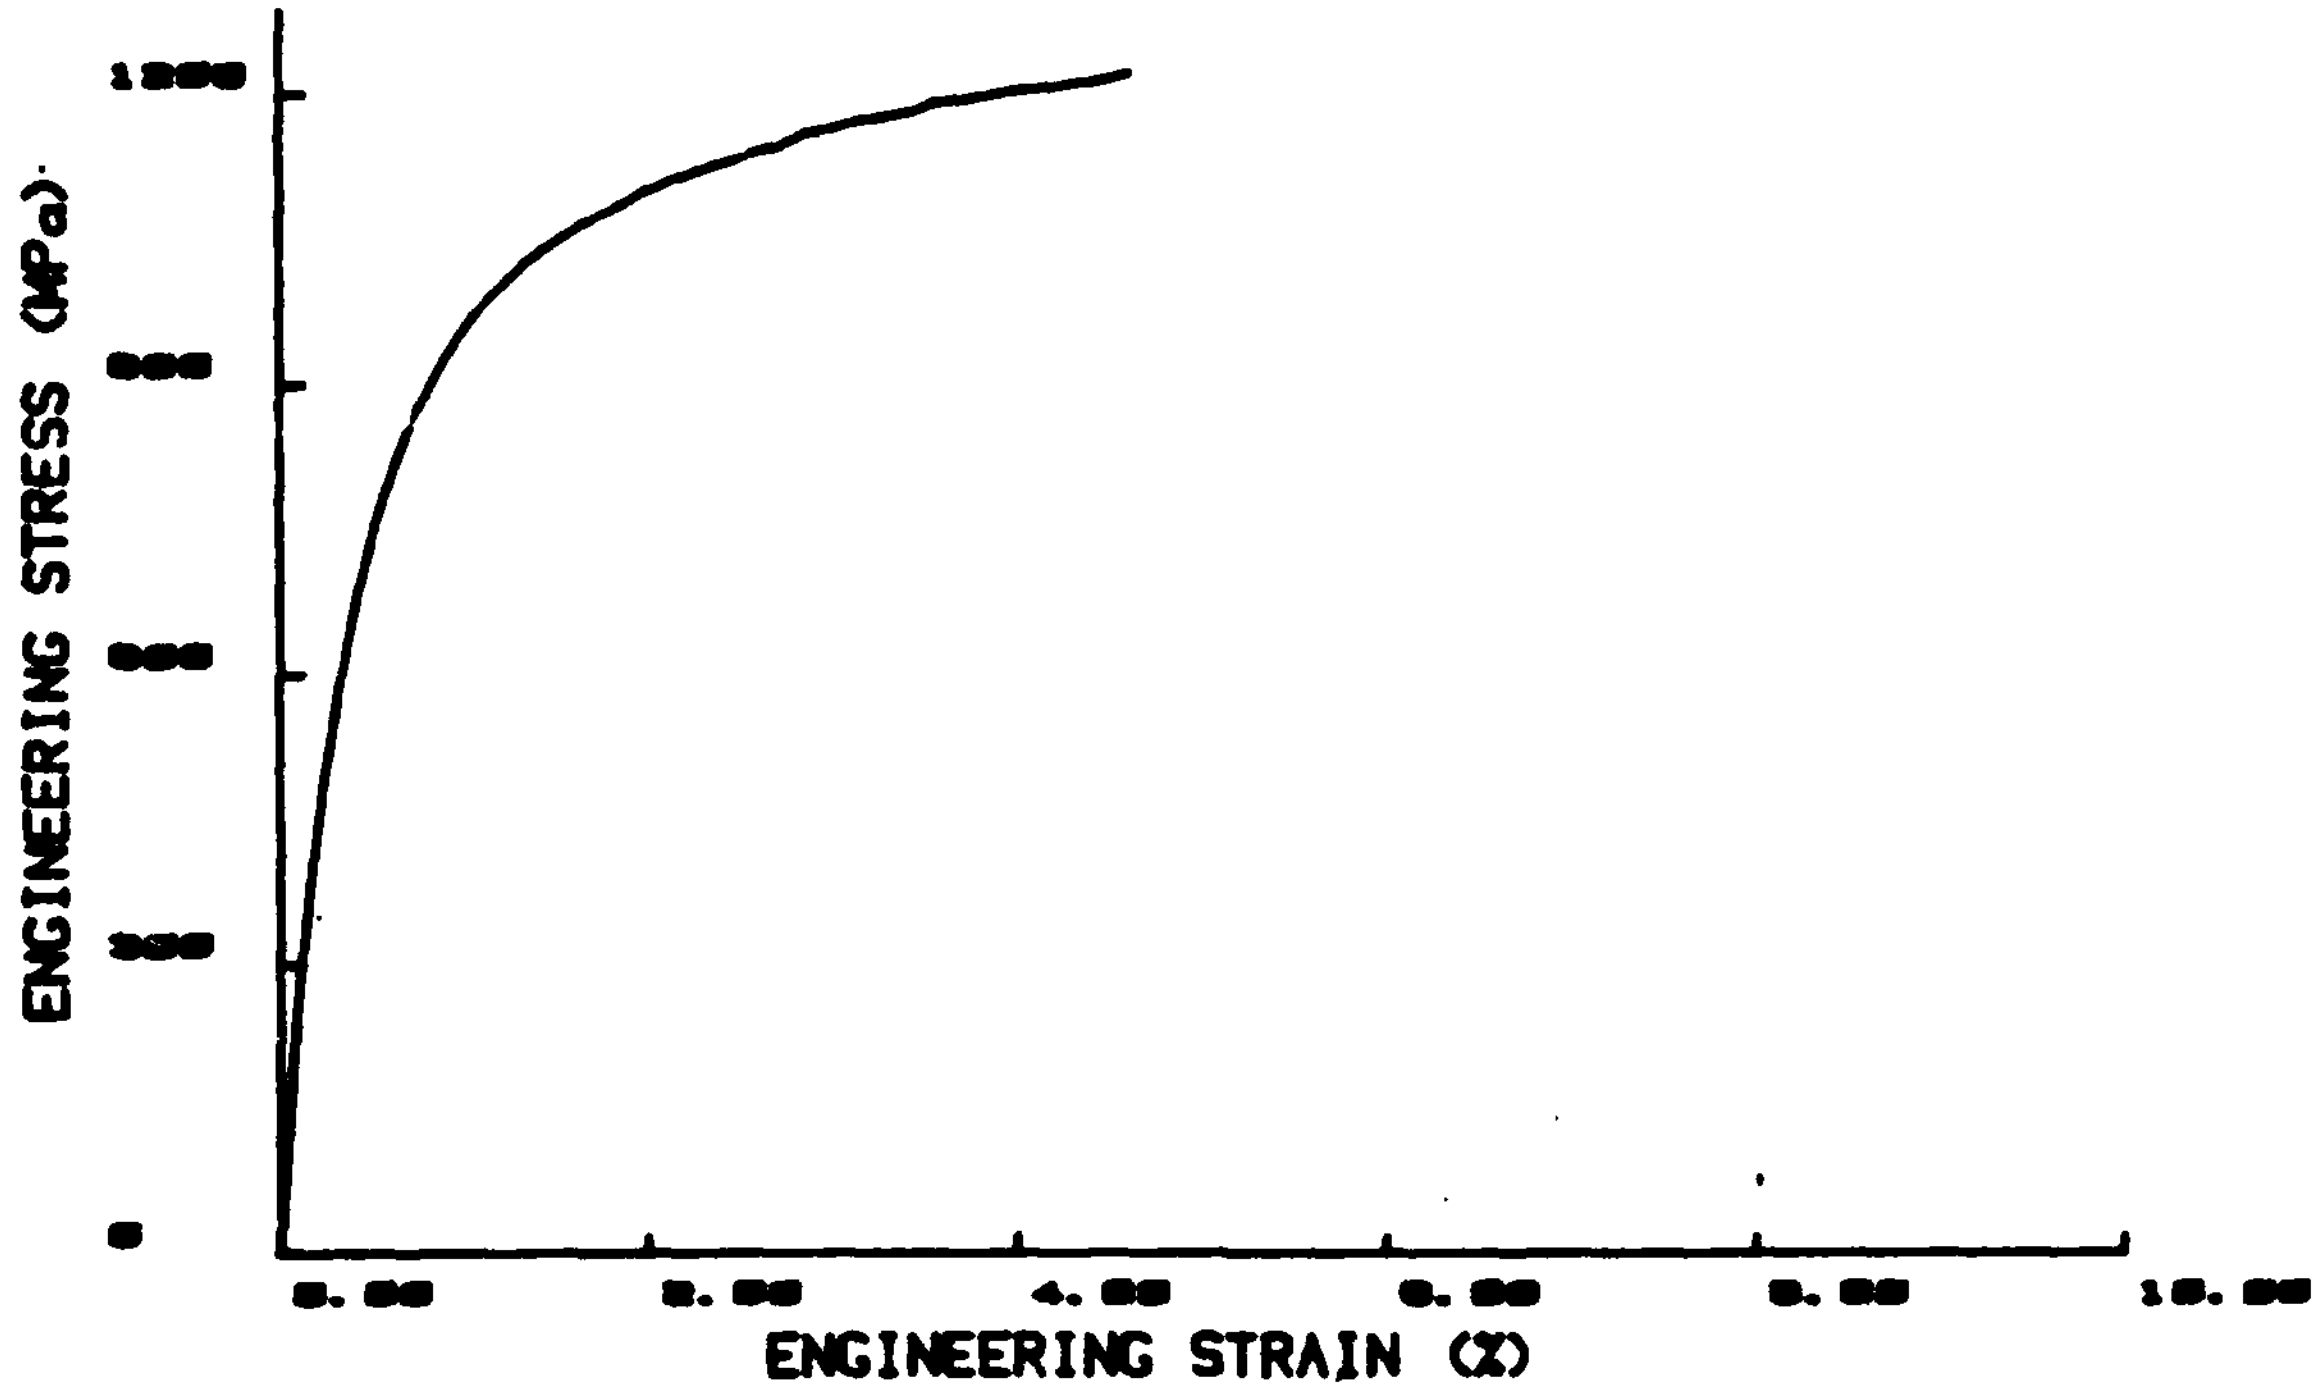

Figure 18. Uniaxial compressive stress-strain curve for a 75% tungsten alloy swaged 21%, Specimen No. 364.

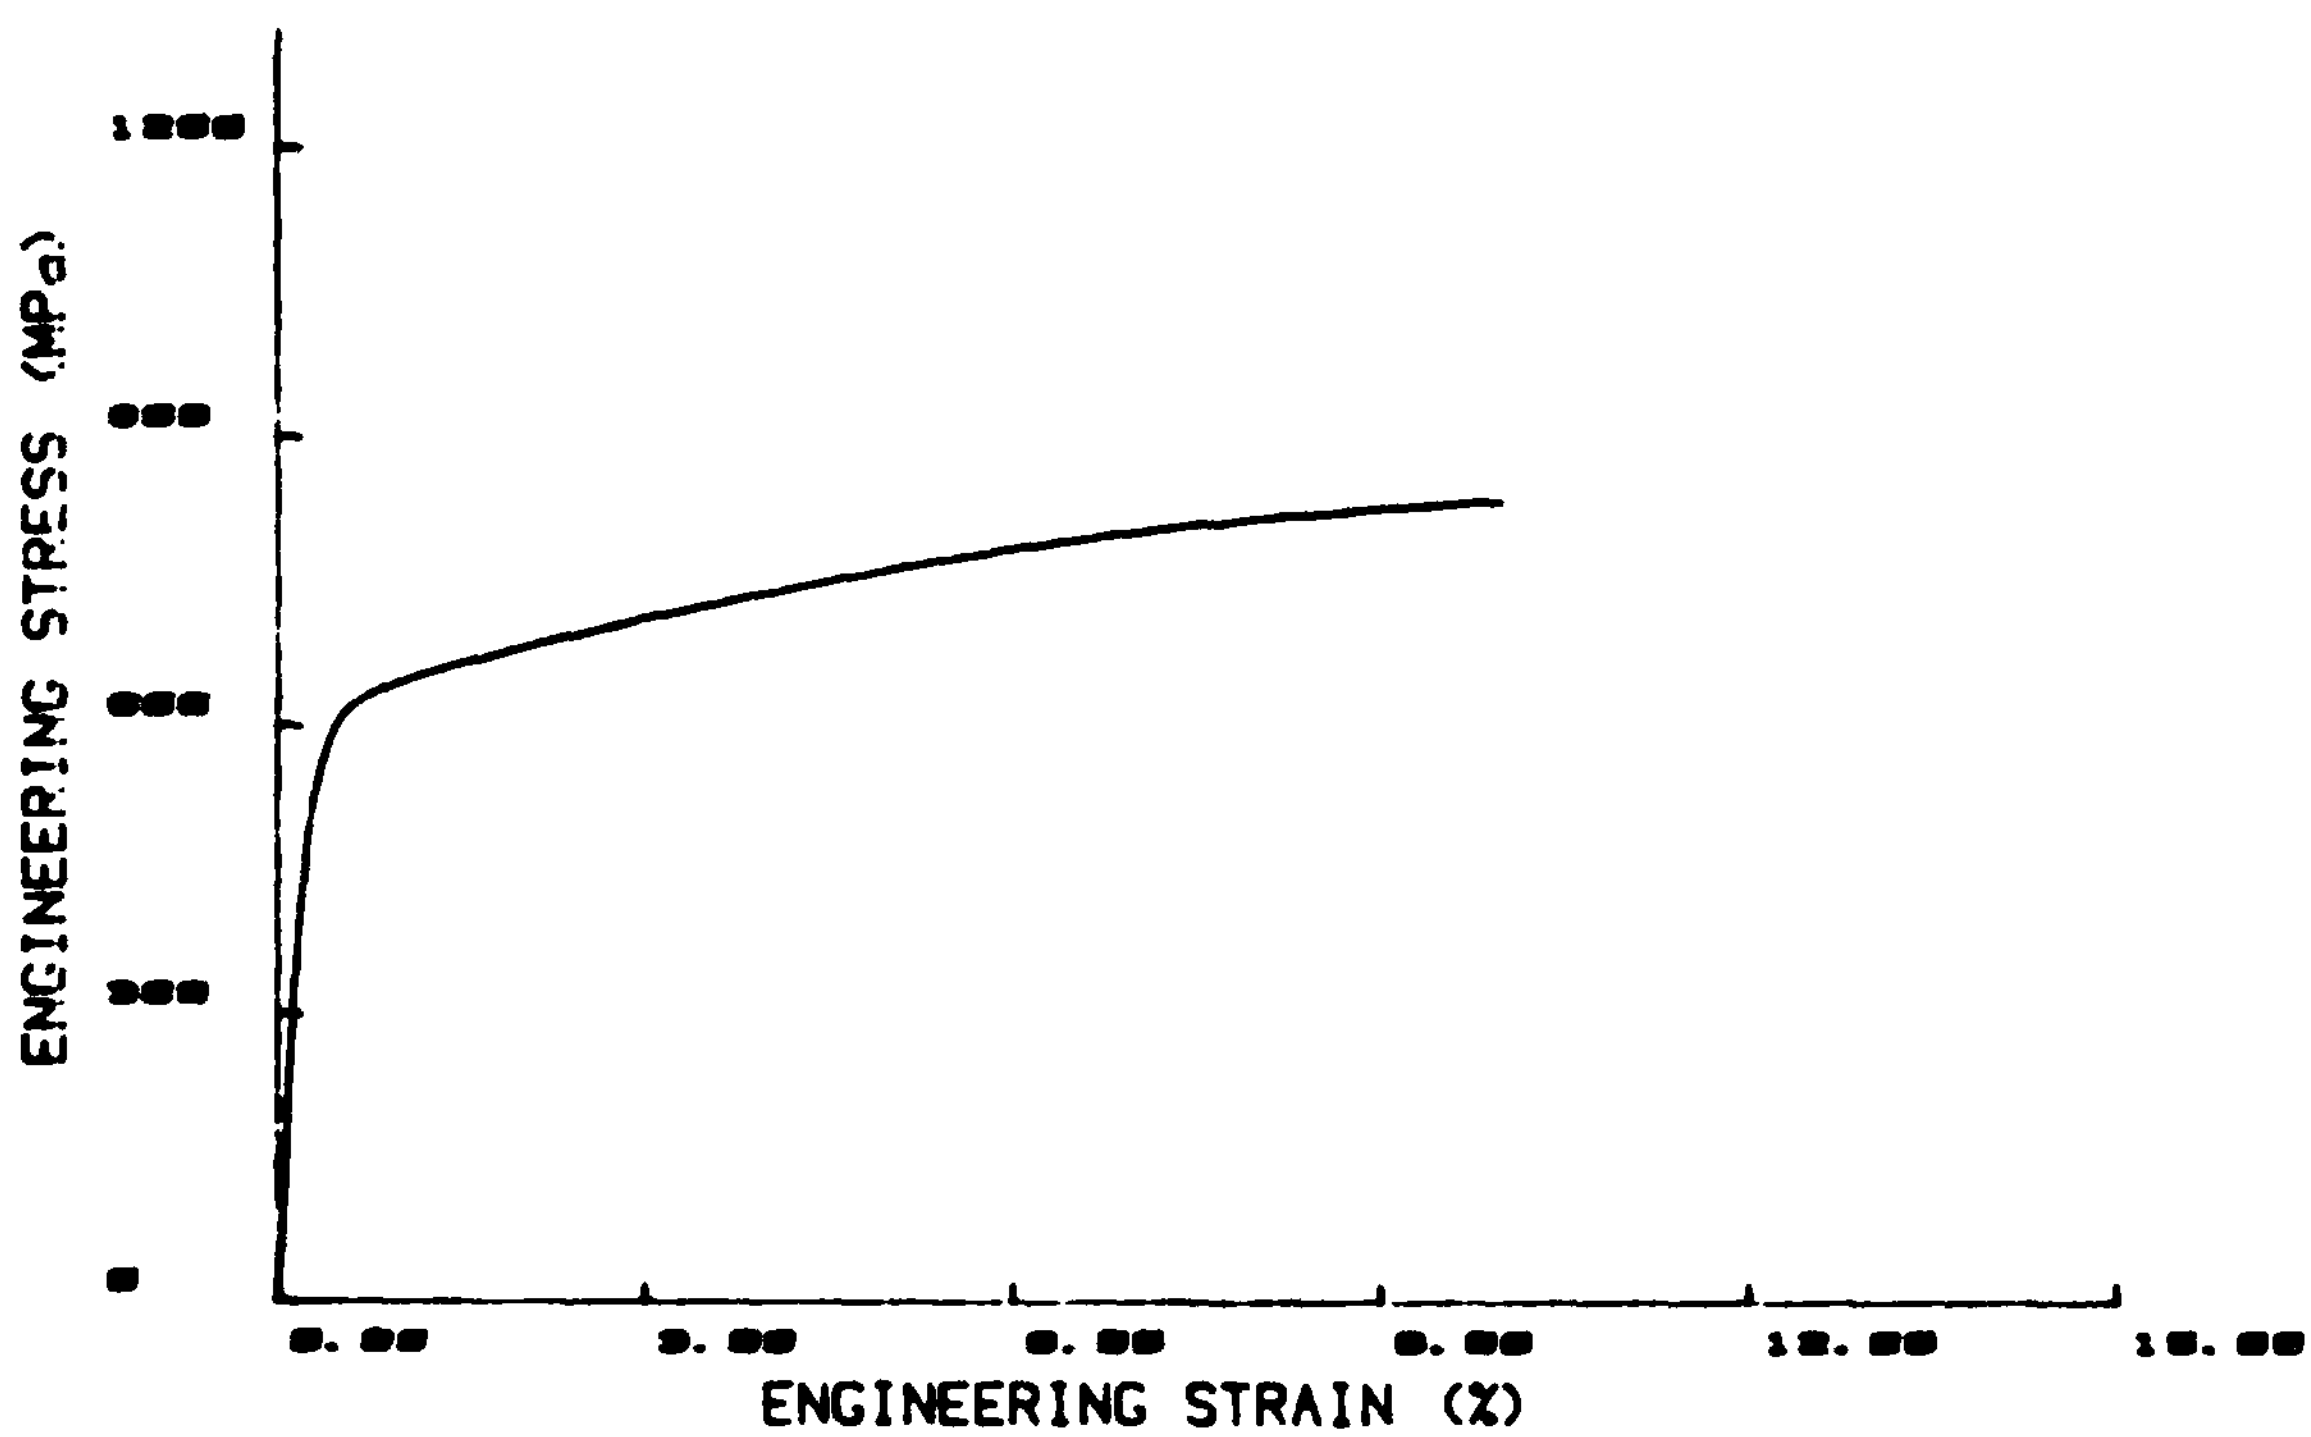

Figure 19. Uniaxial tensile stress-strain curve for a 90% tungsten alloy, double sintered, Specimen No. 331.

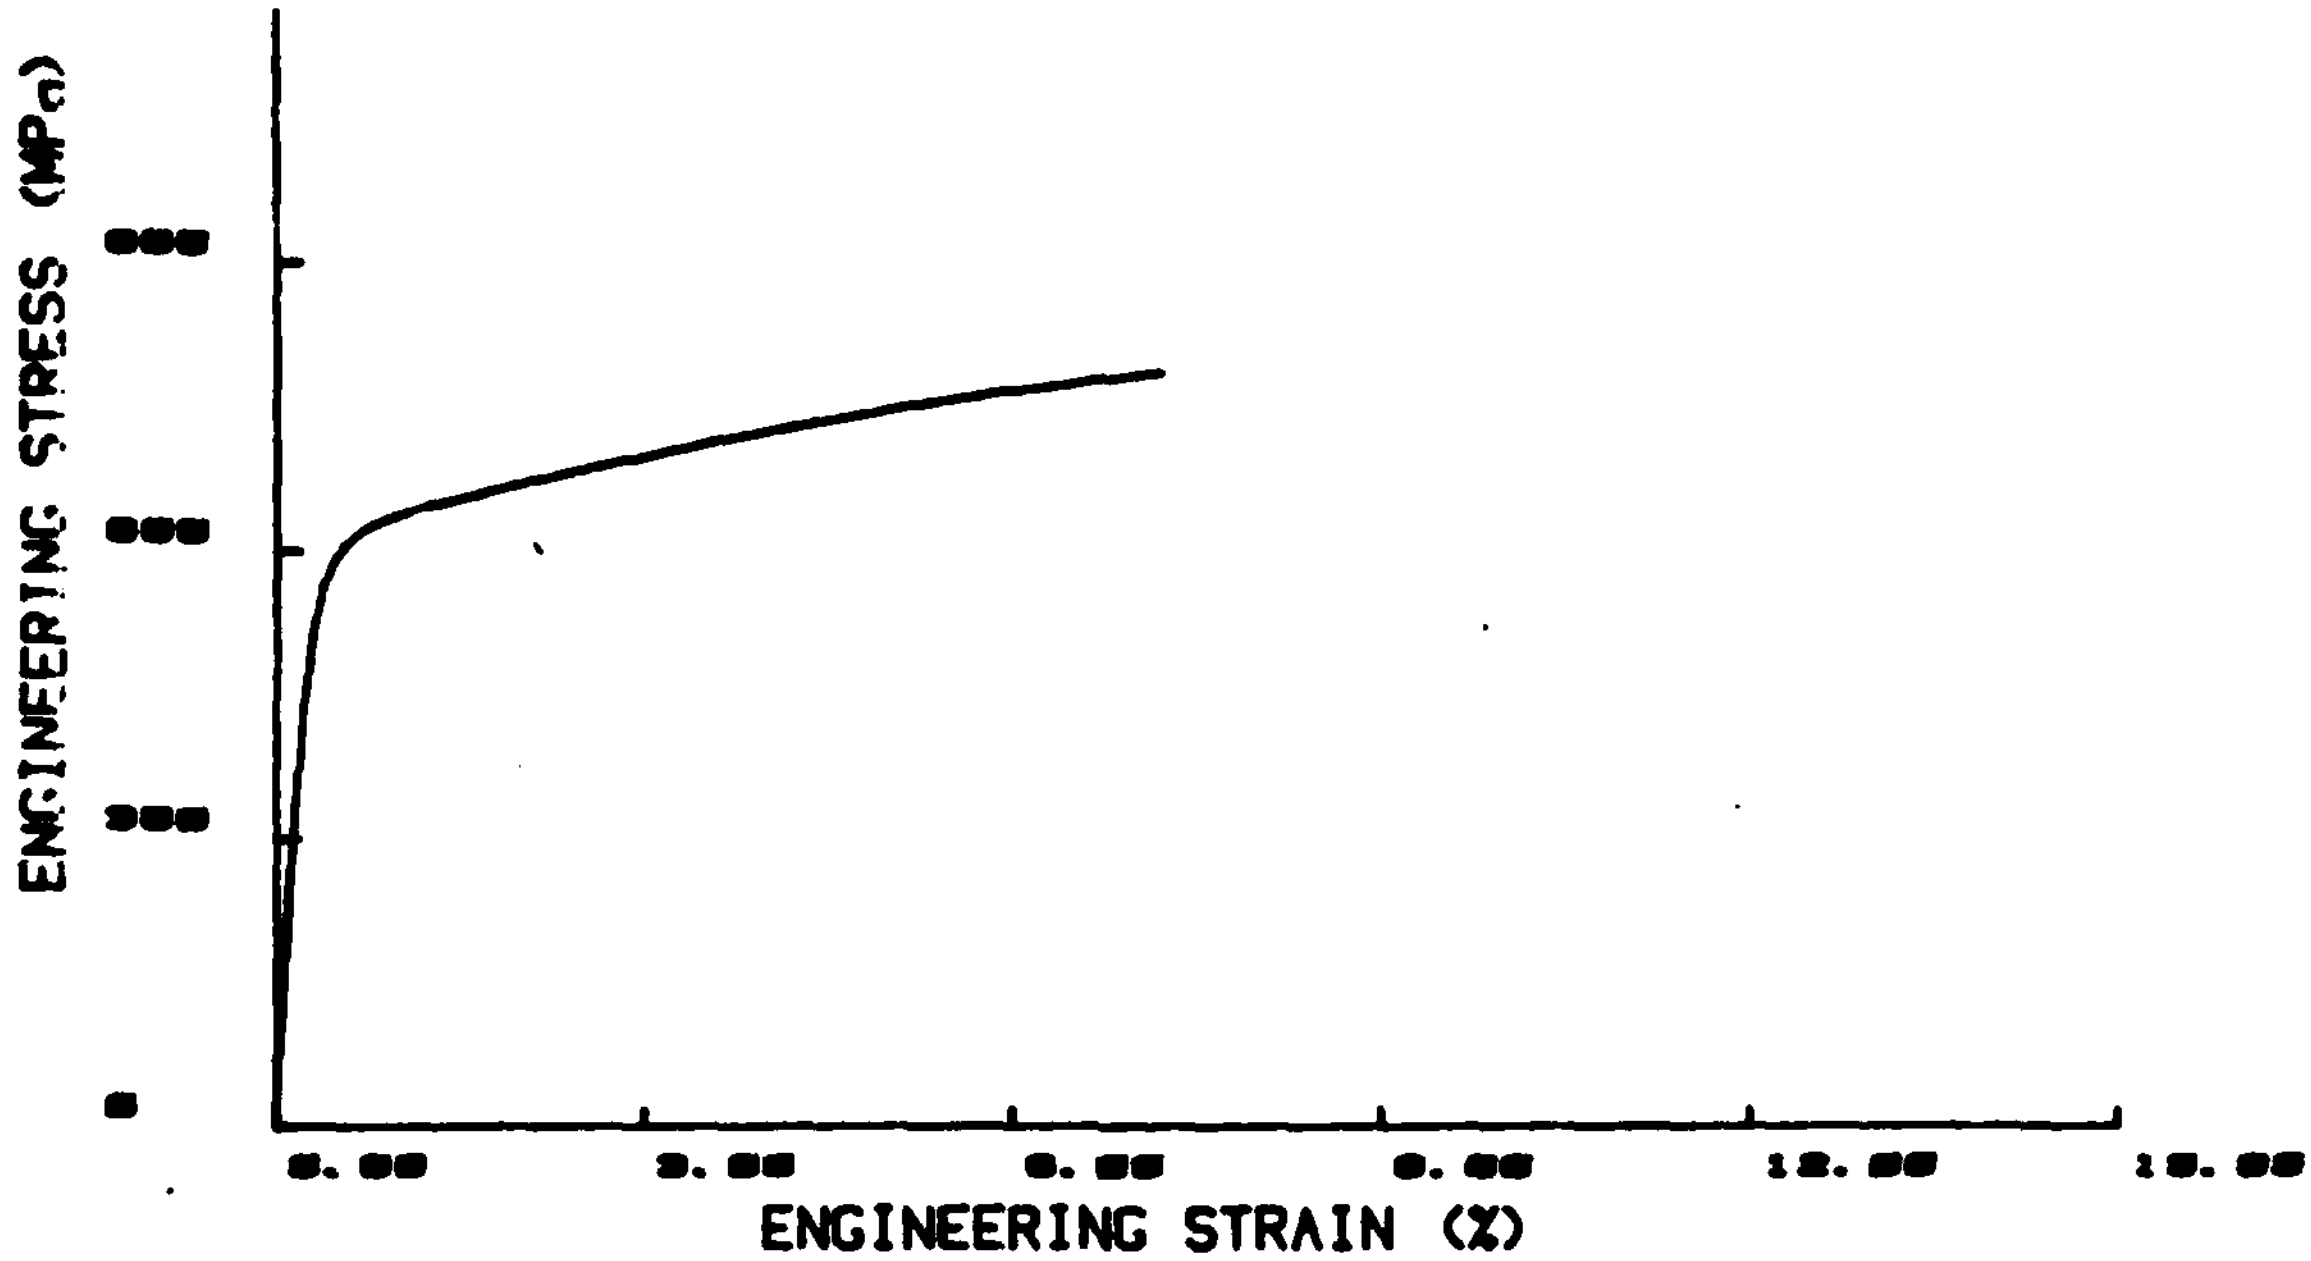

Figure 20. Uniaxial tensile stress-strain curve for a 90% tungsten alloy, double sintered, Specimen No. 335.

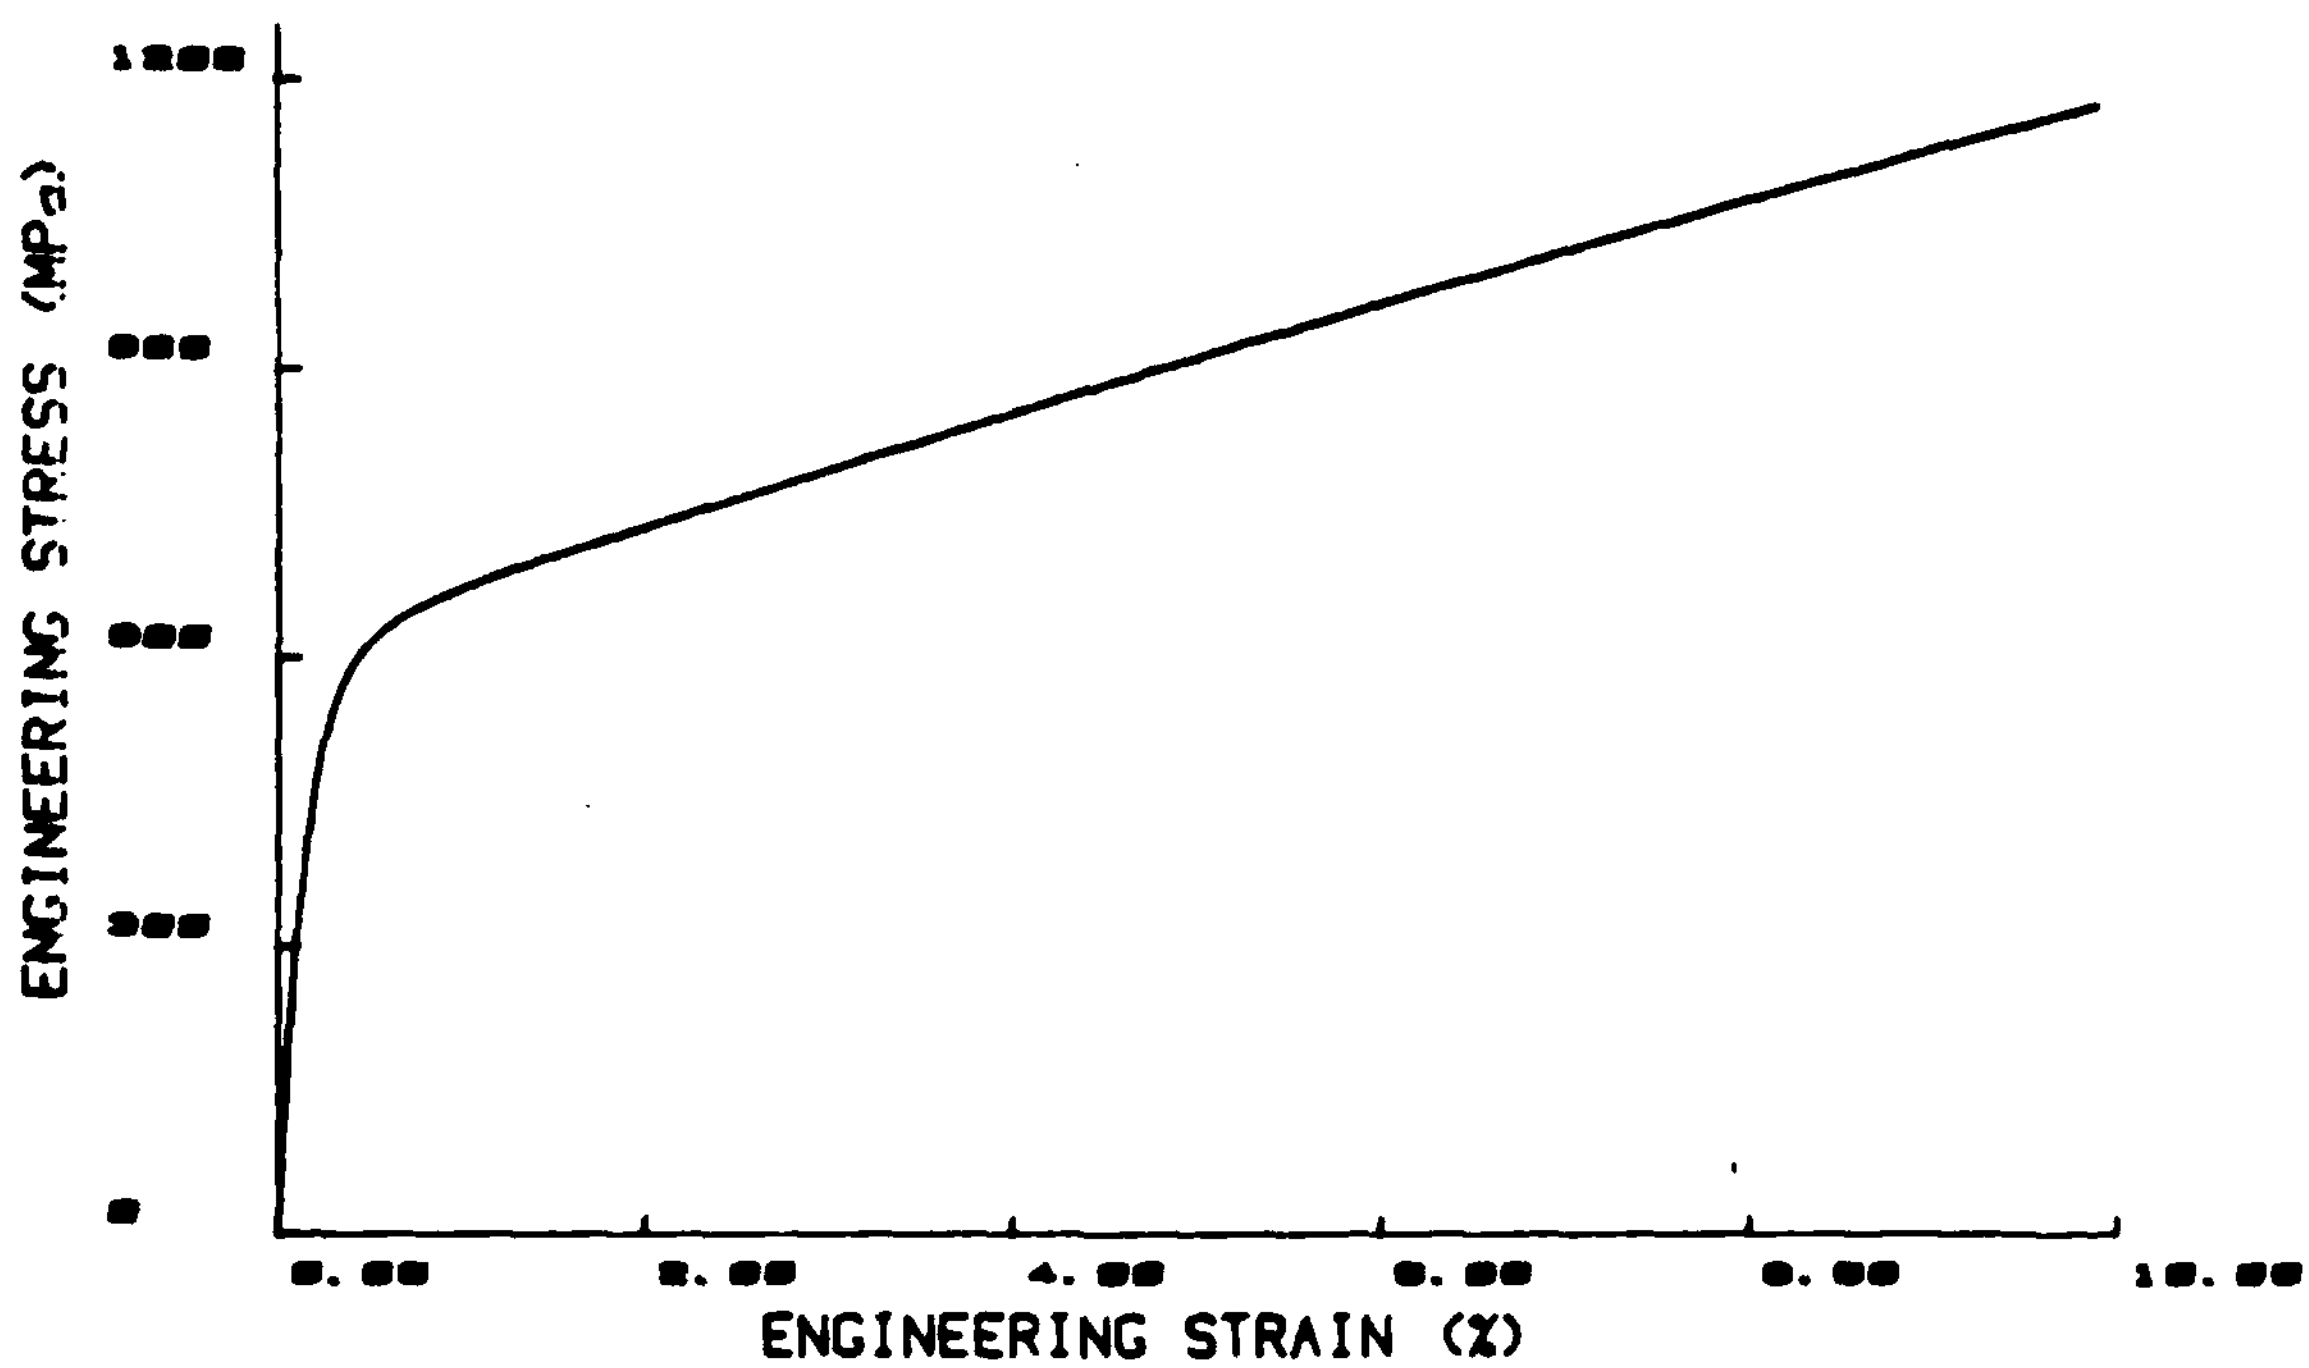

Figure 21. Uniaxial compressive stress-strain curve for a 90% tungsten alloy, double sintered, Specimen No. 336.

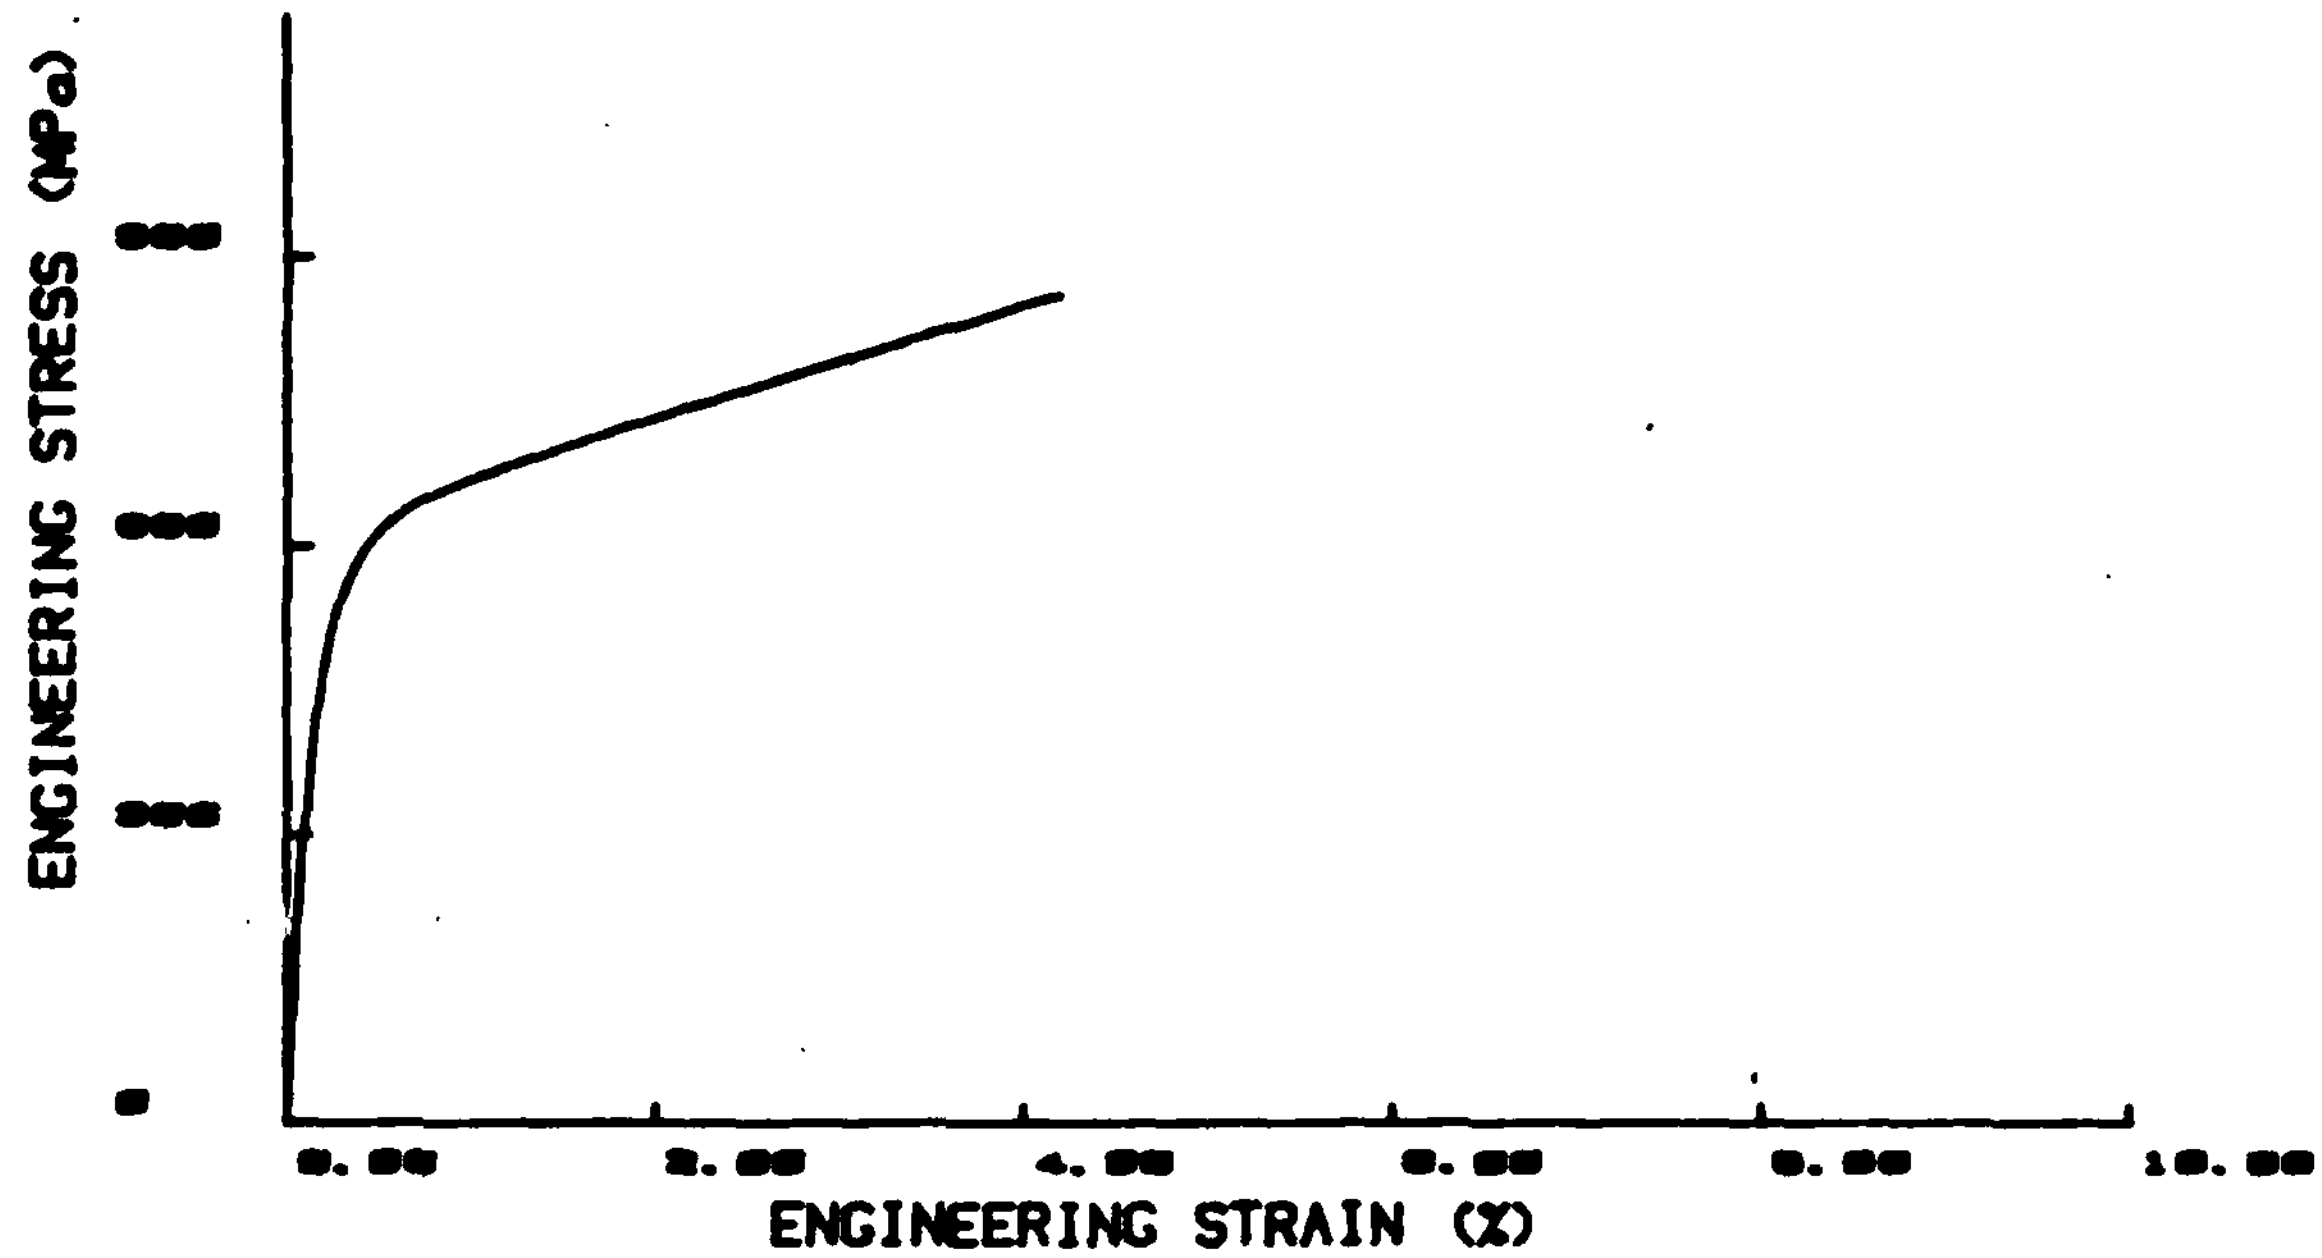

Figure 22. Uniaxial compressive stress-strain curve for a 90% tungsten alloy, double sintered, Specimen No. 339.

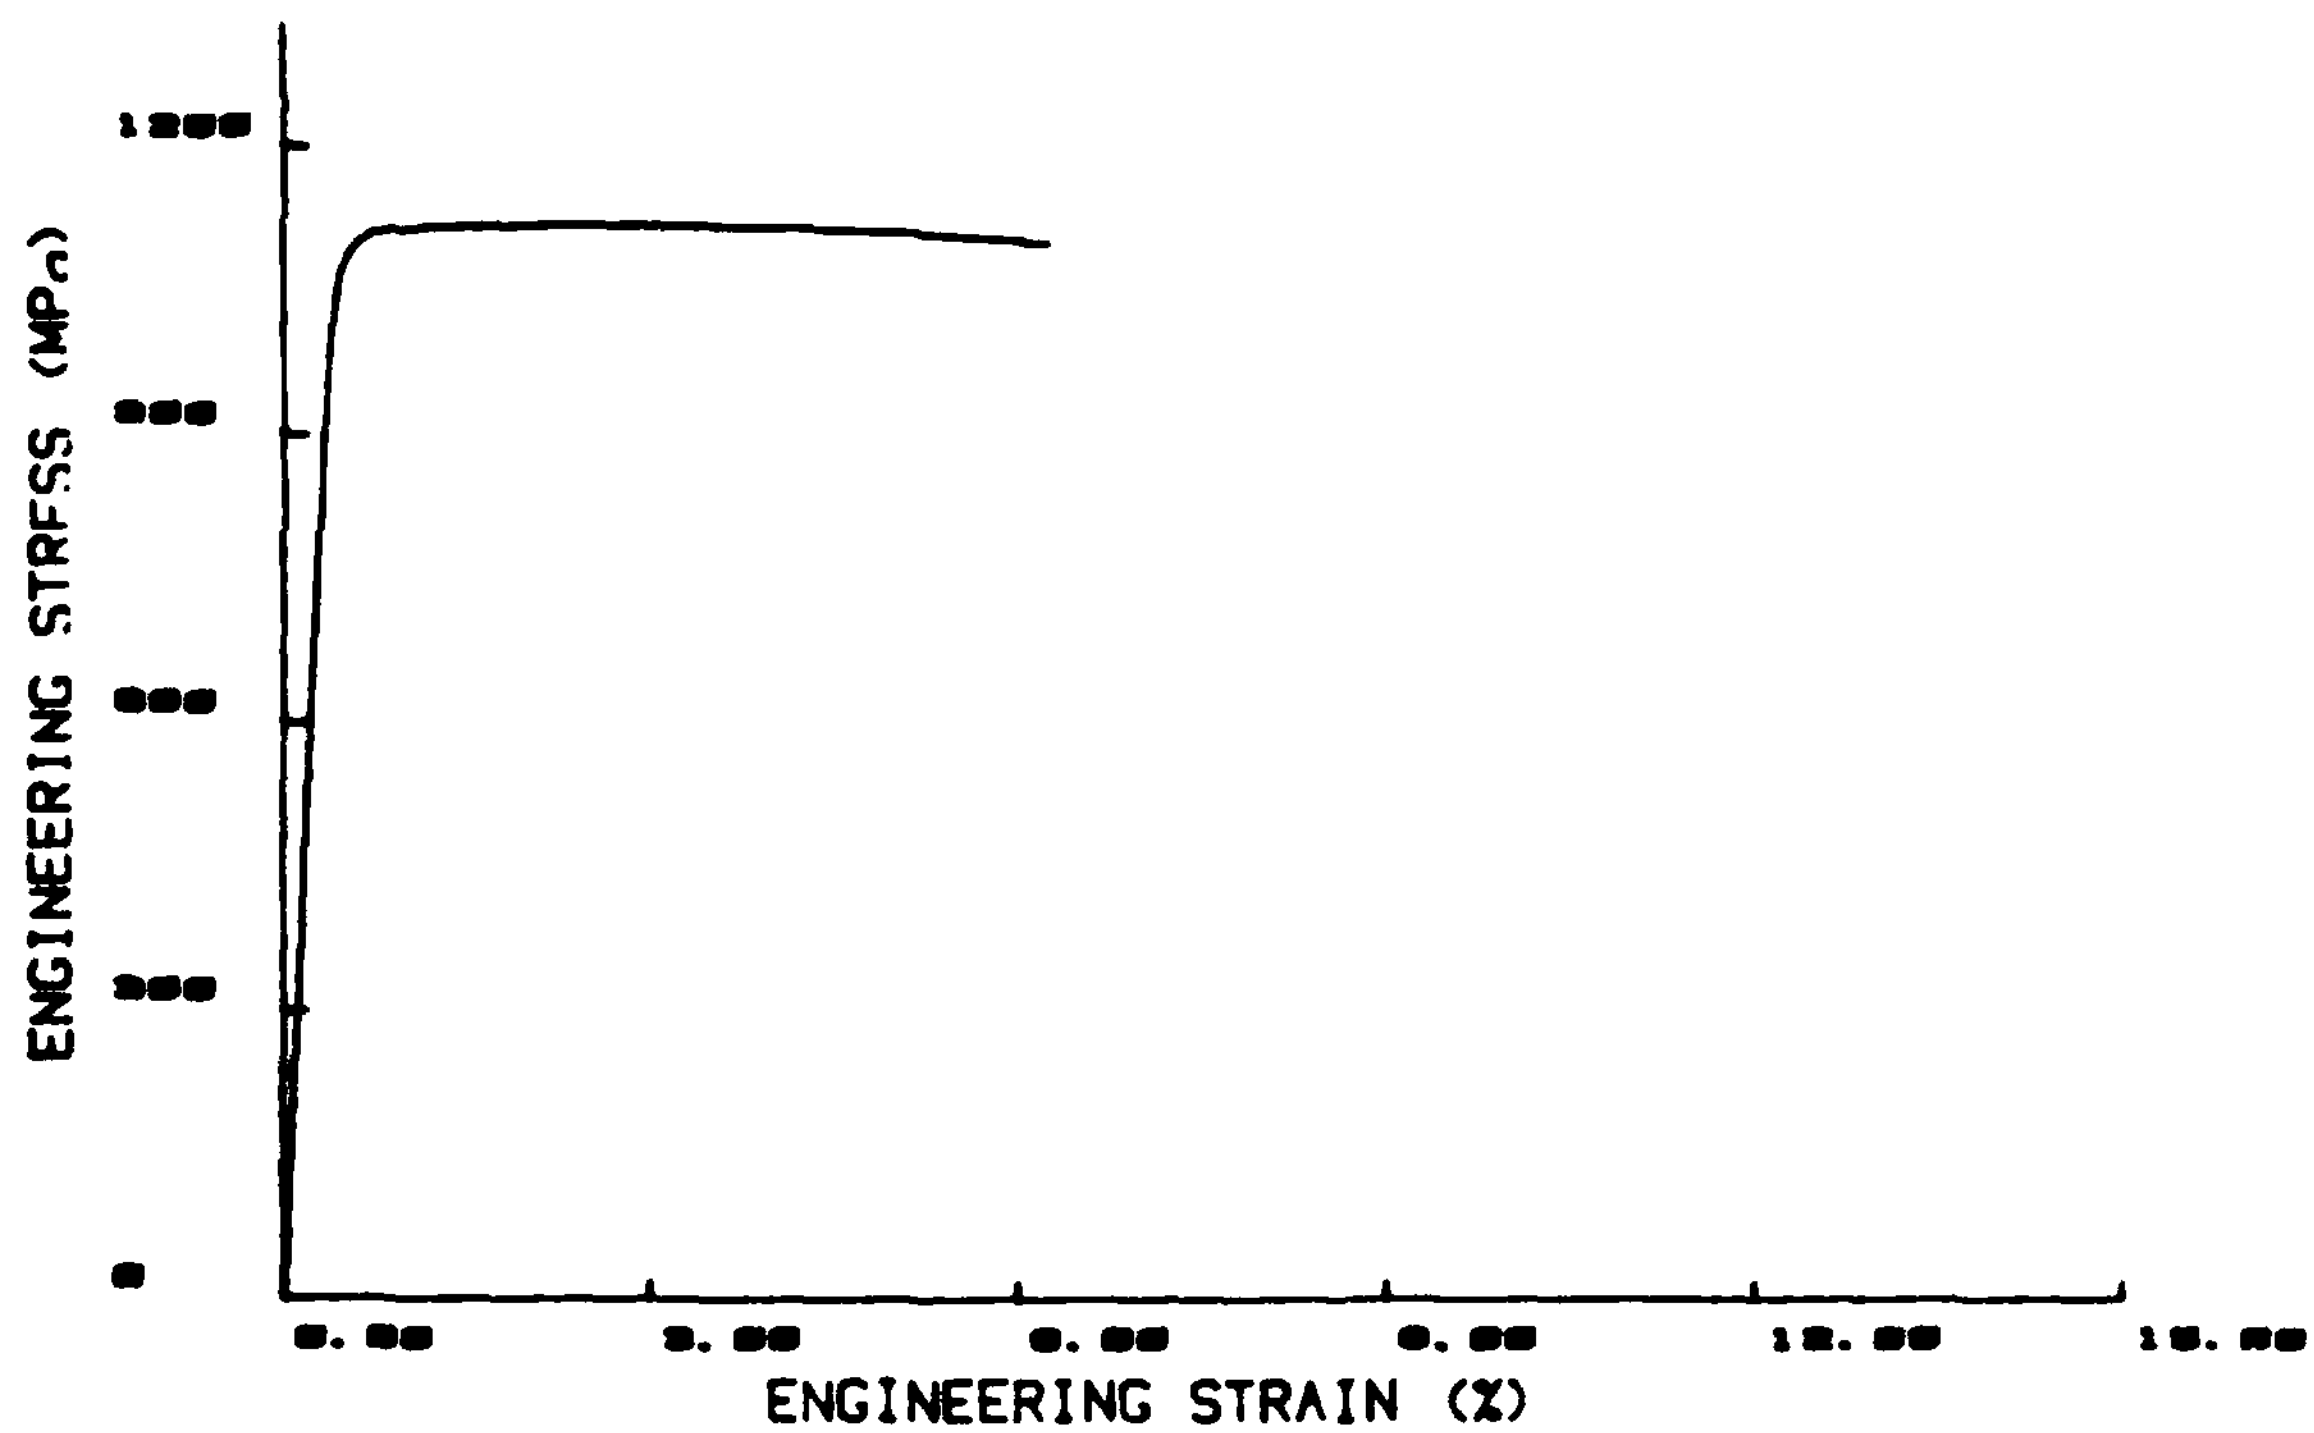

Figure 23. Uniaxial tensile stress-strain curve for a 95% tungsten alloy, Spec.men No. 332.

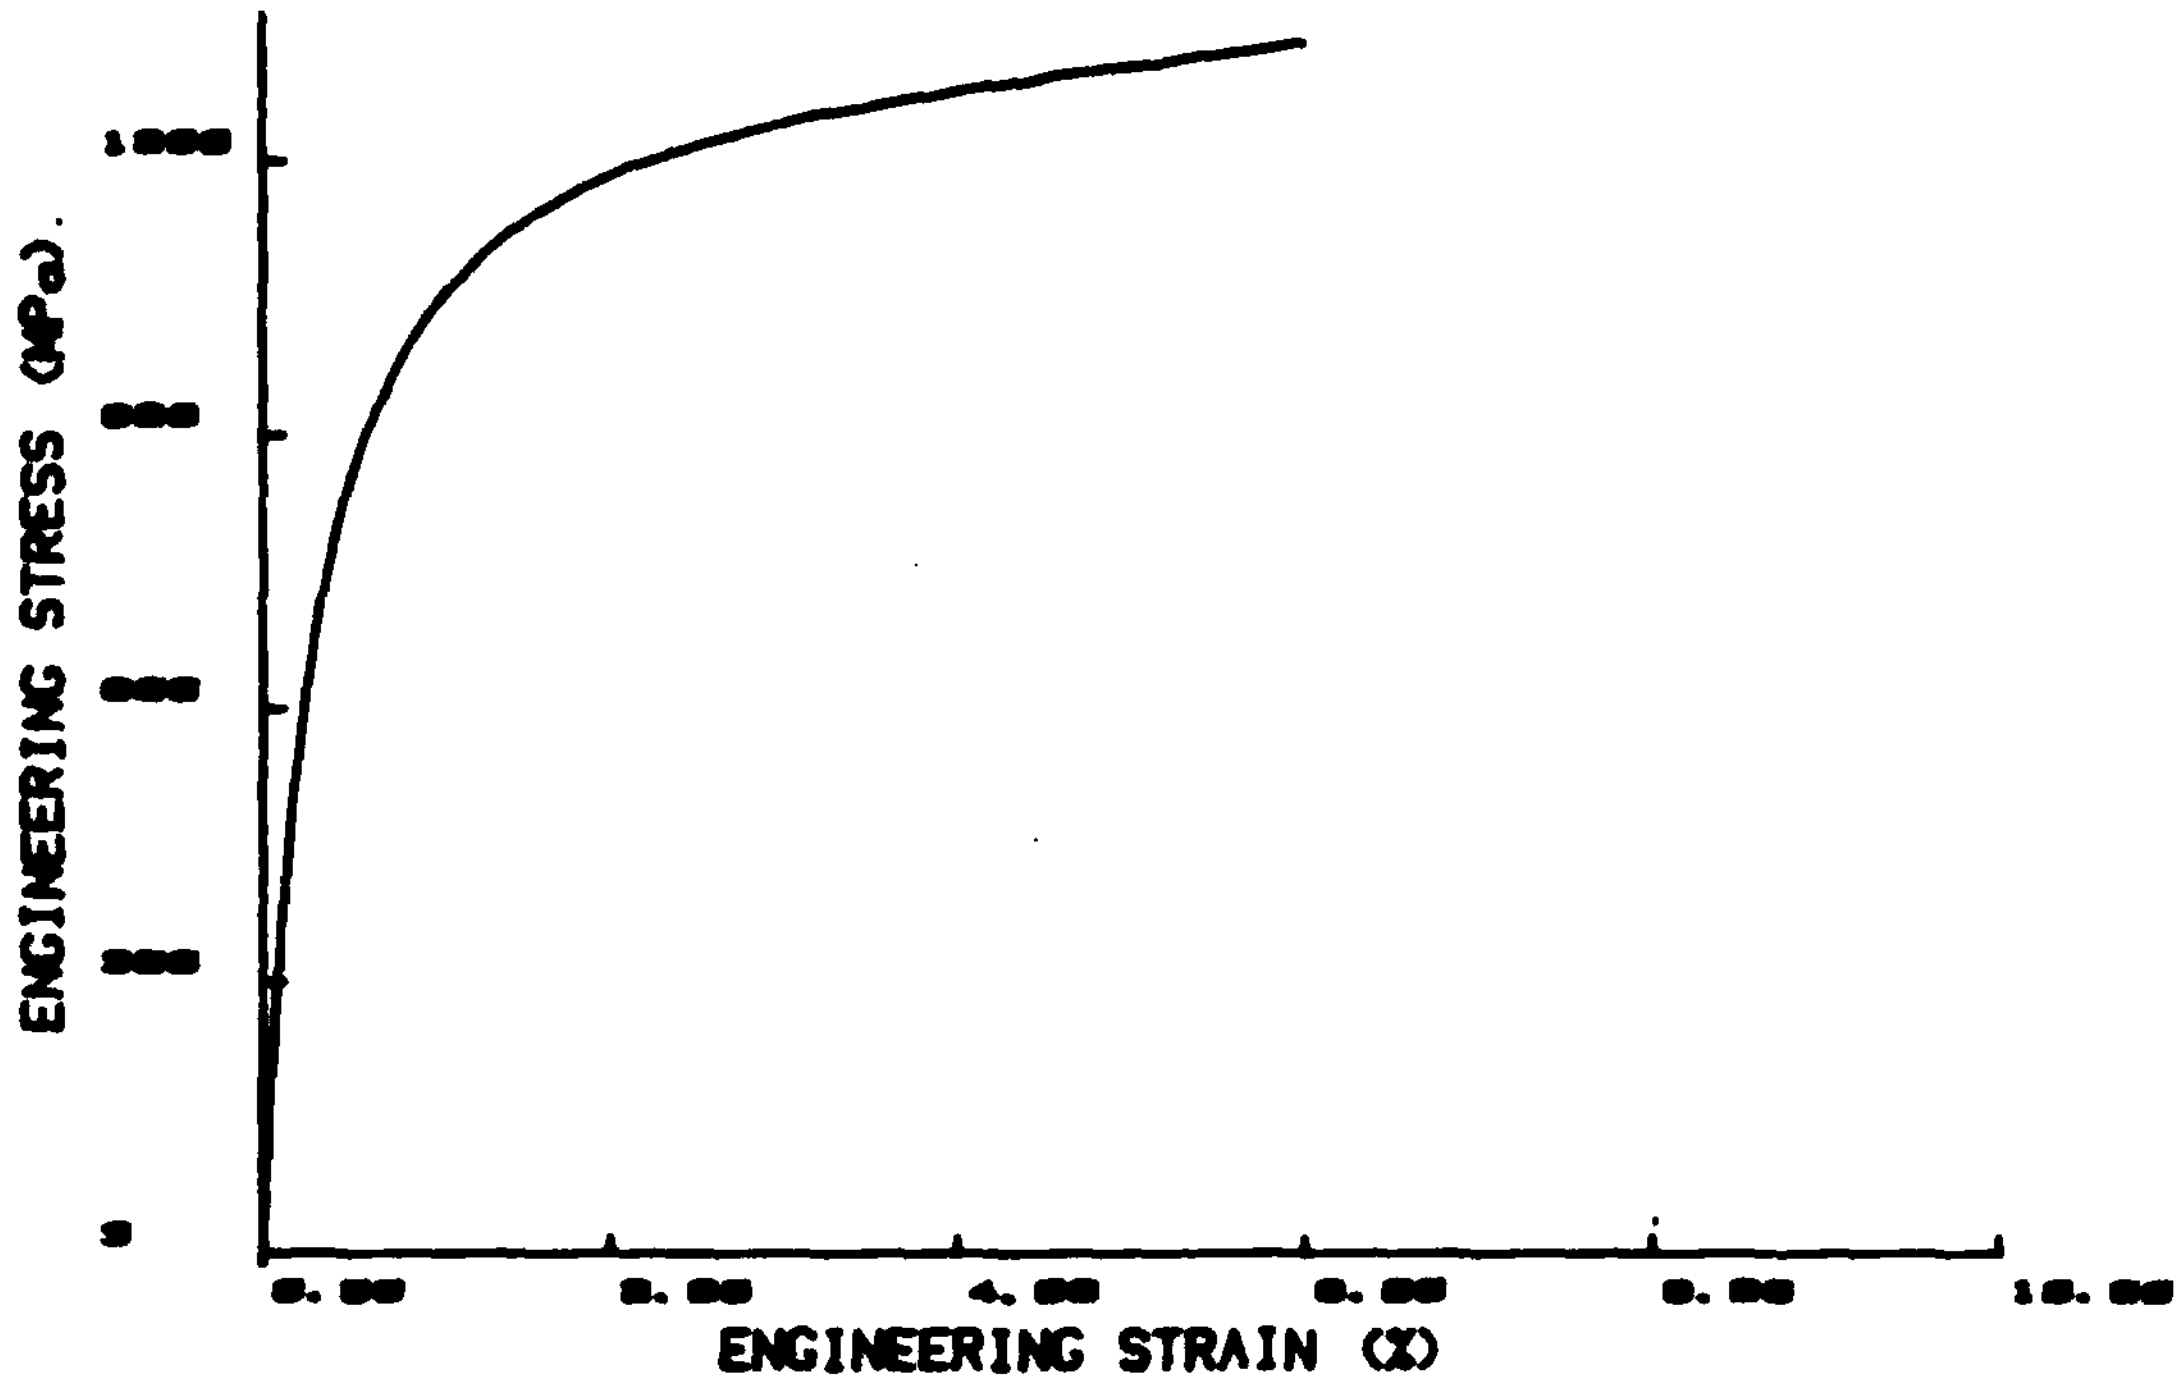

Figure 24. Uniaxial compressive stress-strain curve for a 95% tungsten alloy, Specimen No. 341.

The original material used in the penetrators was a 90% tungsten alloy as supplied by Teledyne Firth-Sterling Co. As stated, the motivation for conducting these tests was the unexpected performance observed during the early stages of the program, when the penetration test results for this material began to show unacceptable variations in the ballistic limits for the penetrator.

Engineering data on the replacement material that was supplied by the manufacturer is given in Table I as Test Nos. 331, 335, 336, 339, and in Figures 19-21. The only known change in the processing history of this material as compared to the original material was a double sinter step.

Comparing the original material and it's replacement, one sees very little difference in the mechanical properties. Only enough material was available to conduct tensile tests on the original material. The only differences that appear are in the ultimate stress and strain, and the fracture strain. The ultimate strain is the strain at the ultimate stress, or maximum load. The fracture stress is the load at failure, divided by the cross-sectional area of the specimen at failure.

A brief look was taken at the fracture surfaces of the tensile specimens for both the original and replacement material. Typical electron micrographs of the fractures are shown in Figures 25 and 26. No significant differences were noted in the particle sizes. The most notable difference is in the number of fractured tungsten particles appearing on the fracture surface; the original material reveals a greater number of fractured particles than the replacement material. This differance would account for the higher ultimate stress and strain of the original material. The tungsten particles in the replacement material are not as tightly bound to each other; consequently, failure occurs in an intergranular mode, rather than transgranular. Processing details were not available; a possibility may be that the replacement material was sintered at a lower temperature than the original material.

IV. DISCUSSION

Tungsten alloy is somewhat of a misnomer; the material should be more correctly referred to as a composite, as it is composed of tungsten particles embedded in a metal matrix. Most often for penetrators, this matrix is a nickel-iron material. The material is processed by liquid phase sintering under pressure, i.e. the nickel-iron matrix becomes liquid at the temperature and pressure used during the process. The manufacturer's concern was that the original material had not been fully liquid phase sintered and that it may have contained some porosity. Unfortunately, ballistic testing does not lend itself to valid examination of the small nuances of the material after the test. These penetrators that failed to perform properly could not be examined after the fact to check for porosity. Consequently, the manufacturer decided to resinter the material in an effort to avoid any possible porosity in the penetrators. The material supplied to the Solid Mechanics Branch may or may not have been representative of the entire batch of material.

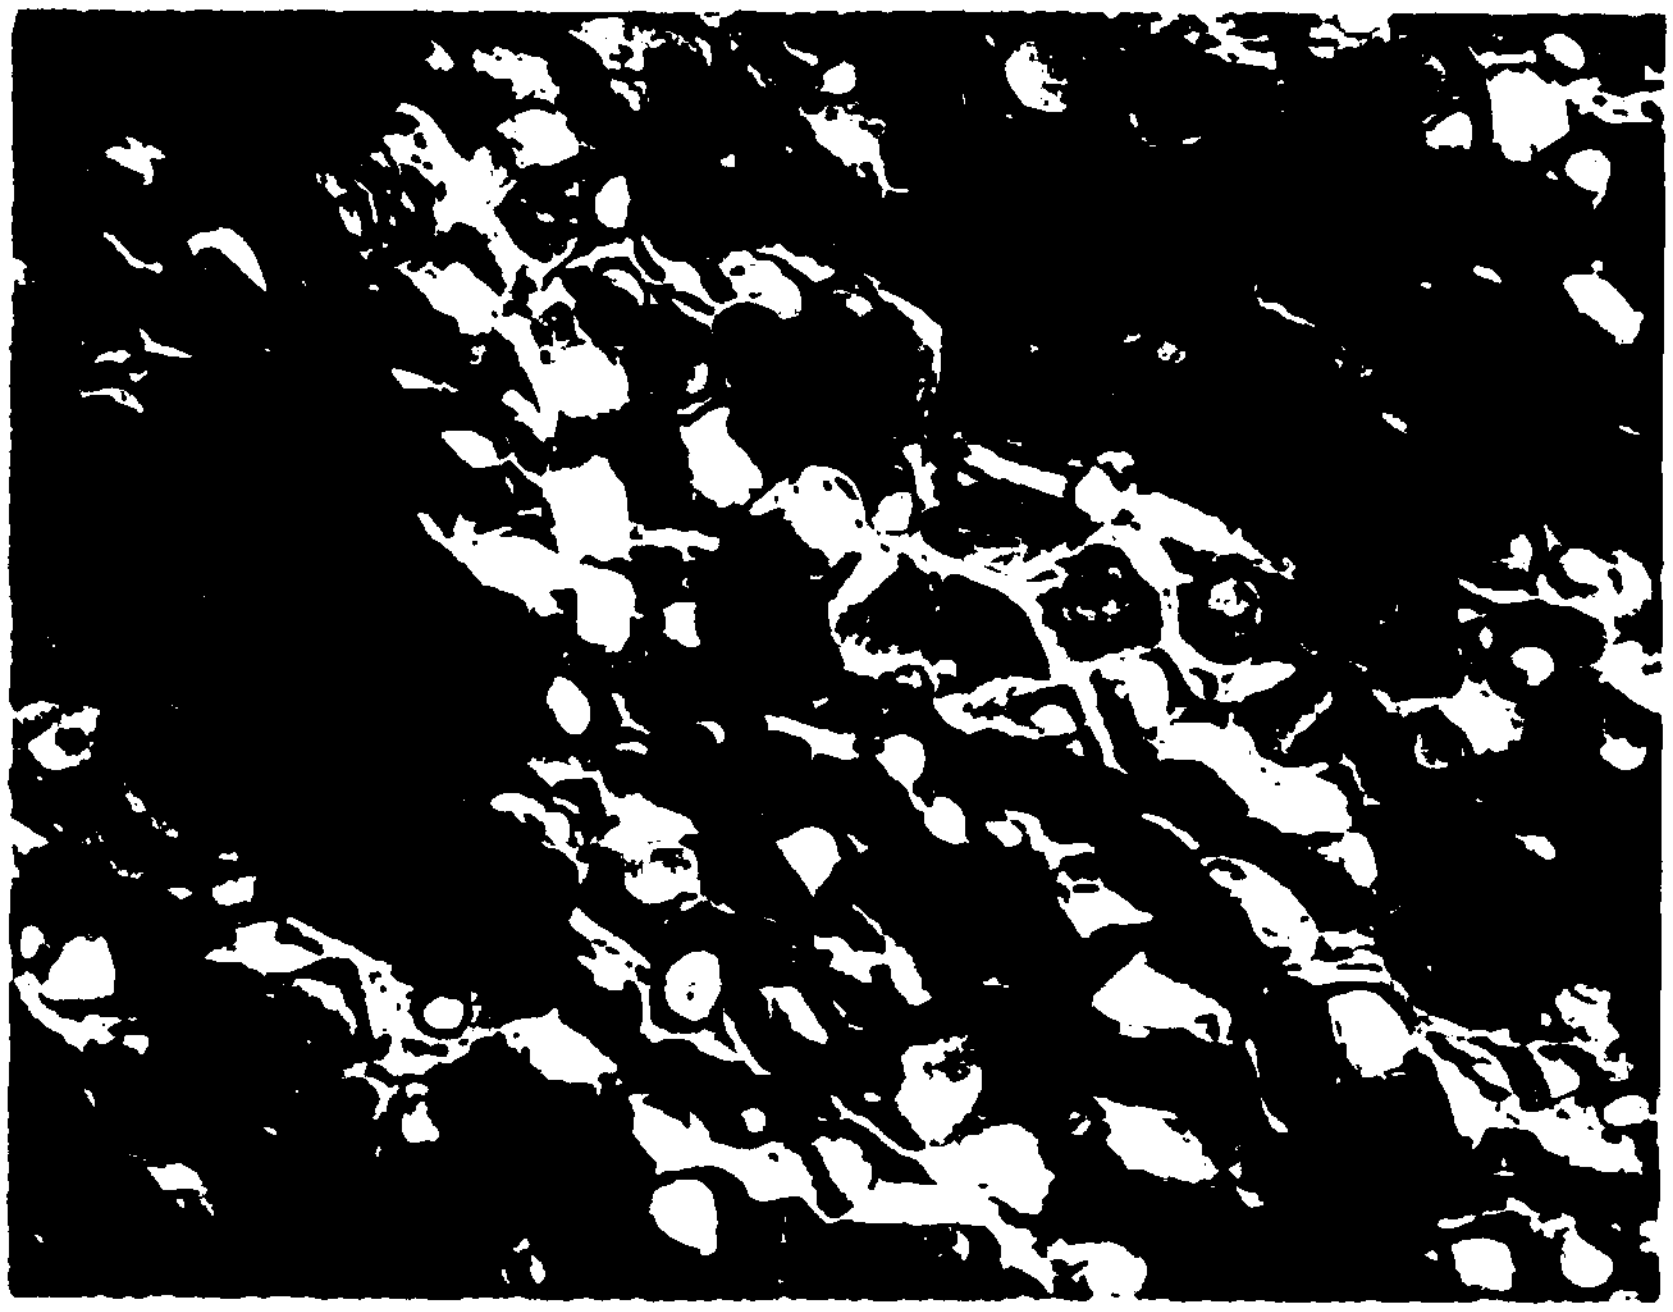

Figure 25. Fracture surface of original material.

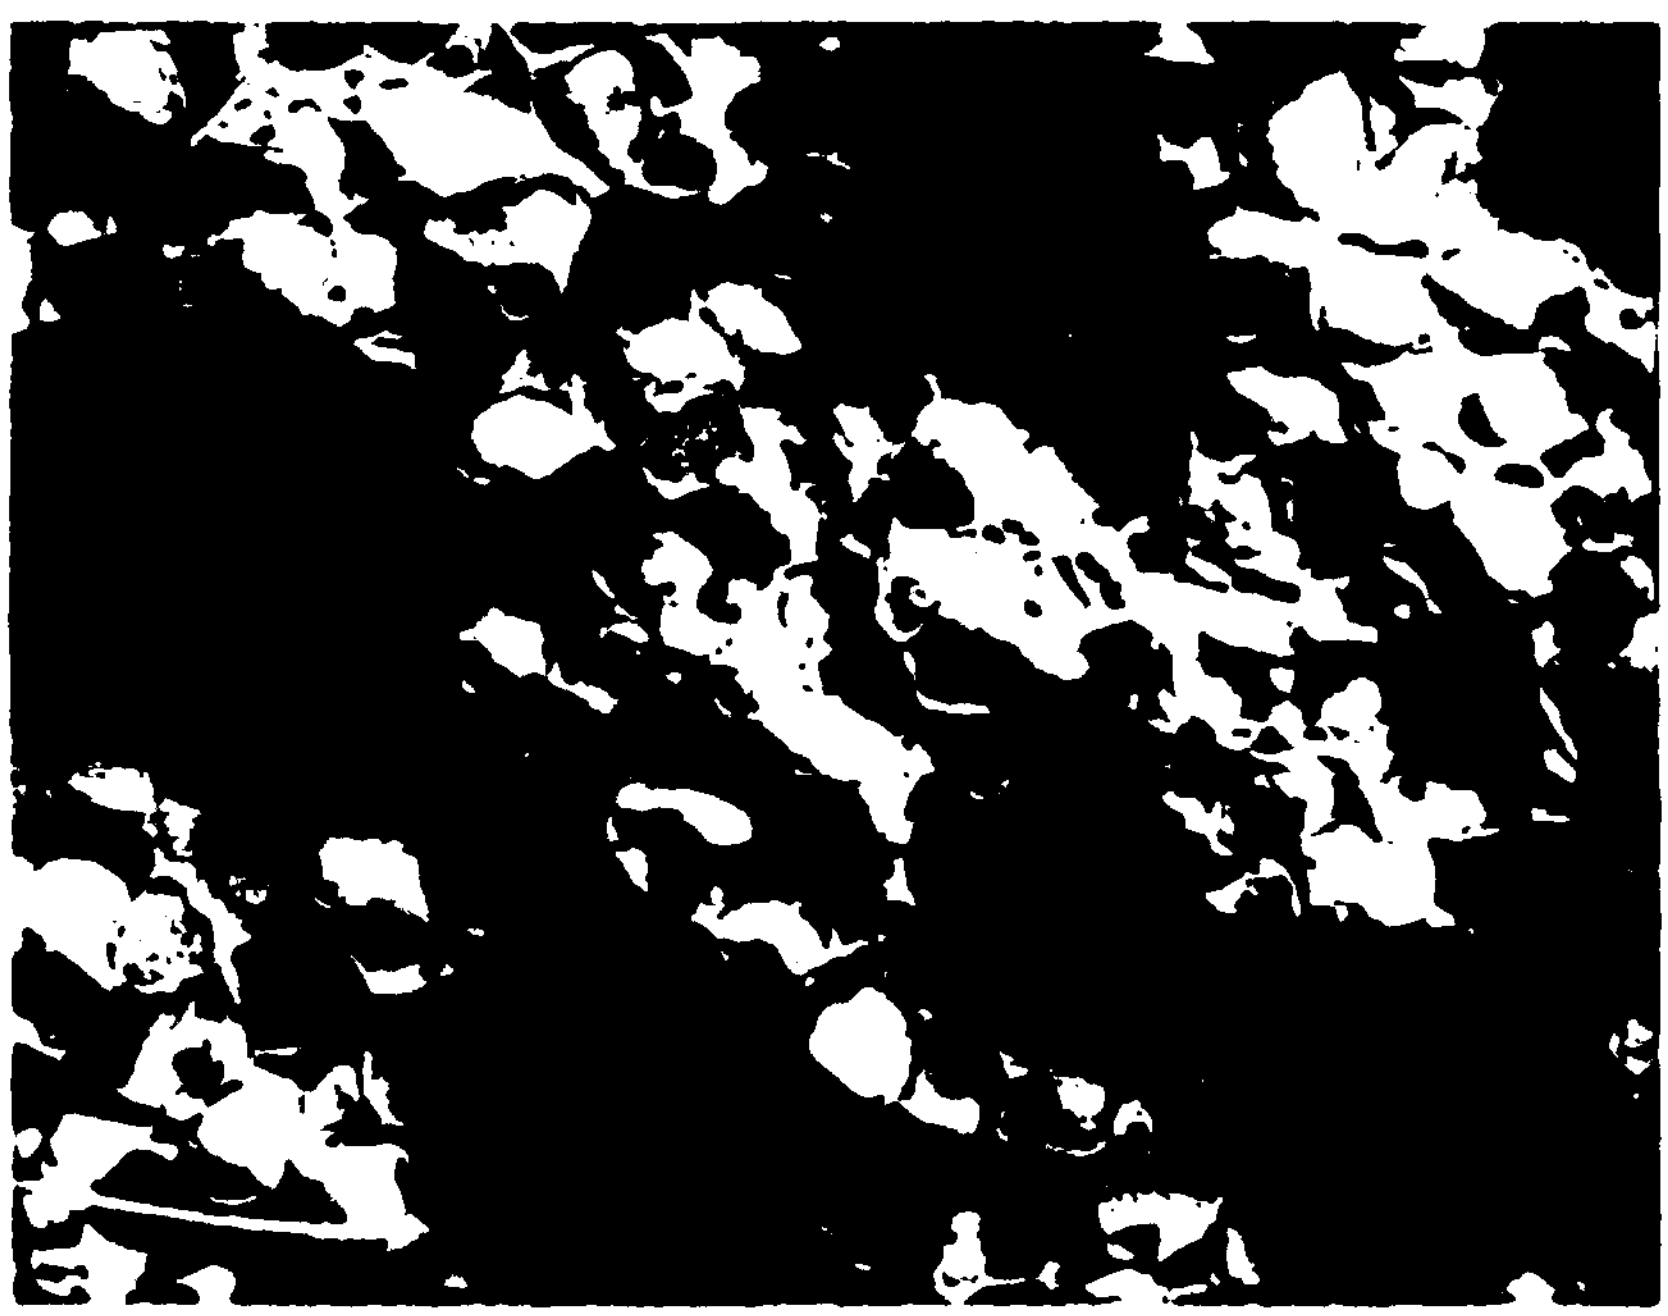

Figure 26. Fracture surface of replacement material.

Test results on a series of tungsten alloys ranging in tungsten content from 75% to 90% are submitted herein. Tensile and compressive data did not reveal unusual variations in material properties. To assess the sensitivity of the small variations observed, it will be necessary to relate the data in this report to the ballistics results as they become available.

DISTRIBUTION LIST

No. of Copies	Organization
12	Administrator Defense Technical Info Center ATTN: DDC-DDA Cameron Station Alexandria, VA 22304-6145
1	Deputy Assistant Secretary of the Army (R&D) Department of the Army Washington, DC 20310
1	HQDA (DAMA-ARP-P, Dr. Watson) Washington, DC 20310
1	HQDA DAMA-ART-M Washington, DC 20310
1	HQDA (DAMA-MS) Washington, DC 20310
1	Commander US Army War College ATTN: Lib Carlisle Barraacks, PA 17013
1	Commander US Army Command and General Staff College ATTN: Archives Fort Leavenworth, KS 66027
1	Commander US Army Materiel Command ATTN: AMCDRA-ST 5001 Eisenhower Avenue Alexandria, VA 22333-0001
2	Commander Armament R&D Center US Army AMCCOM ATTN: SMCAR-TSS Dover, NJ 07801-5001
1	Commander Benet Weapons Laboratory ATTN: Dr. E. Schneider Watervliet, NY 12189
1	Director Benet Weapons Laboratory Armament R&D Center US Army AMCCOM ATTN: SMCAR-LCB-TL Watervliet, NY 12189
1	Commander US Army Armament, Munitions and Chemical Command ATTN: SMCAR-ESP-L Rock Island, IL 61299-7300
1	Commander US Army Aviation Research and Development Command ATTN: AMSAV-E 4300 Goodfellow Boulevard St. Louis, MO 63120
1	Director US Army Air Mobility Research and Development Command Ames Research Center Moffett Field, CA 94035
1	Commander US Army Communications - Electronics Command ATTN: AMSEL-ED Fort Monmouth, NJ 07703-5301
1	Commander US Army Electronics Research and Development Command Technical Support Activity ATTN: DELSD-L Fort Monmouth, NJ 07703-5301

DISTRIBUTION LIST

No. of Copies	Organization
1	Commander Harry Diamond Laboratory ATTN: SLCHD-TA-L 2800 Powder Mill Road Adelphi, MD 20783
1	Commander MICOM Research, Development and Engineering Center ATTN: AMSMI-RD Redstone Arsenal, AL 35898-5500
1	Commander Missile and Space Intelligence Center ATTN: AIAM-S-YDL Redstone Arsenal, AL 35898-5500
3	Director BMD Advanced Technology Center ATTN: ATC-T, M. Capps ATC-M, S. Brockway ATC-RN, P. Boyd P.O. Box 1500 Huntsville, AL 35807
1	Director US Army Ballistic Missile Defense Systems Office 1320 Wilson Boulevard Arlington, VA 22209
2	Commander US Army Mobility Equipment Research & Development Command ATTN: DRDME-WC DRSME-RZT Fort Belvoir, VA 22060
1	Commander US Army Natick Research and Development Center ATTN: DRXRE, Dr. D. Sieling Natick, MA 01762

No. of Copies	Organization
1	Commander US Army Tank Automotive Command ATTN: AMSTA-TSL Warren, MI 48397-5000
1	Commander USAG ATTN: Tech Lib Fort Huachuca, AZ 85613-6000
1	Commandant US Army Infantry School ATTN: ATSH-CD-CSO-OR Fort Benning, GA 31905
1	Director US Army Advanced BMD Technology Center ATTN: CRDABH-5, W. Loomis P. O. Box 1500, West Station Huntsville, AL 35807
1	Director US Army TRADOC Systems Analysis Activity ATTN: ATAA-SL White Sands Missile Range, NM 88002
1	Commander Laboratory Command Materials Technology Laboratory ATTN: AMXMR-H, S. C. Chou Watertown, MA 02172-0001
1	Commander US Army Research Office ATTN: Dr. R. Weigle P. O. Box 12211 Research Triangle Park, NC 27709

DISTRIBUTION LIST

No. of Copies	Organization
1	Commander US Army Development and Employment Agency ATTN: MODE-TED-SAB Fort Lewis, WA 98433
1	Director US Army TRADOC Systems Analysis Activity ATTN: ATAA-SL White Sands Missile Range NM 88002
1	Commandant US Army Infantry School ATTN: ATSH-CD-CSO-OR Fort Benning, GA 31905
1	Office of Naval Research Department of the Navy ATTN: Code 402 Washington, DC 20360
1	Commander Naval Surface Weapons Center ATTN: Code Gr-9, Dr. W. Soper Dahlgren, VA 22448
1	Commander and Director US Naval Electronics Laboratory San Diego, CA 92152
5	Commander US Naval Research Laboratory ATTN: C. Sanday R. J. Weimer Code 5270, F. MacDonald Code 2020, Tech Lib Code 7786, J. Baker Washington, DC 20375
1	AFATL (DLDG) Eglin AFB, FL 32542-5000
1	Air Force Armament Laboratory ATTN: AFATL/DLODL Eglin AFB, FL 32542-5000
1	AFATL (DLYW) Eglin AFB, FL 32542
1	RADC (EMTLD, Lib) Griffiss AFB, NY 13440
1	AFWL/SUL Kirtland AFB, NM 87117
1	AUL (3T-AUL-60-118) Maxwell AFB, AL 36112
1	AFFDL/FB, Dr. J. Halpin Wright-Patterson AFB, OH 45433
5	Sandia National Laboratories ATTN: Dr. L. Davison Dr. P. Chen Dr. W. Herrmann Dr. C. Harness H.J. Sutherland P. O. Box 5800 Albuquerque, NM 87185
2	Forestal Research Center Aeronautical Engineering Lab. Princeton University ATTN: Dr. S. Lam Dr. A. Eringen Princeton, NJ 08540
1	Southwest Research Institute Department of Mechanical Sciences ATTN: Dr. U. Kindholm Dr. W. Baker 8500 Culebra Road San Antonio, TX 78228
1	Wilfred Baker Engineering P. O. Box 6477 San Antonio, TX 78209

DISTRIBUTION LIST

No. of Copies	Organization	No. of Copies	Organization
	Aberdeen Proving Ground		
	Dir, USAMSAA ATTN: AMXSY-D AMXSY-MP, H. Cohen		
	Cdr, USATECOM ATTN: AMSTE-TO-F		
	Cdr, CRDC, AMCCOM ATTN: SMCCR-RSP-A SMCCR-MU SMCCR-SPS-IL		

USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. BRL Report Number____________________ Date of Report__________

2. Date Report Received________________________________

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.)______________

4. How specifically, is the report being used? (Information source, design data, procedure, source of ideas, etc.)____________________

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided or efficiencies achieved, etc? If so, please elaborate.____________________

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.)

CURRENT ADDRESS

Name

Organization

Address

City, State, Zip

7. If indicating a Change of Address or Address Correction, please provide the New or Correct Address in Block 6 above and the Old or Incorrect address below.

OLD ADDRESS

Name

Organization

Address

City, State, Zip

(Remove this sheet, fold as indicated, staple or tape closed, and mail.)

FOLD HERE

Director
US Army Ballistic Research Laboratory
ATTN: DRXBR-OD-ST
Aberdeen Proving Ground, MD 21005-5066

NO POSTAGE NECESSARY IF MAILED IN THE UNITED STATES

OFFICIAL BUSINESS

PENALTY FOR PRIVATE USE, $300

BUSINESS REPLY MAIL

FIRST CLASS PERMIT NO 12062 WASHINGTON,DC

POSTAGE WILL BE PAID BY DEPARTMENT OF THE ARMY

Director
US Army Ballistic Research Laboratory
ATTN: DRXBR-OD-ST
Aberdeen Proving Ground, MD 21005-9989

FOLD HERE

END
11-87
DTIC